

**STRUCTURAL AND ELECTRICAL STUDY OF Nd³⁺ DOPED BaBi₂Nb₂O₉
AURIVILLIUS CERAMIC FOR ENERGY STORAGE APPLICATIONS**

THESIS

**SUBMITTED IN PARTIAL FULFILLMENT OF THE REQUIREMENTS FOR
THE AWARD OF THE DEGREE**

**MASTER OF SCIENCE
IN
PHYSICS**

Submitted by:
HELNA BENNY
24/MSCPHY/47
&
MAHIMA MOMALIYA
24/MSCPHY/31

Under the supervision of
DR. RENUKA BOKOLIA
ASSISTANT PROFESSOR



DEPARTMENT OF APPLIED PHYSICS
DELHI TECHNOLOGICAL UNIVERSITY
(Formerly Delhi College of Engineering)
Bawana Road, Delhi—110042
MAY, 2026

DEPARTMENT OF APPLIED PHYSICS
DELHI TECHNOLOGICAL UNIVERSITY
(Formerly Delhi College of Engineering)
Bawana Road, Delhi – 110042

CANDIDATE'S DECLARATION

We Helna Benny, Roll No. 24/MSCPHY/47, and Mahima Momaliya, Roll No. 24/MSCPHY/31, students of M.Sc. physics, hereby declare that the project dissertation titled “**Structural and electrical study of Nd³⁺ doped BaBi₂Nb₂O₉ Aurivillius ceramic for energy storage applications**” submitted by us to the Department of Applied Physics, Delhi Technological University, Delhi, in partial fulfilment of the requirement for the award of the degree of Master of Science, is an original work carried out by us and has not been plagiarised or copied from any source without proper citation . This work has not previously formed the basis for the award of any Degree, Diploma, Associateship, Fellowship or other similar title or recognition.

Place: Delhi

Date: 28/05/2026



Helna Benny



Mahima Momaliya

DECLARATION AND SUPERVISOR'S CERTIFICATE

We, **Helna Benny, Roll No. 24/MSCPHY/47, and Mahima Momaliya, Roll No.24/MSCPHY/31** hereby certify that the work which is presented in the Dissertation-II entitled in fulfillment of the requirement for the award of the Master in Science in **Physics** and submitted to the Department of **Applied Physics**, Delhi Technological University, Delhi is an authentic record of our own, carried out during a period from January 2026 to May 2026 under the supervision of **Dr. Renuka Bokolia**. The matter presented in this report/thesis has not been submitted by us for the award of any other degree of this or any other Institute/University. The work has been accepted in peer-reviewed SCI/Scopus indexed journals with the following details:

Title of paper: Bi-site Nd^{3+} substitution–induced dielectric relaxation and enhanced energy storage performance in $\text{BaBi}_2\text{Nb}_2\text{O}_9$ layered ceramics.

Author names (in sequence as per research paper): Helna Benny, Mahima Momaliya, Surya Pratap Singh, Ravindra Kumar, Manoj Verma, Renuka Bokolia

Name of Conference/Journal: Ceramics International (Elsevier)

Status of paper (Accepted/Published/Communicated): Accepted ■

Date of paper communication: : February 23, 2026

Date of First revision (completion) : May 15, 2026

Date of Second revision (completion): May 25, 2026

Date of paper acceptance: May 26, 2026

Title of paper: X-Ray Diffraction-Based Structural Optimization and Electrical Properties of Nd^{3+} Doped $\text{BaBi}_2\text{Nb}_2\text{O}_9$ Aurivillius Ceramics.

Author names (in sequence as per research paper): Mahima Momaliya, Helna Benny, Surya Pratap Singh, Manoj Verma, Renuka Bokolia

Name of Conference/Journal: Indian Journal of Pure & Applied Physics

Status of paper (Accepted/Published/Communicated): Communicated

Date of paper communication: : April 20, 2026

Date of First revision: May 18, 2026

Name of Conference: International Conference on Atomic, Molecular, Nano & Optical Physics with Applications (IAMNOP-2025)

Conference Dates with venue (if applicable): School of Physical Sciences, Jawaharlal Nehru University (JNU) , December 17th to 19th, 2025 at the Convention Centre, JNU.

Have you registered for conference (Yes/No)?: Yes

Status of paper (Accepted/Published/Communicated): N/A



Helna Benny
(24/MSCPHY/47)



Mahima Momaliya
(24/MSCPHY/31)

SUPERVISOR CERTIFICATE

To the best of my knowledge, the above work has not been submitted in part or full for any Degree or Diploma to this University or elsewhere. I further certify that the publication and indexing information given by student(s) is correct.

A handwritten signature in blue ink, reading "Renuka", with a long horizontal line extending from the end of the name.

Place: New Delhi
Date: 28 May 2026

DR. RENUKA BOKOLIA
(SUPERVISOR)

DEPARTMENT OF APPLIED PHYSICS
DELHI TECHNOLOGICAL UNIVERSITY

(Formerly Delhi College of Engineering)

Bawana Road, Delhi-110042

CERTIFICATE

I hereby certify that the project dissertation titled "**Structural and electrical study of Nd³⁺ doped BaBi₂Nb₂O₉, Aurivillius ceramic for energy storage applications**" which is submitted by HELNA BENNY, Roll No. (s) 24/MSCPHY/47 and MAHIMA MOMALIYA, 24/MSCPHY/31, Department of Applied Physics, Delhi Technological University, Delhi in partial fulfillment of the requirement for the award of the degree of Master of Science, is a record of the project work carried out by the students under my supervision. To the best of my knowledge, this work has not been submitted in part or full for any degree or diploma to this university or elsewhere.

Place: Delhi



Date: 28/05/2026

DR. RENUKA BOKOLIA
SUPERVISOR

ACKNOWLEDGEMENTS

We would like to express our sincere gratitude to our supervisor, Dr. Renuka Bokolia, Assistant Professor, Department of Applied Physics, Delhi Technological University, for giving us the opportunity to work under her guidance and for her constant inspiration and incessant support throughout the project. We also sincerely thank Mr. Surya Pratap Singh (Ph.D. Scholar) for his continuous guidance, support, and encouragement throughout our research journey. We take this opportunity to express our indebtedness to our supervisor for her enthusiastic help, expertise, brilliant ideas, valuable suggestions, and constant encouragement. We are also grateful to Dr. Manoj Verma, Assistant Professor, University of Delhi, for his valuable assistance and support during this work. We gratefully acknowledge the constant help and cooperation provided by all the lab members, Mr. Ravinder Kumar, Mr. Alok Yadav, and Ms. Diksha (Ph.D. Scholars), Department of Applied Physics, at every step of our project.

Personal Acknowledgements

Mahima Momaliya [24/MSCPHY/31]

I would like to express my deepest gratitude to my parents, Hony/Capt. Mohan Lal and Mrs. Manju Bala, for their unconditional love, sacrifices and encouragement. Their faith in me has always been my greatest strength. I am also thankful to my brother, Mohit Momaliya, for his constant support and motivation. Lastly, I sincerely acknowledge Pankaj for his encouragement, understanding, and support during the completion of this work.

Helna Benny [24/MSCPHY/47]

I would like to express my heartfelt gratitude to my parents, Mr. Benny N. J. and Mrs. Tessy V. V., for their constant love, encouragement, and support throughout my academic journey. I also sincerely thank my brother, Helbin Benny, and my friends for their motivation, support, and encouragement during the completion of this thesis. Finally, I extend my gratitude to all my teachers and everyone who directly or indirectly contributed to this work.



Helna Benny



Mahima Momaliya

TABLE OF CONTENTS

List of Figures	viii
List of Tables	x
Abstract	xi
CHAPTER 1: INTRODUCTION	1
1.1 Background	1
1.2 Literature Review I	3
1.3 Literature Review II	4
1.4 Research Objectives	5
CHAPTER 2: EXPERIMENTAL METHODOLOGY	6
2.1 Materials and Reagents	6
2.2 Synthesis Method	6
2.3 Characterisation Techniques	7
CHAPTER 3: RESULTS AND DISCUSSION	9
3.1 X-ray Diffraction Analysis	9
3.1.1 Optimisation of Calcination Conditions	9
3.1.2 Optimisation of Sintering Conditions	10
3.1.3 Phase Analysis of Nd-Doped BBN Ceramics	12
3.2 SEM Analysis	13

3.3 Density and Porosity Analysis	15
3.4 DC conductivity	16
3.5 Analysis of Fourier transform infrared	17
3.6 Raman Spectroscopy	20
3.7 Diffuse Reflectance Spectroscopy and Band Gap Analysis	23
3.8 Ferroelectric Properties (P–E Analysis)	27
3.9 Dielectric Studies	31
CHAPTER 4: CONCLUSION	35
CHAPTER 5: FUTURE SCOPE	37
CHAPTER 6: REFERENCES	39
PLAGIARISM REPORT.....	44
AI REPORT.....	51
JOURNAL INDEX PROOFs.....	53
Accepted Research Article in <i>Ceramics International proofs</i>.....	55
Manuscript Status in Indian Journal of Pure and Applied Physics...	57
APPENDICES.....	58

LIST OF FIGURES

- Fig. 1.1 Structural, electrical, and optical properties of Aurivillius $\text{BaBi}_2\text{Nb}_2\text{O}_9$ ceramics.
- Fig. 1.2 Ferroelectric hysteresis loop (P–E) of $\text{SrBi}_{2-x}\text{Nd}_x\text{Nb}_2\text{O}_9$
- Fig. 2.1 Schematic representation of synthesis of Nd-doped BBN ceramics
- Fig. 3.1 XRD patterns of $\text{BaBi}_2\text{Nb}_2\text{O}_9$ ceramics showing (a) temperature optimization for calcination and (b) elimination of impurity phase upon addition of 2 wt.% excess Bi_2O_3 at 950°C
- Fig. 3.2 XRD patterns of $\text{BaBi}_2\text{Nb}_2\text{O}_9$ ceramics sintered at 1000°C , 1050°C , and 1100°C showing the effect of sintering temperature on phase purity
- Fig. 3.3 XRD plot of all compositions of BBN
- Fig. 3.4 SEM micrograph of all compositions of BBN
- Fig. 3.5 Histograms of particle sizes obtained from SEM images of (a) BBNB0, (b) BBNB1, (c) BBNB2, (d) BBNB3, and (e) BBNB4 ceramics are shown. The solid curves represent Gaussians, which were fitted to get the average particle size.
- Fig. 3.6 Porosity measuring apparatus
- Fig. 3.7 FTIR spectra of BBNB0 and BBNB1 samples
- Fig. 3.8 FWHM analysis of FTIR absorption bands of BBNB0
- Fig. 3.9 FWHM analysis of FTIR absorption bands of BBNB1
- Fig. 3.10 Stacked Raman spectra of BBNB0–BBNB4 samples recorded at room temperature
- Fig. 3.11 Evolution of Raman peak positions (ν_1 – ν_9) as a function of composition
- Fig. 3.12 Tauc plots of doped and undoped BBN samples
- Fig. 3.13 P–E loop measurement instrument
- Fig. 3.14 P–E hysteresis loops of all BBN compositions

- Fig. 3.15 Comparison bar graphs of total energy (W), efficiency (η), and recoverable energy (Wrec)
- Fig. 3.16 (a) Temperature-dependent P–E loops, (b) variation of Pr, Pm, Wrec and η , (c) fatigue behaviour of P–E loops, and (d) dependence of Pr, Pm, Ec and leakage current on cycle number
- Fig. 3.17 Dielectric measurement instrument
- Fig. 3.18 Dielectric constant versus temperature and frequency plots of $\text{BaBi}_{2-x}\text{Nd}_x\text{Nb}_2\text{O}_9$
- Fig. 3.19 Dielectric loss versus temperature for all compositions of BBN
- Fig. 3.20 Modified Curie–Weiss plots of BBN ceramics

List of Tables

Table 1.1	Refinement and lattice parameters, experimental density, and grain size of all compositions of BBN
Table 3.1	Lattice parameters of all compositions of BBN
Table 3.2	Average grain size, density, porosity, resistivity, and conductivity of undoped and Nd-doped BBN ceramics
Table 3.3	Vibrational modes, corresponding wavenumbers, and FWHM values of FTIR absorption bands for BBNB0 and BBNB1
Table 3.4	Nb–O bond length estimated from Raman stretching mode using Herschbach’s empirical relation
Table 3.5	Raman mode assignments of the BBNB0 sample showing peak position, vibrational origin, and corresponding bonding units
Table 3.6	Optical band gap (E_g) measurements for BBNB0–BBNB4 samples determined from UV–Vis diffuse reflectance spectra
Table 3.7	P–E parameters of all compositions of BBN

**STRUCTURAL AND ELECTRICAL STUDY OF Nd³⁺ DOPED
BaBi₂Nb₂O₉ AURIVILLIUS CERAMIC FOR ENERGY STORAGE
APPLICATIONS**

Helna Benny, Mahima Momaliya

ABSTRACT

In this work, neodymium (Nd³⁺)-substituted barium bismuth niobate ceramics, BaBi_{2-x}Nd_xNb₂O₉ (x = 0.00, 0.04, 0.06, 0.08, and 0.10), belonging to the Aurivillius family, were systematically investigated to examine the influence of Bi-site doping on the structural, dielectric, and energy-storage properties. All compositions were synthesized via the conventional solid-state route and sintered at 1050 °C. XRD analysis confirmed the formation of a single-phase orthorhombic Aurivillius structure, indicating successful incorporation of Nd³⁺ with minimal lattice distortion. SEM analysis revealed plate-like grains with a reduction in grain size upon doping. FTIR analysis confirmed the retention of characteristic NbO₆ vibrational bands, indicating preservation of the layered Aurivillius framework after Nd³⁺ substitution. Dielectric studies exhibited broad, frequency-dependent peaks, confirming relaxor behavior with the diffuseness parameter γ ranging from 1.45 to 1.75. DC conductivity decreased with increasing Nd content due to enhanced resistivity. Slim P–E loops with reduced remnant polarization favored energy-storage performance, with BaBi_{1.94}Nd_{0.06}Nb₂O₉ exhibiting an efficiency exceeding 90%. Raman and DRS analyses confirmed the preservation of the crystal structure and tunable band gaps, highlighting the strong potential of these ceramics for lead-free energy-storage application

CHAPTER 1

INTRODUCTION

1.1 BACKGROUND

Ferroelectric ceramics are materials that naturally develop an electric polarisation, which can be reversed by applying an external electric field [1]. Dipoles are aligned in certain directions in tiny domains. In ferroelectric ceramics, the electric polarisation is inherently present but can be altered by applying an electric field. Dipoles are oriented in specific directions in these ceramics. As a result, these features are widely used in sensors, actuators, capacitors, and memory devices. Due to their strong polarisation, ease of adjustment with an electric field, and ability to control their domain structure, these materials are often selected as host materials [2]. Additionally, they are multifunctional, showing electrical, optical, piezoelectric, and pyroelectric properties. Therefore, ferroelectric ceramics provide better energy storage, switchable polarisation for memory applications, and useful sensing properties for various electronic and thermal devices. Rare earth elements are often used as dopants in ferroelectric ceramics because they significantly improve the material's overall performance. Their addition helps introduce relaxor type behavior, which leads to broader and more stable phase transitions [3]. Rare-earth doping also enhances dielectric properties, making the material more suitable for energy storage applications. These elements help stabilize ferroelectric polarisation, improve grain growth control, and allow better tuning of the microstructure. Another important benefit is the reduction of leakage current, which increases the efficiency and reliability of devices. In addition, rare-earth dopants improve the thermal stability of the material, making it more effective for high-temperature and high-performance applications [4].

Recently, lead-free materials have been getting more attention in the research world due to the various environmental and health issues caused by lead, and it has taken a diversion towards the Aurivillius compounds, which is the family of bismuth layered perovskite type oxides having the general formula $(\text{Bi}_2\text{O}_2)^{2+}(\text{A}_{n-1}\text{B}_n\text{O}_{3n+1})^{2-}$ [5, 6]. The A site cations are usually the large ions or the rare earth ions, which are ionically compatible with Bi^{3+} in the $(\text{Bi}_2\text{O}_2)^{2+}$ layers, whereas the B-site cations are smaller ions. The value of n indicates the number of perovskite layers sandwiched between Bi_2O_2

sheets. Here, we investigate barium bismuth niobate, generally abbreviated as BBN, where the value of n is 2, implying it has two perovskite-like layers between the $(\text{Bi}_2\text{O}_2)^{2+}$ sheets [7-9]. BBN is a relaxor ferroelectric having larger maximum polarisation and less remnant polarisation, and thus coming under the category of Bismuth Layered Structured Ferroelectrics, abbreviated as BLSF [9], BLSFs are considered strong alternatives to lead-based ceramics because they are non-toxic and environmentally friendly. This makes them a better and safer option for modern applications. Lead-free BLSF materials have gained a lot of interest since they offer several useful properties, such as a relatively high dielectric constant, resistance to fatigue, high phase transition temperatures, good electromechanical anisotropy, and excellent stability over a wide temperature range [10-12]. Neodymium (Nd^{3+}) is selected because of its limited published work, specifically Nd-doped BBN. Prior studies on Nd-doped $\text{SrBi}_2\text{Nb}_2\text{O}_9$ (SBN) and related Aurivillius-type compounds have shown enhanced ferroelectric, dielectric, and fatigue endurance because of a reduction in the generation of unwanted oxygen vacancies, which improves dielectric stability and optical properties due to its characteristic 4f-4f transitions in the near infrared region (NIR)[13]. This provided a strong foundation for expecting similar or improved behaviour in Nd-doped BBN systems as well. Also, neodymium has an identical valence state to Bi^{3+} and ionic radius very close to BBN ($\text{Nd}^{3+} \approx 1.11 \text{ \AA}$; $\text{Bi}^{3+} \approx 1.17 \text{ \AA}$ for 12 coordination number), which allows substitution without significant lattice distortion. This reduced distortion leads to better lattice symmetry and thermal stability. This research explores the incorporation of Nd^{3+} (0.04, 0.06, 0.08, 0.10) into the BBN matrix to fine-tune the structural, ferroelectric, and dielectric properties employing techniques such as X-ray diffraction, scanning electron microscopy, Fourier transform infrared spectroscopy, diffuse reflectance spectroscopy, Raman spectroscopy, polarisation electric field characterisation and dielectric spectroscopy to illuminate these effects. Barium bismuth niobate ($\text{BaBi}_2\text{Nb}_2\text{O}_9$) finds applications in ferroelectric memories [FeRAM], high-temperature piezoelectric sensors, dielectric capacitors, and energy-related devices due to its robust polarisation, thermal stability, and layered perovskite structure.

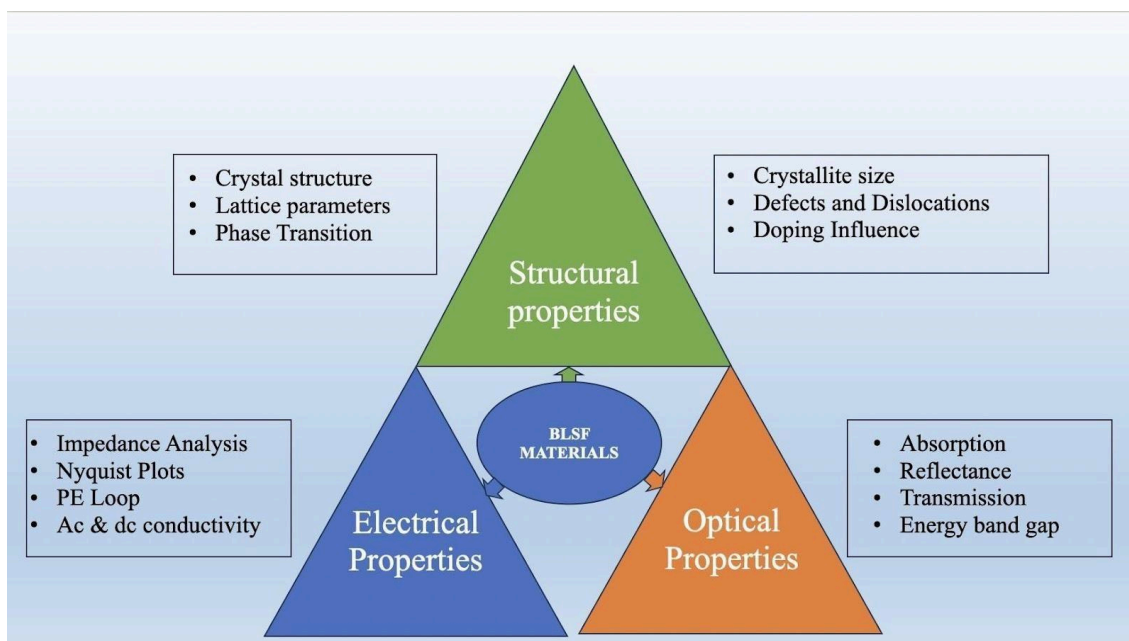


Fig. 1.1 Structural, electrical, and optical properties of Aurivillius $BaBi_2Nb_2O_9$ ceramics.

1.2 LITERATURE REVIEW 1

Temperature stability and improved energy storage efficiency of

$BaBi_2Nb_2O_9$: Er^{3+}/Yb^{3+} relaxor ferroelectric ceramic under moderate electric fields. [9]

Ankita Banwal · Manoj Verma · Bharti Singh · Renuka Bokolia

Table 1.1 Refinement and lattice parameters, experimental density, and grain size of all compositions of BBN

Samples	Refinement parameters			Lattice parameters						
	R_{exp}	R_p	GoF	a (Å)	b (Å)	c (Å)	V (Å ³)	Orthorhombic distortion (b/a)	Exp. density, ρ (g/cm ³)	Average grain size
BBNE0Y0	10.76	12.84	1.02	5.5439	5.5536	25.5975	788.111	1.00174	7.00919	1.39 ± 0.0278
BBNE4Y0	11.57	13.59	1.05	5.5441	5.5550	25.5976	788.341	1.00196	6.87240	1.42 ± 0.014
BBNE4Y2	10.39	14.93	1.46	5.5448	5.5551	25.5980	788.467	1.00185	6.83796	1.54 ± 0.0125
BBNE4Y4	10.13	13.53	1.35	5.5450	5.5552	25.5989	788.537	1.00183	6.72015	1.67 ± 0.1365
BBNE4Y6	10.01	14.46	1.44	5.5454	5.5561	25.5991	788.728	1.00192	6.77289	1.78 ± 0.0889
BBNE4Y8	7.07	8.64	1.07	5.5479	5.5601	25.6178	790.229	1.00219	6.47426	1.89 ± 0.1129
BBNE4Y10	7.27	9.19	1.08	5.5488	5.5612	25.6200	790.581	1.00223	6.76007	1.92 ± 0.1761
BBNE4Y12	10.21	14.87	1.45	5.5497	5.5600	25.6219	790.597	1.00185	6.01060	1.45 ± 0.0295

- Ankita and Renuka Bokolia reported that undoped, Er^{3+} -doped, and Er^{3+}/Yb^{3+} co-doped $BaBi_{2-x-y}Nb_2Er_xYb_yO_9$ ceramics show orthorhombic Fmmm symmetry with dense, square-like grains. FTIR confirmed Aurivillius peaks at 619 and 822 cm^{-1} , while Raman spectra increased from 4 modes (undoped) to 12 modes (doped). Nb–O bond lengths at 840 cm^{-1} were calculated using Herschbach's exponential relation.

- According to the authors, dielectric studies showed strong dispersion around T_m , frequency-dependent ϵ' decrease, and diffused ϵ'' peaks, all confirming relaxor ferroelectric behaviour. Doping strengthened diffuseness and modified polar nanoregions.
- The authors highlighted thin P–E loops at 75–100 kV/cm and calculated W , W_{rec} , and η using P_m and P_r . Undoped, Er^{3+} doped, and Er^{3+}/Yb^{3+} co-doped BBN showed values of (0.683, 0.534, 78.25%), (0.471, 0.392, 83.39%), and (0.508, 0.461, 90.87%), respectively.
- They concluded that energy parameters were thermally stable (303–415 K) with only $\sim 0.03\%$ variation. While W and W_{rec} remained comparable, η increased with doping, and BBNE4Y4 showed the best ϵ' , diffuseness, and efficiency—suitable for advanced energy-storage applications.

1.3 LITERATURE REVIEW 2

Structural and ferroelectric modifications in $SrBi_2Nb_2O_9$ Aurivillius phase compounds by Nd^{3+} ion doping. [13]

-Zulhadjri*, Alfir Rizki, Tio Putra Wendari, Yulia Eka Putri

- Zulhadjri reported that Nd^{3+} -doped $SrBi_{2-x}Nd_xNb_2O_9$, synthesised via the molten salt method, retained a single-phase orthorhombic Aurivillius structure (A21am). Increasing Nd^{3+} reduced unit cell volume and orthorhombicity, confirming successful Bi-site substitution without disturbing the perovskite layer.
- all samples displayed the typical plate-like morphology of Aurivillius materials, while FTIR results confirmed the preservation of perovskite-layer bonding. The dielectric response exhibited consistency. ferroelectric–paraelectric transition temperature (T_c), with higher Nd^{3+} levels promoting diffuse ferroelectric behaviour. These effects were attributed to the reduced influence of the $Bi^{3+} 6s^2$ lone pair and lowered lattice distortion. Nd^{3+} levels promoting diffuse ferroelectric behaviour. These effects were attributed to the reduced influence of the $Bi^{3+} 6s^2$ lone pair and lowered lattice distortion.
- Zulhadjri highlighted that P–E loops remained non-saturated, especially at $x = 0.275$, indicating diffuse ferroelectricity. Nd^{3+} incorporation effectively adjusted structural, dielectric, and ferroelectric properties, enhancing the material's potential for advanced ferroelectric applications.

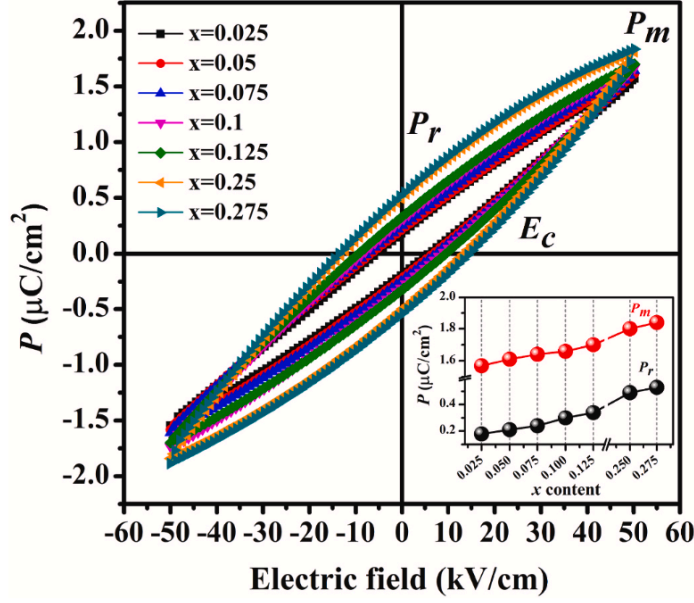


Fig. 1.2: Ferroelectric hysteresis loop (P - E) of $\text{SrBi}_{2-x}\text{Nd}_x\text{Nb}_2\text{O}_9$ measured at room temperature. The inset shows the polarisation (P_r and P_m) dependence on x content.

1.4 Research Objectives

- To synthesise single-phase Aurivillius-type $\text{BaBi}_2\text{Nb}_2\text{O}_9$ (BBN) ceramics doped with Nd^{3+} ions via solid state reaction method.
- Correlates microstructure and dielectric properties for different compositions of Nd^{3+} .
- To optimise the prepared compositions to attain maximum energy efficiency via the P - E hysteresis loop.
- Explore the possible applications in energy storage devices.

CHAPTER 2

EXPERIMENTAL METHODOLOGY

2.1 Materials and Reagents

Barium Carbonate [BaCO_3] (99%), Bismuth(iii)oxide [Bi_2O_3] (99.975%), Neodymium Oxide [Nd_2O_3] (99.99%), Niobium(V) Oxide [Nb_2O_5] (99.99%) were purchased from Sigma Aldrich.

2.2 Synthesis Methods

Solid-state method

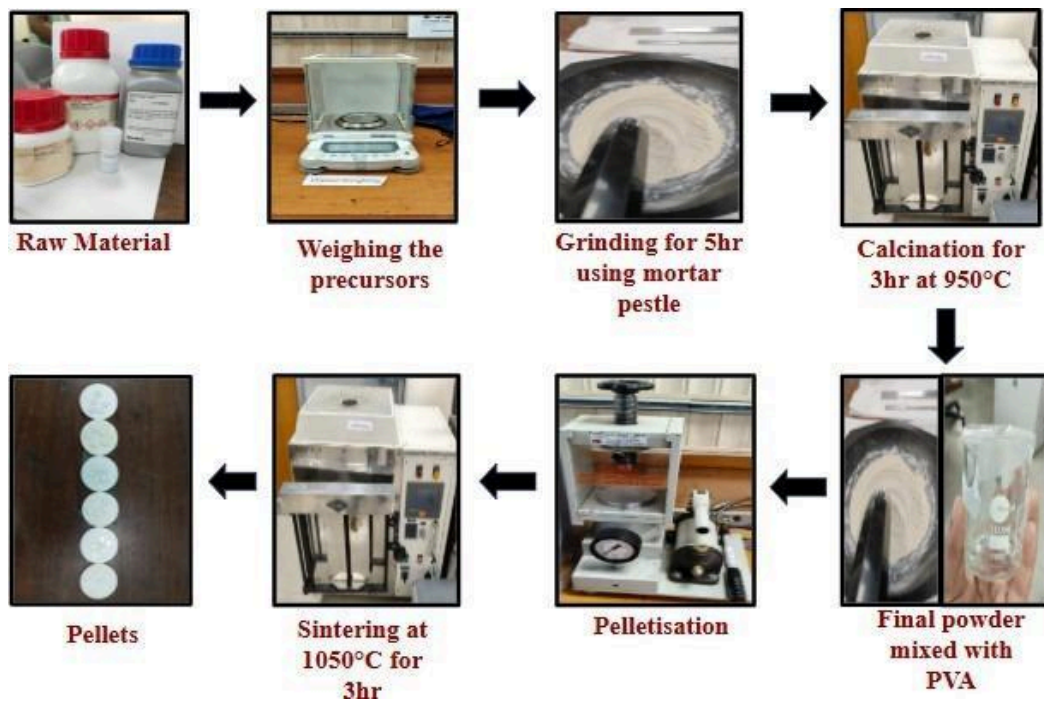


Fig. 2.1: Pictorial representation of synthesis of $\text{BaBi}_2\text{Nb}_2\text{O}_9$ (BBN) ceramics doped with Nd^{3+} ions.

The $\text{BaBi}_2\text{Nb}_2\text{O}_9$ (BBN) and $\text{BaBi}_{2-x}\text{Nb}_2\text{Nd}_x\text{O}_9$ ($x = 0.04, 0.06, 0.08, \text{ and } 0.1$) were synthesised by a conventional solid state method. Initially, the precursor powders were weighed stoichiometrically and ground thoroughly with a mortar and pestle for about 5 hrs by mixing ethanol (Sigma Aldrich) to maintain homogeneity of the sample. After drying, the sample was then subjected to calcination at 950°C for 3 hours in a closed alumina crucible. The calcined powders were then dry ground again to ensure uniformity. The polyvinyl alcohol (PVA) was added to the final powder as a temporary binder (3-4 drops) and ground to a fine powder, then pressed into pellets of different sizes according to the characterisation using a hydraulic press. These pellets were

sintered at 1050°C for 3 hours with a heating rate of 2°C per minute and 1 hour hold at 600°C for removing PVA in a high-temperature furnace to obtain the final $\text{BaBi}_{2-x}\text{Nb}_2\text{Nd}_x\text{O}_9$ ceramics. After this, the obtained pellets will be polished on both sides using sandpaper to get a smooth and uniform surface for electrical characterisation. Then the density and porosity were measured using Archimedes' principle with distilled water as the medium. Apart from that, the resulting samples were characterised for their structural and optical properties.

2.3 Characterisation Techniques

The crystal structure of the $\text{BaBi}_2\text{Nb}_2\text{O}_9$ and $\text{BaBi}_{2-x}\text{Nb}_2\text{Nd}_x\text{O}_9$ ($x = 0.04, 0.06, 0.08$, and 0.1) were studied using X-ray diffraction (XRD) with $\text{Cu K}\alpha$ radiation of wavelength $1.5402\text{ \AA}$. Surface morphology was studied using a scanning electron microscope (SEM), and we have done the imaging using secondary electron 1 (SE1) to provide the possible highest resolution and detailed surface topographical data. The study reveals the average grain size and grain boundary of the crystal. The densities of the ceramics were measured using Archimedes' method, and the porosities were estimated to analyse the densification process of the sintered materials.

DC electrical conductivity measurements were carried out using sintered pellet samples coated with silver paste on both sides to ensure good electrical contact during the measurement process.

Fourier transform infrared (FTIR) spectroscopy was utilised to characterise the vibration and bonding nature of the NbO_6 octahedral units. In this case, for FTIR measurement, the powder form of the samples prepared from the BBNB0 and BBNB4 compositions was selected. FTIR studies also facilitated the evaluation of local structural changes caused by Nd^{3+} ions.

Raman spectroscopic experiments were conducted at room temperature to probe the short-range ordering, lattice distortions, and local structural symmetry of the Nd-added ceramics. Further, the Raman results were interpreted to understand changes in vibration frequencies and Nb-O bonding.

The optical behavior of the prepared samples was determined by UV-visible diffuse reflectance spectroscopy (DRS). The optical bandgap energy was determined using the Kubelka–Munk function and Tauc plot analysis method to determine the effect of Nd doping on the electronic behavior of the material.

The ferroelectric nature of the sample was determined using Polarization-Electric Field (P-E) hysteresis loop analysis with respect to varying applied electric fields. In the case of P-E loops, the sintered pellets were mechanically polished and made thin to about 0.2 mm in thickness. On one surface of the sintered pellets, a paste of silver powder mixed with toluene was spread uniformly, whereas at the other surface, the silver-paste mixture was spread in the form of an electrode dot.

Dielectric (DE) studies were performed at wide temperatures and frequencies by employing an LCR meter to understand the properties of dielectric constant, dielectric losses, and phase transition in the ceramics. In the case of dielectric studies, pellets with a thickness of more than 0.7 mm were employed. The silver paste-toluene combination was applied to both faces of the pellet surface without going to the sides so that no edge conduction influence occurs. To analyse the relaxor behavior of the samples, the modified Curie-Weiss law was also considered.

CHAPTER 3

RESULTS AND DISCUSSION

3.1 X-ray Diffraction Analysis

3.1.1 Optimization of Calcination Conditions

Calcination conditions for obtaining pure-phase $\text{BaBi}_2\text{Nb}_2\text{O}_9$ ceramics had been optimized in terms of several variables, including calcination temperature, time period required for heating, heating rate, and precursor compositions. First, the variation in calcination temperatures ranging between 850 °C and 950 °C at a heating rate of 5 °C per minute was performed for 3 hours. The XRD results obtained on the calcined powders are compared with the JCPDS card no. 00-012-0403 [12], illustrated in Fig. 3.1(a).

All compositions exhibit the characteristic diffraction peaks of the Aurivillius layered perovskite structure. An improvement in peak sharpness and intensity is observed with increasing calcination temperature, indicating enhanced crystallinity. However, an additional impurity peak persists in all samples, suggesting incomplete phase formation.

From all the studied temperatures, 950°C was found to be the best calcination temperature since it gives a higher degree of crystallinity without exceeding the temperature where substantial evaporation of Bi_2O_3 begins to occur. The further optimization of calcination was performed at 950°C through changes in calcination time and heating rate. While the diffraction peaks were significantly sharpened, the impurity peak did not disappear. This suggests that the formation of impurities does not depend much on the heating rate but instead on the Bi deficiency resulting from Bi_2O_3 evaporation at high calcination temperatures.

The deficiency of Bi was addressed by adding 2 wt.% of excess Bi_2O_3 into the precursor formula, according to the literature reports that 2 wt.% is sufficient to yield phase-pure Aurivillius materials [13]. A smaller quantity of excess Bi_2O_3 may not suffice to cover the volatilization loss, while a larger quantity could cause segregation of Bi_2O_3 at grain boundaries, which would be harmful to the material's characteristics [13].

The XRD profile of the material obtained after calcination at 950 °C for 5 hours with a heating rate of 2 °C/min and 2 wt. % excess of Bi_2O_3 is presented in Fig. 3.1(b). It can be clearly observed that the absence of any impurity peaks signifies the formation of the pure phase Aurivillius-layered perovskite structure.

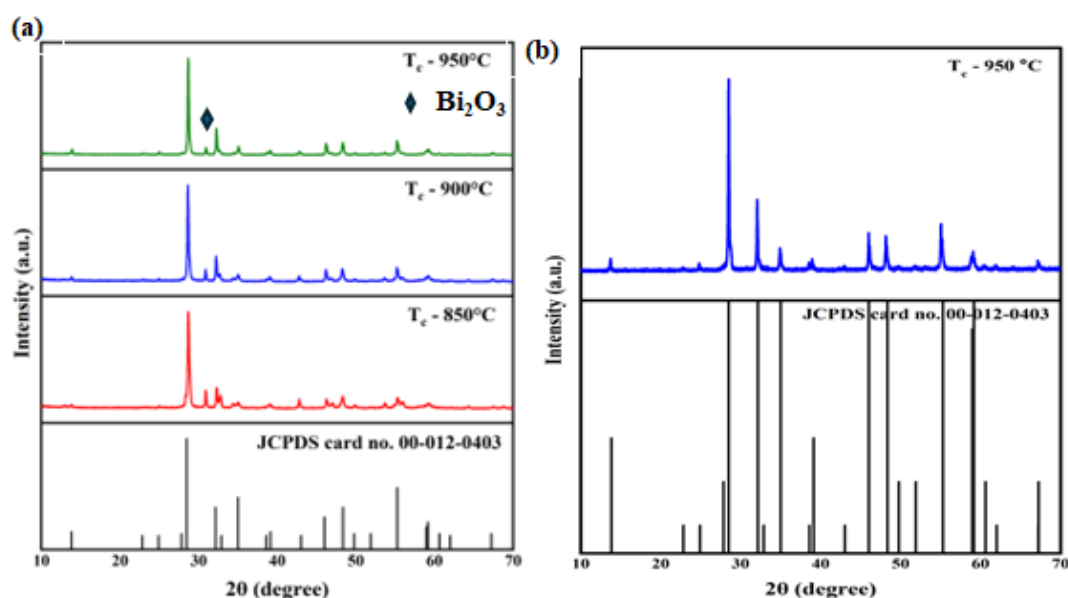


Fig. 3.1 XRD patterns of $\text{BaBi}_2\text{Nb}_2\text{O}_9$ ceramics showing (a) temperature optimization for calcination and (b) elimination of impurity phase upon addition of 2 wt% excess Bi_2O_3 at 950°C.

3.1.2 Optimization of Sintering Conditions

The optimum sintering temperature for $\text{BaBi}_2\text{Nb}_2\text{O}_9$ ceramics was investigated by subjecting pure BBN green pellets to sintering processes conducted at 1000 °C, 1050 °C, and 1100 °C. Sintering was done using a uniform rate of heating of 2 °C/min for 3 hours. Before undergoing the actual sintering process, pure BBN green pellets underwent pre-sintering treatment at 600 °C for 1 hour to eliminate any trace of PVA binder that might still be present in the sample [14]. This procedure ensures that no residual organic matter will contaminate the ceramic body.

Figure 3.2 displays the X-ray diffraction pattern for the sintered pellets in comparison with the standard JCPDS card number 00-012-0403. The XRD patterns of all the samples consist mainly of typical diffraction peaks of the Aurivillius perovskite layered structure. But there are differences in the location of the peaks and phase purity with variations in sintering temperature.

The sintered pellet at 1000 °C shows the presence of the Aurivillius phase; however, the diffraction peaks show a small right shift, suggesting that there is some lattice shrinkage. This could be due to the partial loss of Bi^{3+} cations during the sintering process, creating an A-site vacancy [12,15].

On the other hand, the XRD pattern of the 1050 °C sintered sample reveals distinct peaks in good agreement with the standard JCPDS database. However, for the 1100 °C sintered sample, besides the main Aurivillius peaks, some impurity peaks also become observable, which could imply that secondary phases have formed due to excess Bi evaporation at higher temperatures.

According to the above XRD results, 1050°C can be considered the best sintering temperature for BBN ceramics [15]. Consequently, using these optimal conditions, pure and Nd-doped BBN ceramics were prepared.

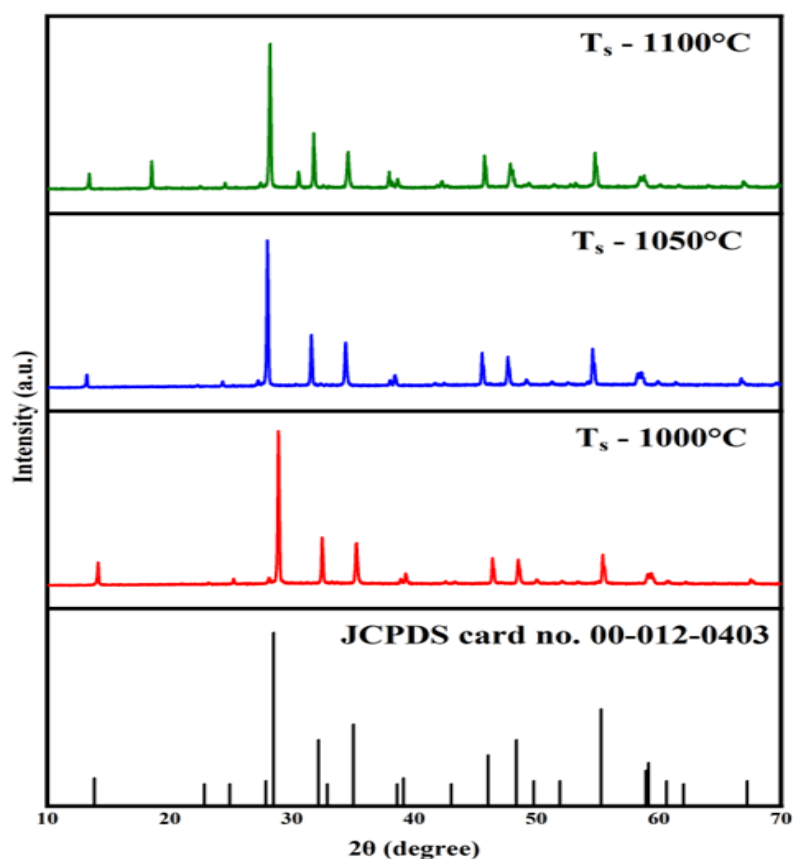


Fig. 3.2 XRD patterns of $\text{BaBi}_2\text{Nb}_2\text{O}_9$ ceramics sintered at 1000°C, 1050°C, and 1100°C, compared with the standard JCPDS card no. 00-012-0403, showing the effect of sintering temperature on phase purity.

3.1.3 Phase Analysis of Pure and Nd-Doped BBN Ceramics

All the prepared samples exhibit a single-phase Aurivillius structure with no detectable impurity phases, and it matches the JCPDS data of the orthorhombic structure. In the Nd-doped $\text{BaBi}_2\text{Nb}_2\text{O}_9$ system, the slight leftward shift of the XRD peaks indicates that Nd^{3+} ions influence the distortion caused by Bi^{3+} lone pairs, resulting in a small increase in lattice spacing and cell volume [3,9,10]. Changes in peak intensity further show that doping modifies the microstructure of the material. For all compositions, the strongest diffraction peak is observed at the (115) plane, confirming the typical Aurivillius phase associated with $\text{BaBi}_2\text{Nb}_2\text{O}_9$. Other major peaks include (002), (202), and (242). From the lattice parameter table, the b/a ratio of the BBNB4 sample comes out to be 1, which means the orthorhombic structure of the crystal is changing to a pseudo-tetragonal structure [5, 12].

Table 3.1. *lattice parameters of all compositions of BBN*

Sample	a (Å)	b (Å)	c (Å)	Volume (Å ³)	b/a
BBNB0	5.5548	5.5611	25.5789	790.15	1.0011
BBNB1	5.5634	5.5696	25.5079	790.38	1.0012
BBNB2	5.5652	5.5714	25.5134	791.06	1.0011
BBNB3	5.5654	5.5709	25.5024	790.68	1.0009
BBNB4	5.5648	5.5624	25.5013	789.35	1.0004

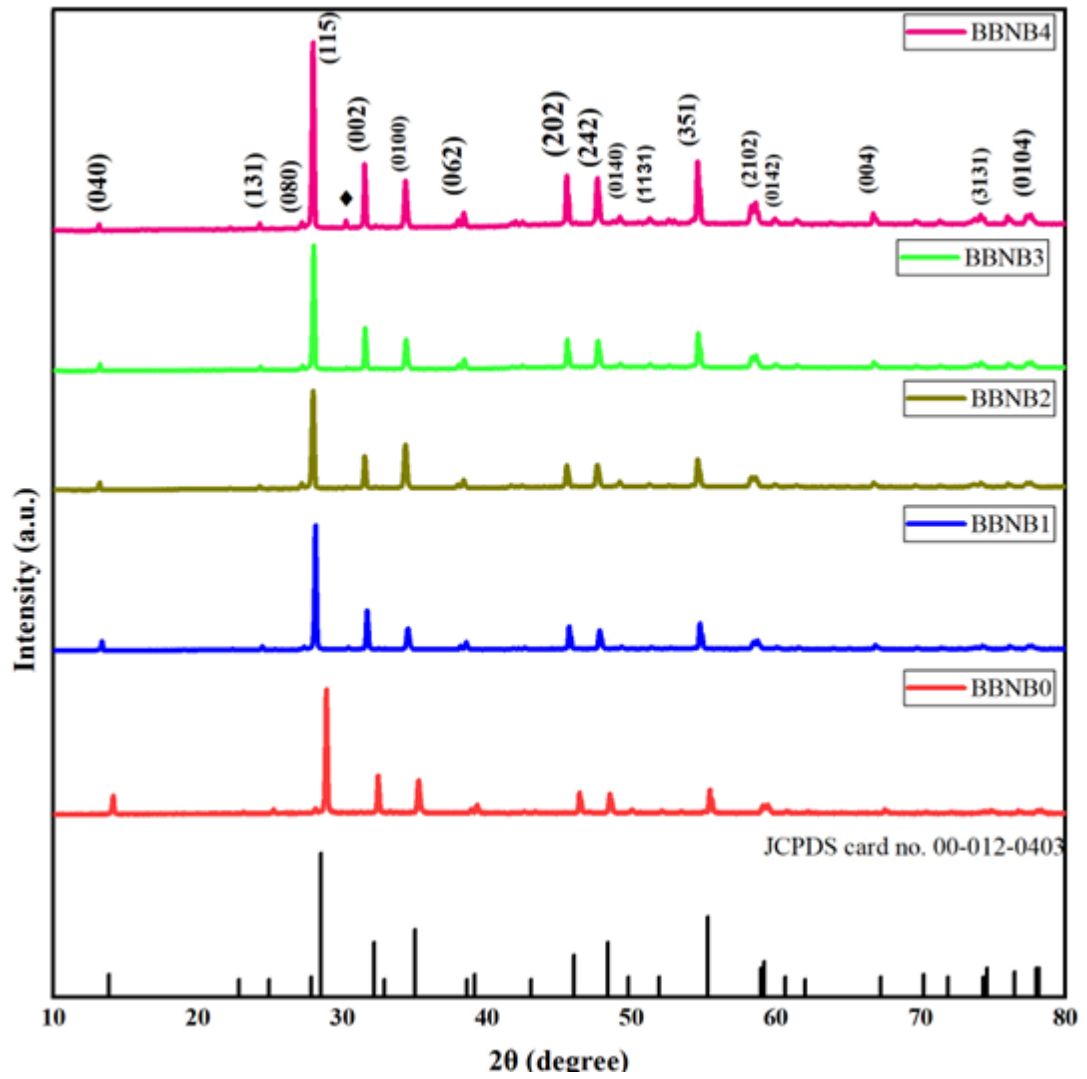


Fig. 3.3. XRD plot of all compositions of BBN

3.2 SEM Analysis

All the samples show tightly packed grains, which means the materials were well sintered and do not contain large pores. Nd doping leads to smaller grains, and the BBNB2 sample ($x = 0.06$) shows the most even and smooth grain structure. This good grain connection in the BBNB2 sample helps explain why its electrical properties are improved [18].

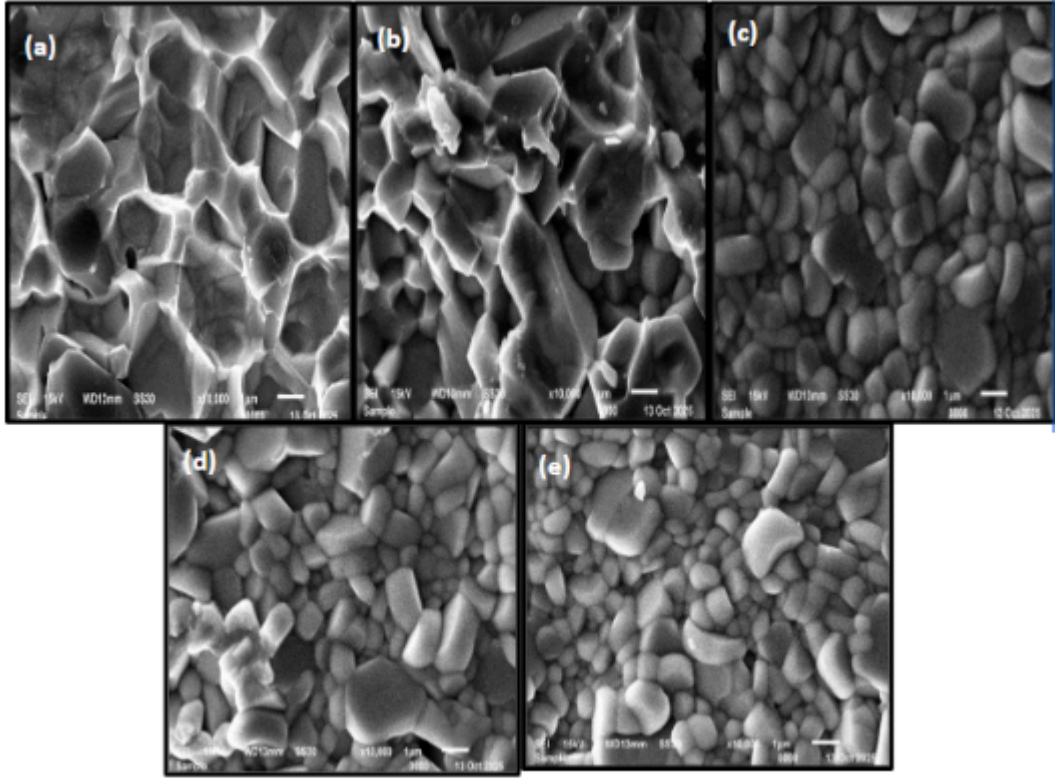


Fig. 3.4: SEM micrograph of the all composition of BBN

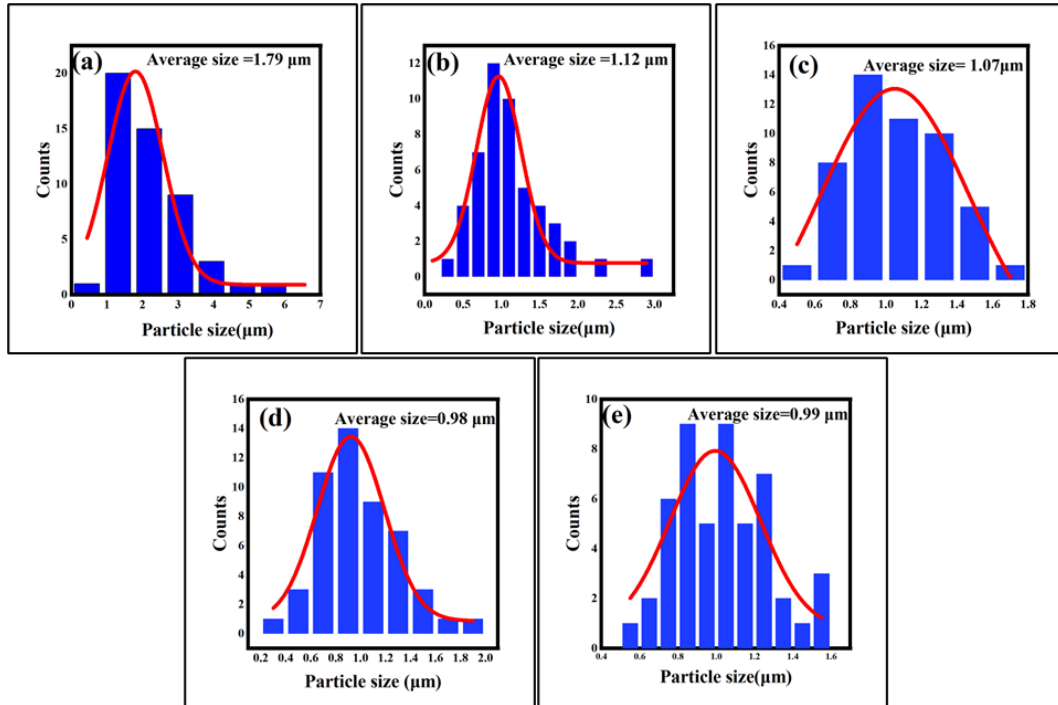


Fig. 3.5. Histograms of particle sizes obtained from SEM images of (a) BBNB0, (b) BBNB1, (c) BBNB2, (d) BBNB3, and (e) BBNB4 ceramics are shown. The solid curves represent Gaussians, which were fitted to get the average particle size.

3.3 Density and Porosity Analysis

- **Porosity slightly increases with Nd doping**, leading to reduced density and minor microstructural looseness consistent with the reduced grain size seen in SEM images [11].
- Despite slightly higher porosity, the **BBNB2 (x = 0.06)** sample maintains good density (~7.13 g/cc) and shows the **best electrical performance**, indicating that its optimised grain structure compensates for porosity.

Formulae used: [20]

$$\rho_{\text{experimental}} = m_{\text{balance}} / (m_{\text{air}} - m_{\text{water}}) \text{ g/cc} \quad (3.1)$$

$$\rho \text{ (\%)} = [(\rho_{\text{theoretical}} - \rho_{\text{experimental}}) / \rho_{\text{theoretical}}] * 100\% \quad (3.2)$$

Theoretical value of density ($\rho_{\text{theoretical}}$) = 7.52 g/cc



Fig 3.6: Porosity measuring apparatus

3.4 DC conductivity

This research paper focuses on investigating the electrical properties of BaBi₂Nb₂O₉ (BBN) ceramic material with Nd³⁺ ions concentration levels of x = 0, 0.04, 0.06, 0.08, and 0.10. The ceramic material samples were placed under a DC voltage of 20 volts for recording the electrical currents, from which resistivity, resistance, and conductivity were determined using the following formulas:

$$R = (\rho \times t) / A \quad (3.3)$$

$$\sigma = 1 / \rho \quad (3.4)$$

In the above equations, R denotes resistance, ρ is resistivity, t represents the thickness, A indicates the area, and σ shows conductivity. Table 3.2 displays the resistivity and conductivity values.

Table 3.2. Average grain size, density, porosity, resistivity, and conductivity of undoped and Nd-doped BBN ceramics

Composition	Average grain size (μm)	Density (ρ_{exp}) (g cm ⁻³)	Porosity (p, %)	Resistivity (Ω cm)	Conductivity (Ω cm) ⁻¹
BBNB0	1.79 $\pm$ 0.14	7.3297	2.53	7.80 $\times$ 10 ¹³	1.28 $\times$ 10 ⁻¹⁴
BBNB1	1.12 $\pm$ 0.03	7.2132	4.07	1.06 $\times$ 10 ¹⁴	0.947 $\times$ 10 ⁻¹⁴
BBNB2	1.07 $\pm$ 0.35	7.1327	5.15	3.50 $\times$ 10 ¹⁴	0.286 $\times$ 10 ⁻¹⁴
BBNB3	0.98 $\pm$ 0.03	7.1411	5.03	1.73 $\times$ 10 ¹⁴	0.579 $\times$ 10 ⁻¹⁴
BBNB4	0.99 $\pm$ 0.05	7.1886	4.41	1.70 $\times$ 10 ¹⁴	0.588 $\times$ 10 ⁻¹⁴

As seen from the analysis of the results, the DC conductivity of BaBi₂Nb₂O₉ ceramics doped with Nd³⁺ ions becomes lower with higher concentrations of dopants because of the increase in the resistivity values. It is associated with the changes detected in the microstructure of the samples based on the SEM images. Due to the incorporation of Nd³⁺ ions, the average grain sizes become lower; hence, more grain boundaries emerge inside the material. Grain boundaries are the sources of resistance that limit the movement of charge carriers, hence reducing DC conductivity [22]. Consequently, it was found that sample BBNB2 has the optimum grain boundary.

3.5 Analysis of Fourier transform infrared (FTIR)

The FTIR spectra recorded for the undoped BBNB0 and doped BBNB1 samples reveal distinct absorption bands appearing near 566 cm^{-1} , 618 cm^{-1} and 822 cm^{-1} . These absorption bands are mainly associated with the characteristic bending and stretching vibrational modes of Nb—O bonds present in the NbO_6 octahedral units of the crystal structure [4,7,21]. The observed vibrational features confirm the formation of the niobate framework and indicate that the octahedral arrangement remains intact in both compositions. Similar vibrational characteristics have also been reported for layered niobate and aurivillius type oxide ceramics [7]. The corresponding spectra are presented in Fig. 3.7.

After the incorporation of Nd^{3+} ions into the host lattice, a slight but noticeable shift in the bending vibrational band is observed. In the pure BBNB0 sample, the bending vibration appears around 618 cm^{-1} whereas in the Nd doped BBNB1 composition, the peak shifts towards a higher wavenumber near 624 cm^{-1} as illustrated in fig. 3.8 and fig. 3.9. Such a shift toward higher frequency generally indicates a modification in the local bonding environment surrounding the NbO_6 octahedral [9]. This behaviour suggests that the Nd^{3+} ions are successfully incorporated into the lattice and influence the bond characteristics within the structure. Similar peak shift behaviour due to rare earth ion substitution has also been observed in Nd doped layered ferroelectric systems [6,22].

The shift in vibrational frequency may be attributed to variations in the Nb—O bond strength caused by the substitution of Nd ions in the crystal lattice. The presence of rare earth ions can alter the local atomic arrangement and produce slight changes in bond length and bond energy which consequently affect the vibrational behaviour of the Nb—O bonds. The increase in wavenumber indicates a possible strengthening of the bond interaction or local lattice distortion induced by Nd incorporation. Such modifications in the local structural symmetry are commonly associated with ionic radius mismatch and lattice strain generated during substitutional doping .

Furthermore, the full width half maximum values of the major absorption bands remain nearly unchanged for both BBNB0 and BBNB1 compositions as listed in Table 3.3. The absence of significant peak broadening indicates that Nd doping does not introduce considerable lattice disorder or the structural instability into the material. This observation suggests that the overall structural integrity of the NbO_6 octahedral

framework is well preserved even after rare earth ion incorporation. The retention of comparatively sharp absorption bands also reflects good crystallinity and structural ordering within the ceramic matrix.

The FTIR results therefore confirm that Nd doping modifies the local bonding environment without causing major disruption to the crystal structure. The retention of characteristic absorption bands together with minimal variation in FWHM demonstrates that the structural framework of the material remains stable after Nd incorporation. These findings are in good agreement with the XRD analysis which also confirms phase stability and preservation of the layered aurivillius structure in the Nd doped compositions.

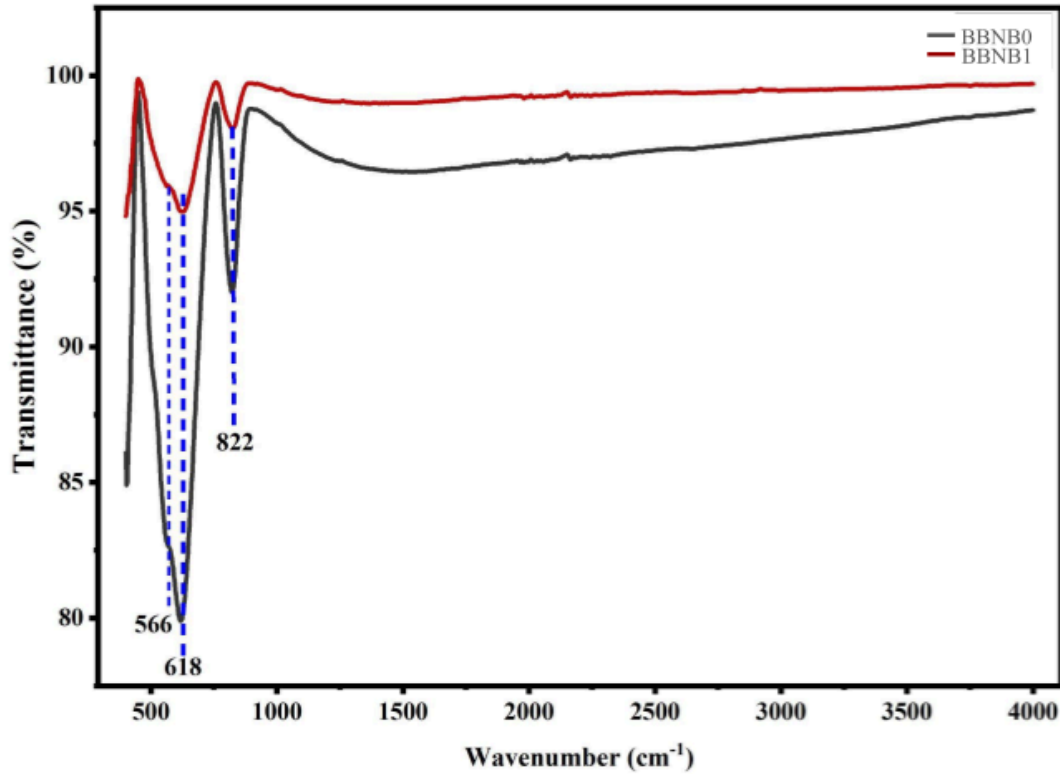


Fig. 3.7 shows Fourier transform infrared (FTIR) data obtained at room temperature for BBNB0 and BBNB1 with prominent absorption peaks marked on 566 cm⁻¹, 618 cm⁻¹ and 822 cm⁻¹.

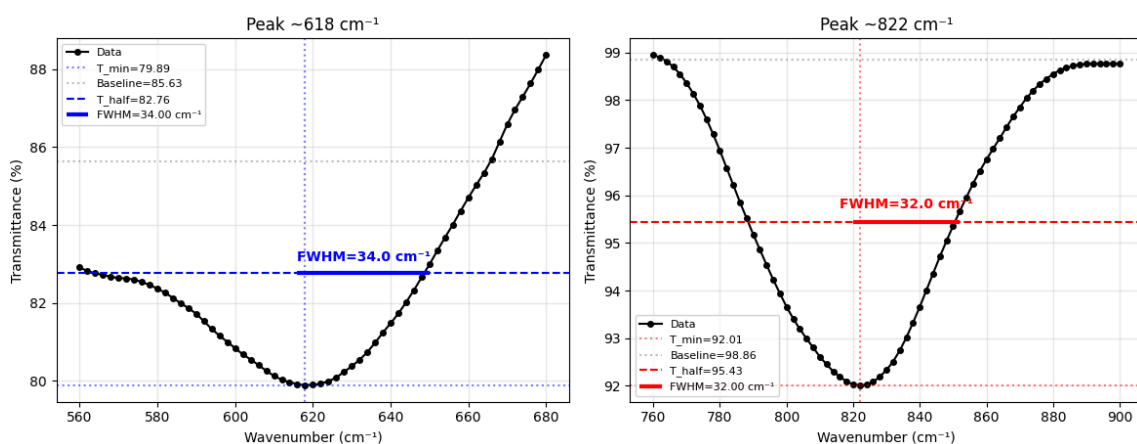


Fig. 3.8 FWHM analysis of FTIR absorption bands of BBNB0 at 618 cm⁻¹ and 822 cm⁻¹ using Direct method.

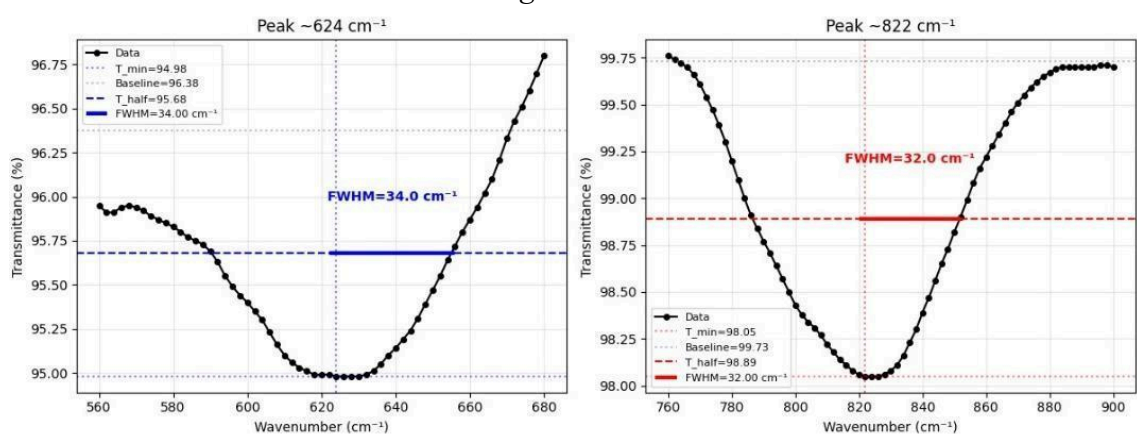


Fig. 3.9 FWHM analysis of FTIR absorption bands of BBNB1 at 624 cm⁻¹ and 822 cm⁻¹ using Direct method.

Table 3.3. Vibrational modes, corresponding wavenumbers, and FWHM values of FTIR absorption bands for BBNB0 and BBNB1.

<u>Sample</u>	<u>Vibrational Mode</u>	<u>Wavenumber (cm⁻¹)</u>	<u>FWHM (cm⁻¹)</u>
BBNB0	Nb–O bending	618.00	34.00
BBNB0	Nb–O stretching	822.00	32.00
BBNB1	Nb–O bending	624.00	34.00
BBNB1	Nb–O stretching	822.00	32.00

3.6 Raman Spectroscopy

Raman spectroscopy was employed to investigate the local structural modifications induced by Nd^{3+} substitution in $\text{BaBi}_2\text{Nb}_2\text{O}_9$ ceramics. Raman analysis is highly sensitive to short-range structural ordering and local lattice distortion, making it an effective technique for studying Aurivillius layered compounds. The room-temperature Raman spectra of all compositions (BBNB0–BBNB4), recorded in the range of $100\text{--}1200\text{ cm}^{-1}$ using a 660 nm excitation laser, are shown in Fig. 3.10.

All compositions possess almost identical characteristic Raman bands, implying that the introduction of Nd does not modify the long-range Aurivillius-layered crystal structure. This is in agreement with the X-ray diffraction findings and earlier work on BBN-based materials [26].

The Raman modes below $\sim 250\text{ cm}^{-1}$ are mainly associated with Bi–O vibrations and translational lattice modes involving A-site cations [22, 23]. The intermediate bands between $300\text{--}600\text{ cm}^{-1}$ correspond to bending and deformation vibrations of NbO_6 octahedra [23, 24, 26]. An intense band existing around 865 cm^{-1} is related to the stretching vibration of Nb–O bond with high sensitivity to octahedral distortion [23, 25, 28].

A weak band around $\sim 198\text{ cm}^{-1}$ shows significant enhancement after Nd doping, implying that there are more localized distortions because of Bi site substitution [29]. Systematic composition-dependent changes in Raman peak positions and peak broadening are also observed with increasing Nd concentration.

From the figure (Fig. 3.11), it is clear that the symmetric stretching vibration of Nb–O (v9) undergoes a red shift from 865.92 cm^{-1} to 862.17 cm^{-1} as the amount of substitution changes from BBNB0 to BBNB4. The Raman mode centered at $\sim 304\text{ cm}^{-1}$ (v5) shows a slight blue shift, while a small red shift can be seen in the Raman peak centered at $\sim 567\text{ cm}^{-1}$ (v8). These inconsistent mode-specific shifts imply that there is distortion of the NbO_6 octahedra without lattice expansion [24, 27].

In addition, some Raman modes exhibit increased FWHM values due to the addition of Nd, which implies a higher degree of strain and disorder in the lattice structure.

Further analysis of the Nb-O stretching mode was performed by the application of Herschbach's equation:

$$\nu = A e^{BR} \quad (3.4)$$

where ν is the Raman frequency, R is the bond length, and A and B are empirical constants [9, 24].

The calculated Nb–O bond length increases gradually from 1.773 Å for BBNB0 to 1.776 Å for BBNB4, confirming progressive elongation of Nb–O bonds with increasing Nd concentration. The local octahedral distortion and increased structural disorder disrupt long-range dipolar ordering and promote relaxor ferroelectric behaviour in Nd-modified BBN ceramics.

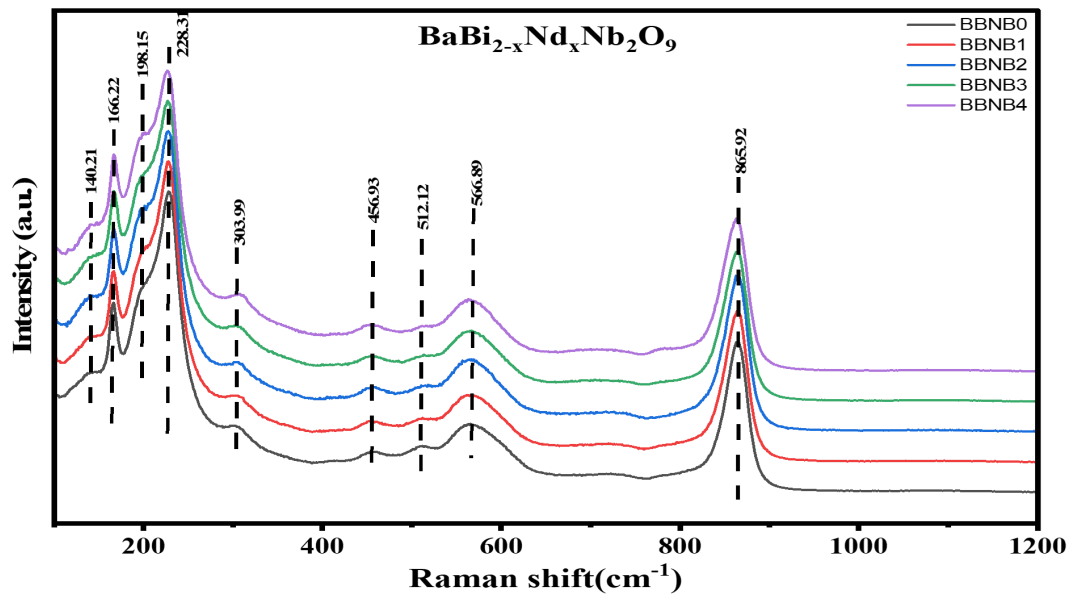


Fig. 3.10: Stacked Raman spectra of BBNB0–BBNB4 samples recorded at room temperature using a 660 nm excitation laser.

Table 3.4. Nb–O bond length estimated from the Raman stretching mode using Herschbach’s empirical relation.

Sample	Raman peak ν (cm^{-1})	Nb–O bond length R ($\text{\AA}$)
BBNB0	865.9	1.7733
BBNB1	864.2	1.7744
BBNB2	864.1	1.7744
BBNB3	862.8	1.7752
BBNB4	862.2	1.7756

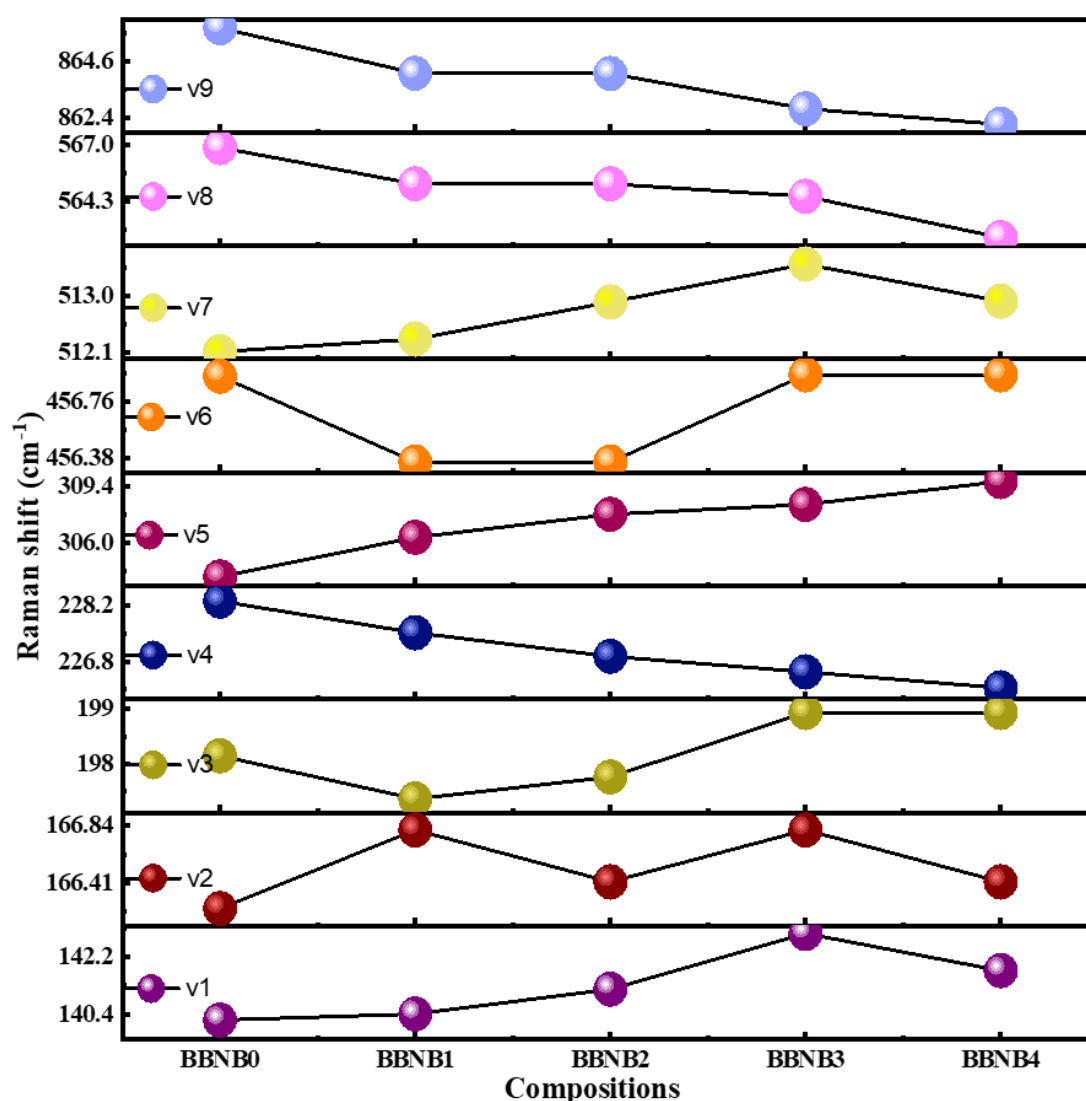


Fig. 3.11: Evolution of Raman peak positions ($\nu 1$ – $\nu 9$) as a function of composition, illustrating composition-dependent peak shifts.

Table 3.5. Raman mode assignments of the BBNB0 sample showing peak position, vibrational origin, and corresponding bonding units.

Raman shift (cm ⁻¹)	Band assignment	Mode assignment	Structural origin	Reference
140.21	v1	Lattice vibrational mode	A-site (Ba/Bi)-O vibrations	[23, 24, 26]
166.22	v2	Bi-O related vibration	BiO ₆ polyhedral dynamics	[23, 24, 26]
198.15	v3	Disorder-activated mode	A-site vibration/symmetry breaking	[23, 24, 26]
228.31	v4	Bi-O / octahedral tilting mode	Coupled A-site–octahedral vibration	[23, 24, 26]
303.99	v5	NbO ₆ bending mode	Nb-O-Nb bending vibration	[24, 25]
456.93	v6	NbO ₆ deformation mode	Octahedral distortion vibration	[24, 25]
512.12	v7	NbO ₆ asymmetric bending	NbO ₆ octahedral vibration	[24, 25]
566.89	v8	NbO ₆ stretching-related mode	Nb-O vibration	[24, 25]
865.92	v9	Nb-O symmetric stretching mode	NbO ₆ octahedral stretching	[25]

3.7 Diffuse Reflectance Spectroscopy and Band Gap Analysis

The optical properties of Nd³⁺ doped barium bismuth niobate ceramics, BaBi_{2-x}Nd_xNb₂O₉ (x= 0.00, 0.04, 0.06, 0.08, and 0.10), were investigated using UV-visible diffuse reflectance spectroscopy (DRS) in order to understand the influence of Nd incorporation on the electronic structure of the material. The diffuse reflectance spectra for all synthesized compositions are presented in Fig. 3.12 . The spectra exhibit a distinct absorption edge within the visible region which is a typical characteristic of semiconducting oxide ceramics [30]. The presence of a sharp absorption edge indicates

a good optical response and confirms the semiconducting nature of the prepared samples.

A gradual change in the position of the absorption edge is observed with increasing Nd^{3+} concentration. These variations suggest that the incorporation of Nd ions produces modifications in the electronic band structure of the $\text{BaBi}_2\text{Nb}_2\text{O}_9$ host lattice [23, 31]. The shift in optical absorption behaviour may arise due to changes in lattice parameters, local structural distortion, and alteration in the interaction between metal and oxygen orbitals after rare earth ion substitution [30].

Rare earth doping is known to introduce localised electronic states in oxide ceramics without significantly disturbing the fundamental crystal framework of the material [29]. In the present system, Nd^{3+} ions are incorporated into the layered oxide structure while preserving the structural stability of the host material. The optical absorption process is mainly governed by electronic transitions between the valence and conduction bands of the host lattice. In addition, weak absorption features associated with intra-configuration 4f-4f electronic transitions of Nd^{3+} ions may also contribute to the spectra. However, these transitions generally appear weak because the 4f electrons are effectively shielded by the outer 5s and 5p orbits minimising their interaction with the surrounding crystal field [32-34].

To estimate the optical band gap energy of the prepared ceramics, the diffuse reflectance data were analysed using the Kubelka-Munk theory, which is commonly employed for optically thick polycrystalline samples [35]. The Kubelka-Munk function as:

$$F(R) = \frac{(1-R)^2}{2R} \frac{S}{\alpha} \quad (3.5)$$

Where R represents the diffuse reflectance and F(R) corresponds to the absorption function. In this relation the scattering coefficient is assumed to remain nearly constant over the measured wavelength range [35]. This method enables reliable conversion of reflectance data into absorption related information suitable for band gap analysis.

The optical band energy (E_g) was determined using the Tauc relation [36]:

$$[F(R)hv] = C(hv - E_g)^n \quad (3.6)$$

Where $h\nu$ denotes the incident photon energy, C is a proportionality constant, and n depends on the nature of the electronic transition involved. For the present layered oxide ceramic system, an incident allowed transition was assumed, and therefore the value of $n = 1/2$ was considered during the analysis [36]. The photon energy was calculated using the relation:

$$h\nu = \frac{1240}{\lambda} \text{ (eV)} \quad (3.7)$$

Where $h\nu$ is expressed in electron volts (eV) and λ represents the wavelength in nanometers.

The Tauc plots obtained from the variation of $[F(R) h\nu]^{1/2}$ with photon energy for different compositions are shown in Fig. 3.12. The linear portion of each curve was extrapolated towards the energy axis, and the point of intersection was taken as the optical band gap value of the corresponding composition. The calculated band gap energies for all samples are summarized in the table.

The variation of optical band gap with Nd^{3+} concentration does not follow a linear trend. An initial increase in band gap energy is observed for lower Nd doping concentrations, which may be attributed to local lattice distortion and internal strain produced by the substitution of Nd^{3+} ions at Bi^{3+} lattice sites. Such structural modifications can alter the Nb—O—Nb bond angles and reduce orbital overlap between neighboring atoms, thereby affecting the electronic band structure of the material [31, 37, 38].

At higher Nd concentrations, partial relaxation of lattice strain may occur through the generation of oxygen vacancies and defect states within the crystal lattice. These defects introduce localized energy levels near the conduction or valence band edges leading to band tailing effects and a reduction in the effective optical band gap energy. Similar behaviour has been reported in several rare earth doped layered perovskite oxide systems where defect induced states strongly influence optical absorption characteristics [35].

Overall the DRS analysis clearly demonstrates that Nd^{3+} incorporation significantly influences the optical behaviour of $\text{BaBi}_2\text{Nb}_2\text{O}_9$ ceramics. The observed changes in absorption edge position and band energy are mainly associated with lattice distortion, defect generation, and modification of the electronic structure induced by rare earth

doping. These results confirm that Nd substitution can effectively tune the optical properties of BBN ceramics without causing major structural instability [31, 37, 38].

Table 3.6. Optical band gap (E_g) measurements for BBNN0–BBNN4 samples were determined from UV–Vis diffuse reflectance spectra by applying the Tauc method.

Sample code	Optical band gap E_g (eV)
BBNB0	2.6526
BBNB1	2.8424
BBNB2	2.7348
BBNB3	2.7069
BBNB4	2.6359

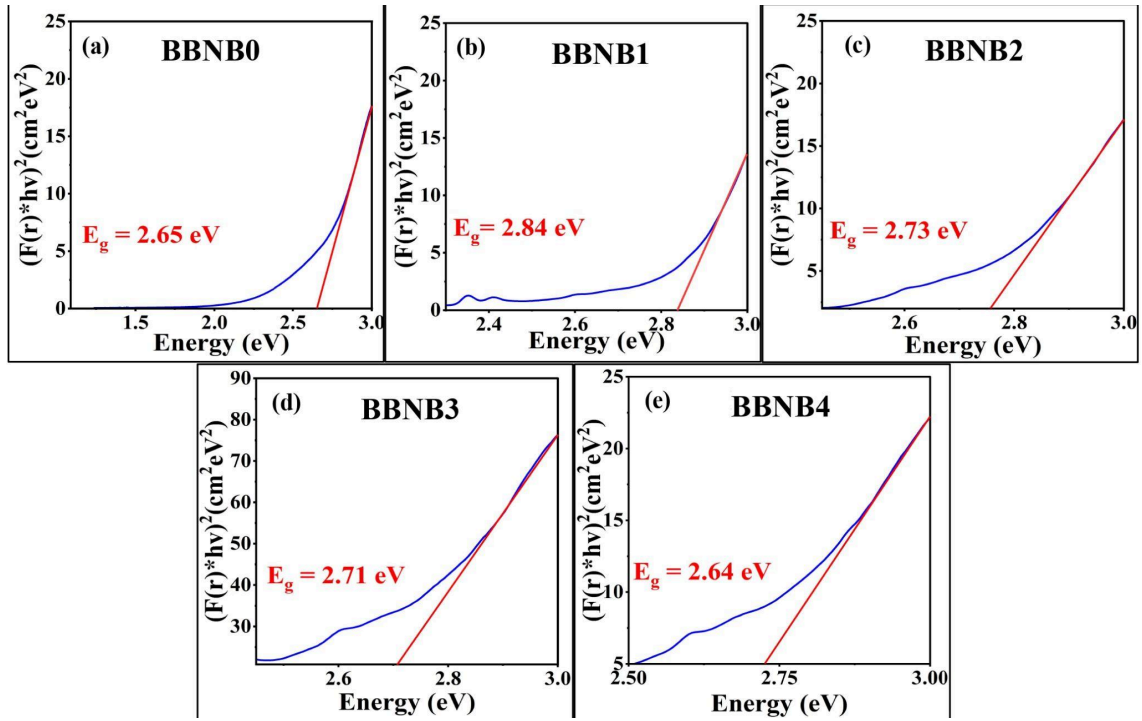


Fig. 3.12. a-e Tauc plots of doped and undoped samples of BBN

3.8 Ferroelectric Properties (P-E Analysis)

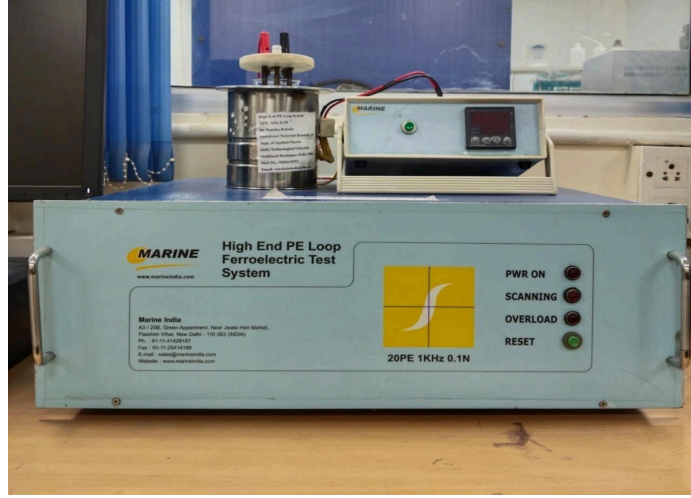


Fig. 3.13. P-E loop measurement instrument

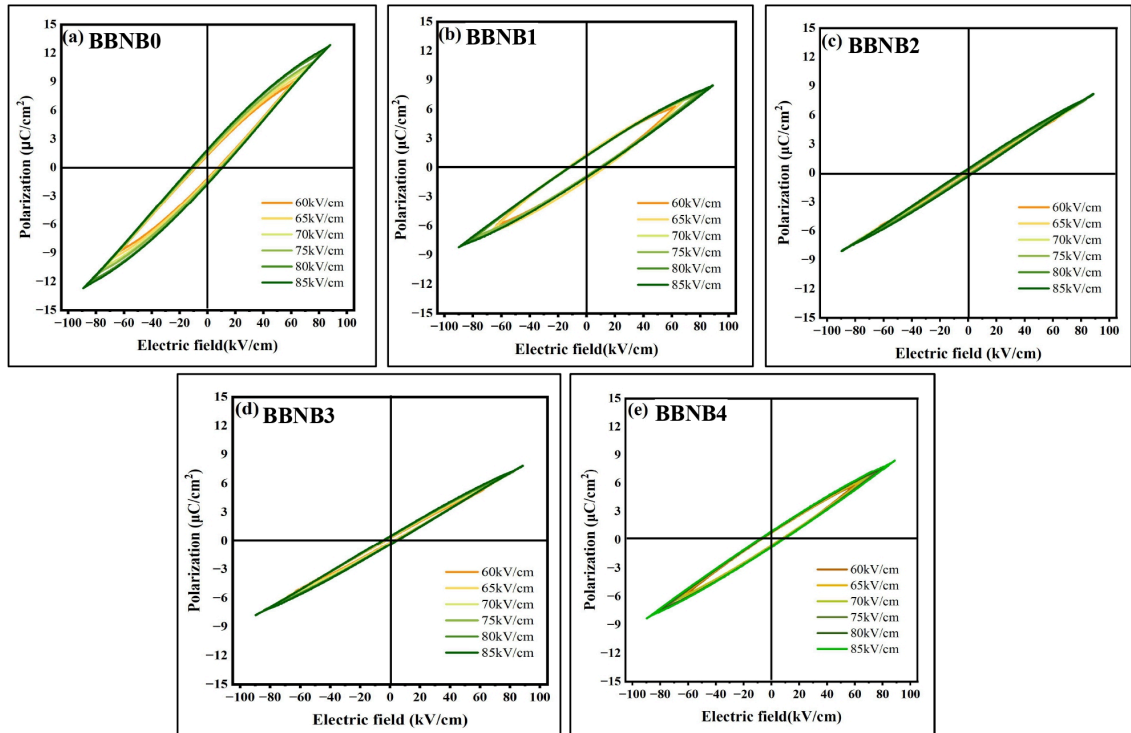


Fig. 3.14. PE loop of BBN for all compositions

All the samples display slim P-E loops, which is a typical sign of relaxor-type ferroelectric behaviour with low hysteresis loss. The polarisation increases steadily with the applied electric field, showing that all compositions have a good dielectric response. Among them, the BBNB2 sample ($x = 0.06$) shows a slightly wider loop, indicating

better ferroelectric activity compared to the other doped samples. Nd doping also affects the domain-switching process and helps reduce leakage, which contributes to the improved functional performance of the material.

The temperature dependent PE loops of BBNB2 measured at 80 kV/cm exhibit slim hysteresis behaviour with only minor variations in the loop shape over the temperature range of 30-140 degree celsius, as shown in fig.3.16 (a) and (b), indicating excellent thermal stability and relaxor ferroelectric characteristics.

Polarization electric field hysteresis loops were further studied to evaluate the energy storage performance of $\text{BaBi}_{2-x}\text{Nb}_2\text{Nd}_x\text{O}_9$ ceramics. The total energy density (W), recoverable energy density (W_{rec}), and energy storage efficiency (η) were calculated from the P—E loops using the following relations:

$$W = \int_0^{P_m} E dP \quad (3.8)$$

$$W_{\text{rec}} = \int_{P_r}^{P_m} E dP \quad (3.9)$$

$$\eta = \frac{W_{\text{rec}}}{W} \times 100\% \quad (3.10)$$

Where P_m denotes the maximum polarization, P_r represents the remnant polarization, and E is the applied electric field. The area enclosed by the P—E loop corresponds to the energy loss during one electric field cycle, while the area under the discharge curve between P_r and P_m represents the recoverable energy density [41-44]. The low remnant polarization and narrow hysteresis area contribute to enhanced energy storage efficiency and reduced energy loss. Furthermore, the nearly stable values of recoverable energy density (W_{rec}) and efficiency (η) with increasing temperature confirm the suitability of ceramic for high temperature energy storage applications [9, 39-41].

The fatigue behaviour of the samples were examined up to 10,000 electric field cycles. The nearly invariant values of remnant polarization (P_r), maximum polarization (P_m), coercive field (E_c) and leakage current shown in fig.3.16 (c) and (d) indicate excellent fatigue endurance and stable ferroelectric switching characteristics. The absence of

significant degradation confirms low defect accumulation and reduced domain wall pinning during repeated polarization reversal, which demonstrates good electrical reliability of BBNB2 sample [13, 43].

Table 3.7. *PE parameters of all compositions of BBN*

Electric field (kV/cm)	Parameter	BBNB0	BBNB1	BBNB2	BBNB3	BBNB4
60	Pr ($\mu\text{C}/\text{cm}^2$)	1.2843	1.23239	0.21958	0.30193	0.73105
	Pm ($\mu\text{C}/\text{cm}^2$)	8.9383	6.29202	5.61874	5.34849	6.04715
	W (J/cm^3)	0.30808	0.23008	0.17766	0.17209	0.21181
	Wrec (J/cm^3)	0.21472	0.14414	0.16594	0.15145	0.15689
	η (%)	69.7	62.64	93.4	88.01	74.07
65	Pr ($\mu\text{C}/\text{cm}^2$)	1.39823	1.39172	0.2325	0.35585	0.72396
	Pm ($\mu\text{C}/\text{cm}^2$)	9.73321	6.87407	6.13541	5.08969	6.5156
	W (J/cm^3)	0.35997	0.27285	0.20965	0.2035	0.24612
	Wrec (J/cm^3)	0.25148	0.16751	0.19395	0.18244	0.18481
	η (%)	69.86	61.39	92.51	89.65	75.1
70	Pr ($\mu\text{C}/\text{cm}^2$)	1.56329	1.23564	0.28094	0.39898	0.79493
	Pm ($\mu\text{C}/\text{cm}^2$)	10.5574	7.54067	6.65207	6.41244	6.99468
	W (J/cm^3)	0.41662	0.33048	0.24468	0.23894	0.27932
	Wrec (J/cm^3)	0.29344	0.22785	0.22617	0.21226	0.21492
	η (%)	70.43	68.94	92.43	88.98	76.94
75	Pr ($\mu\text{C}/\text{cm}^2$)	1.63576	1.16411	0.29708	0.39539	0.86946
	Pm ($\mu\text{C}/\text{cm}^2$)	11.27434	7.5927	7.12999	6.8893	7.48442

	W (J/cm ³)	0.48579	0.33465	0.28232	0.2798	0.32282
	Wrec (J/cm ³)	0.33589	0.2318	0.25835	0.24341	0.24511
	η (%)	70.15	69.27	91.51	86.99	75.93
80	Pr ($\mu\text{C}/\text{cm}^2$)	1.84282	1.17061	0.34875	0.43852	0.83752
	Pm ($\mu\text{C}/\text{cm}^2$)	12.16469	8.02192	7.63374	7.32542	7.90318
	W (J/cm ³)	0.54288	0.37647	0.32107	0.31455	0.35898
	Wrec (J/cm ³)	0.38115	0.26112	0.29395	0.27478	0.28246
	η (%)	70.2	69.36	91.55	87.36	78.68
85	Pr ($\mu\text{C}/\text{cm}^2$)	1.84282	1.23564	0.44562	0.49603	0.90849
	Pm ($\mu\text{C}/\text{cm}^2$)	12.85574	8.4674	8.18915	7.83223	8.47099
	W (J/cm ³)	0.60576	0.41892	0.37112	0.36059	0.41333
	Wrec (J/cm ³)	0.42964	0.29536	0.32914	0.30957	0.31732
	η (%)	70.92	70.5	88.69	85.85	76.77

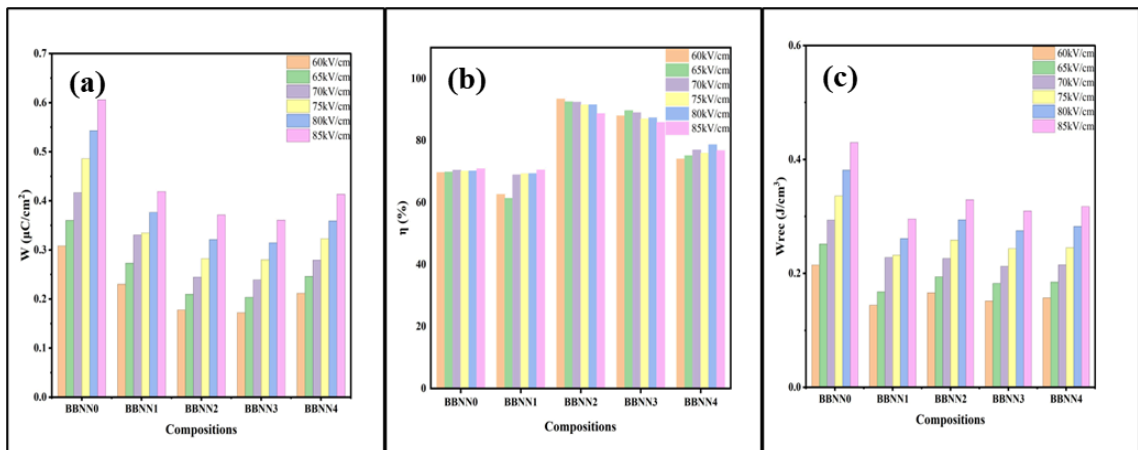


Fig. 3.15. a-e Comparison bar graphs of total energy (W), efficiency (η), and energy recovered (w_{rec}) of doped and undoped samples of BBN

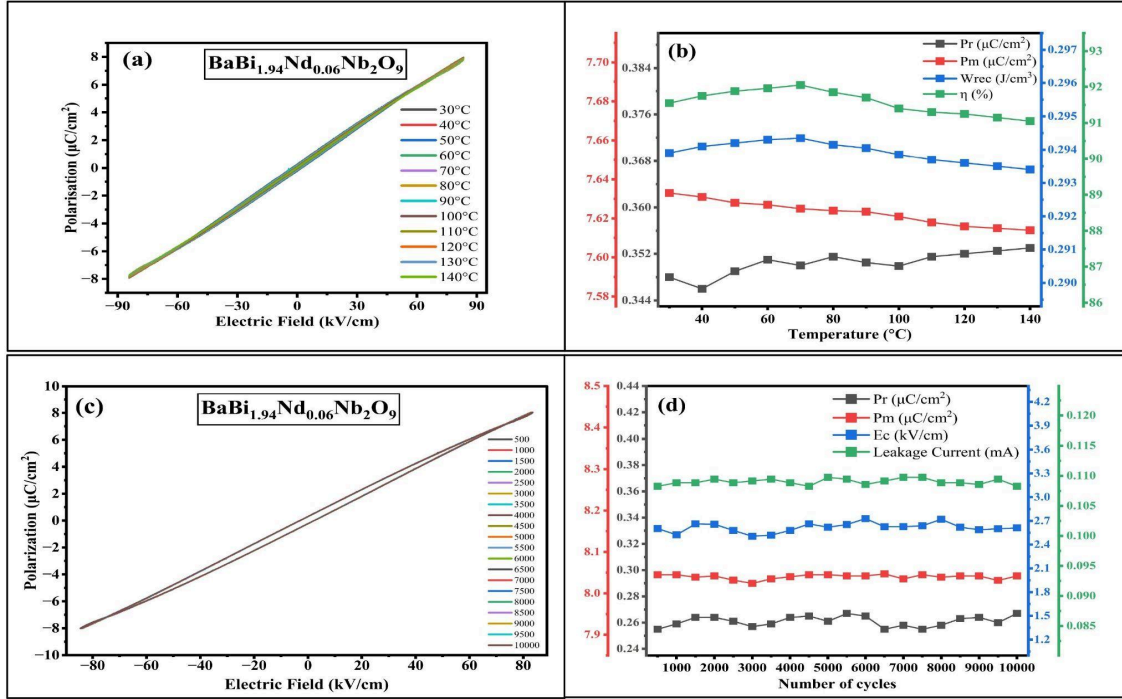


Fig. 3.16. (a) Temperature-dependent polarization-electric field (P - E) hysteresis loops of $\text{BaBi}_{1.94}\text{Nd}_{0.06}\text{Nb}_2\text{O}_9$ ceramic recorded at an electric field of 80 kV/cm across temperature range from 30°C to 140°C. **(b)** Temperature dependence of the remnant polarization (P_r), maximum polarization (P_m), recoverable energy (W_{rec}) and energy efficiency (η). **(c)** Fatigue behavior of the P - E loops measured from 500 to 10,000 switching cycles at 80 kV/cm. **(d)** Dependence of remnant polarization (P_r), maximum polarization (P_m), coercive field (E_c) and leakage current (I_{leak}) on the number of cycles.

3.9 Dielectric Studies

The dielectric constant and the dielectric loss for different BBN compositions are shown in Fig. 3.18 and Fig. 3.19. These figures show the results for a range of frequencies from 1 kHz to 1 MHz. The BBN compositions have a dielectric maximum instead of a sharp peak. This means that the BBN compositions have a diffuse phase transition. This is typical of ferroelectrics [47, 48].

To understand the degree of diffuseness the dielectric data were analyzed using a law. This law is called the modified Curie-Weiss law [1, 49]. The law is expressed as:

$$\frac{1}{\epsilon'} - \frac{1}{\epsilon'_m} = \frac{(T - T_m)^\gamma}{C} \quad (3.11)$$

In this law ϵ'_m is the peak constant at the temperature T_m . C is the Curie constant. γ is the diffuseness parameter. For ferroelectrics, γ is close to 1. For relaxor behavior, γ values are close to 2. If γ is between 1 and 2, it means that the material has relaxor characteristics [4].

Fig. 3.20 shows a correlation between the graph of $\ln(1/\epsilon' - 1/\epsilon'_m)$ and $\ln(T - T_m)$ at a frequency of 500 kHz for all the BBN compositions. The slope γ values measured are 1.7038 for BBNB0, 1.5233 for BBNB1, 1.7511 for BBNB2, 1.5310 for BBNB3, and 1.5831 for BBNB4. All these values are greater than one. This means that the BBN compositions have a diffuse phase transition and relaxor traits [9].

The high γ values for BBNB0 and BBNB2 mean that they have relaxor characteristics. The lower γ value for BBNB3 means that it has diffuseness. This could be because BBNB3 has an uniform structure. The dielectric loss shows maxima over temperature and frequency. This is typical of polarization. The lack of loss anomalies means that long-range ferroelectric ordering is minimal.

As the concentration of Nd increases, the dielectric loss decreases. The BBNB4 sample has the overall loss. The relaxor behavior of the BBN compositions is mainly due to the disorder caused by Nd substitution. This substitution disrupts range dipolar order and creates polar nano-regions [50].

Although BBNB0 and BBNB2 have γ values, their energy-storage efficiency is not the same. The γ parameter only describes the degree of diffuse transition under low electric fields. The energy storage behavior is dependent on polarization reversibility and hysteresis loss under electric fields. In the Nd modified compositions, local structural disorder and dynamic polar nano-regions suppress domain wall motion and reduce remnant polarization. This results in energy dissipation [51].

The increase in constant for Nd substituted compositions is due to the distinct polarization mechanisms governing low field dielectric response and high field ferroelectric behavior. Nd substitution induces structural disorder and enhances polar nano region dynamics. This increases polarizability under low electric fields. However, the same local disorder disrupts range ferroelectric domain ordering and suppresses complete dipole alignment under high electric fields. This results in reduced

polarization and lower energy dissipation. Such behavior is characteristic of relaxor systems and is advantageous for dielectric energy storage applications [52].

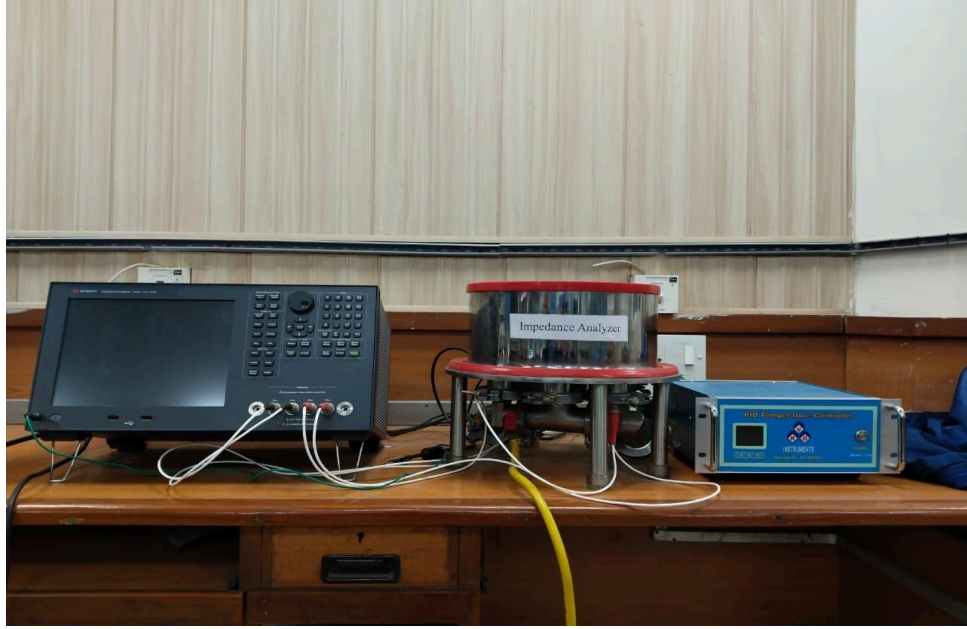


Fig 3.17. DIELECTRIC INSTRUMENT

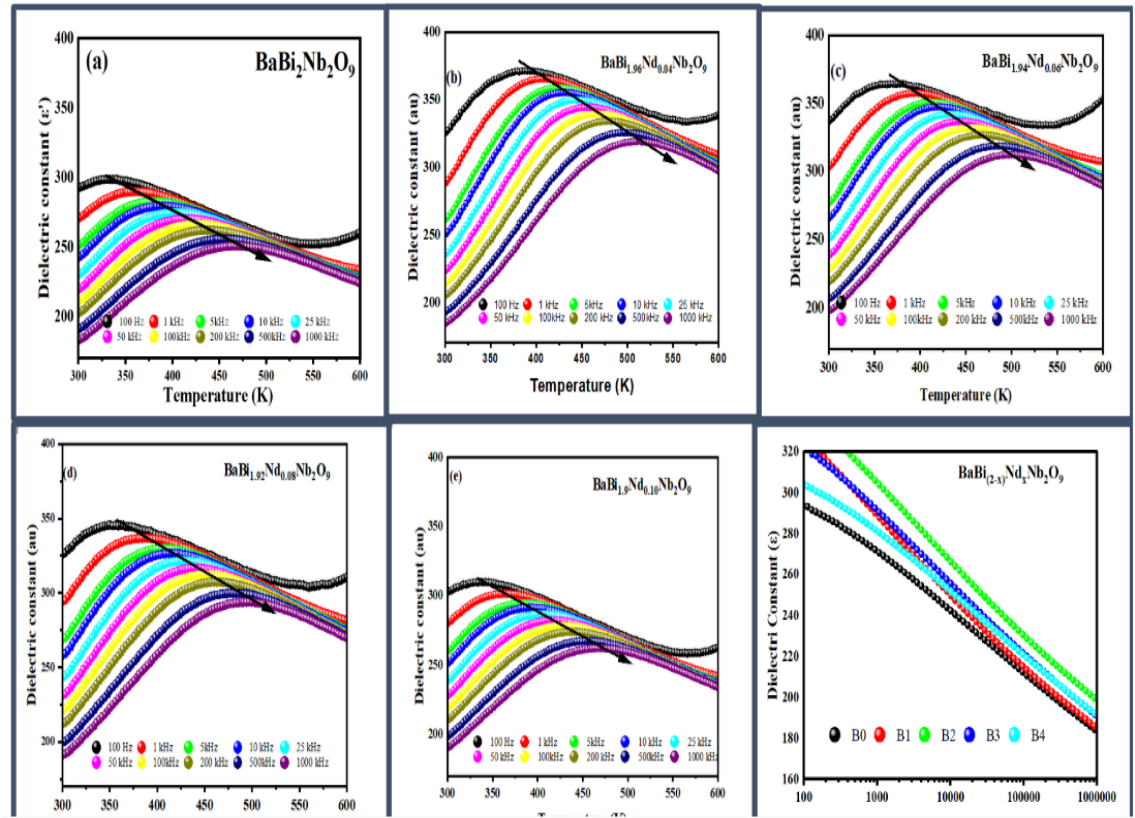


Fig. 3.18. (a, b, c, d, e) Dielectric constant vs temp graph and dielectric constant vs. frequency (room temp) of $\text{BaBi}_{2-x}\text{Nd}_x\text{Nb}_2\text{O}_9$ ($x=0, 0.04, 0.06, 0.08, \text{ and } 0.10$.)

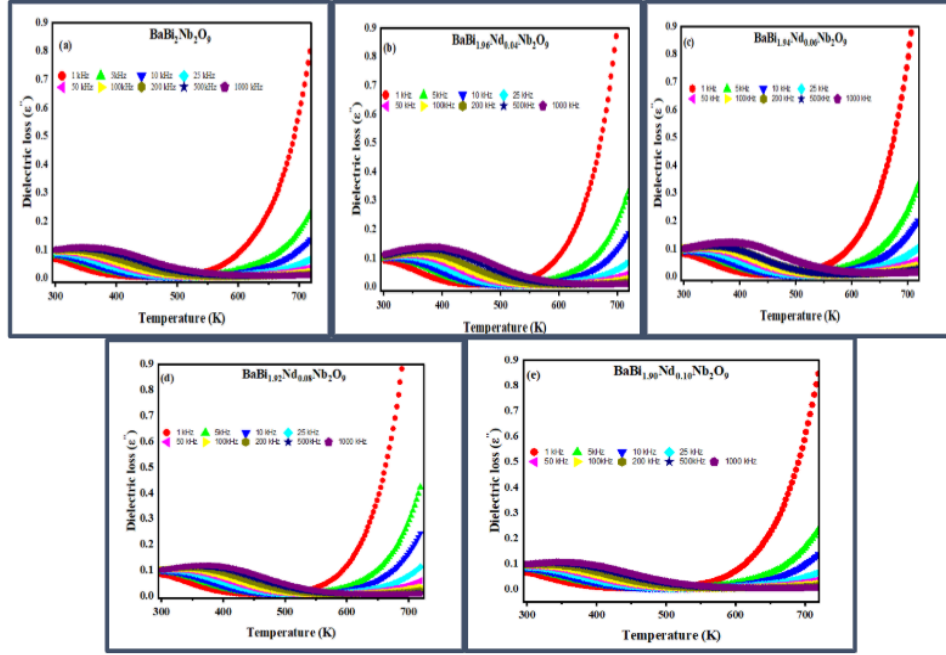


Fig. 3.19. Dielectric loss vs temperature of all composition of BBN

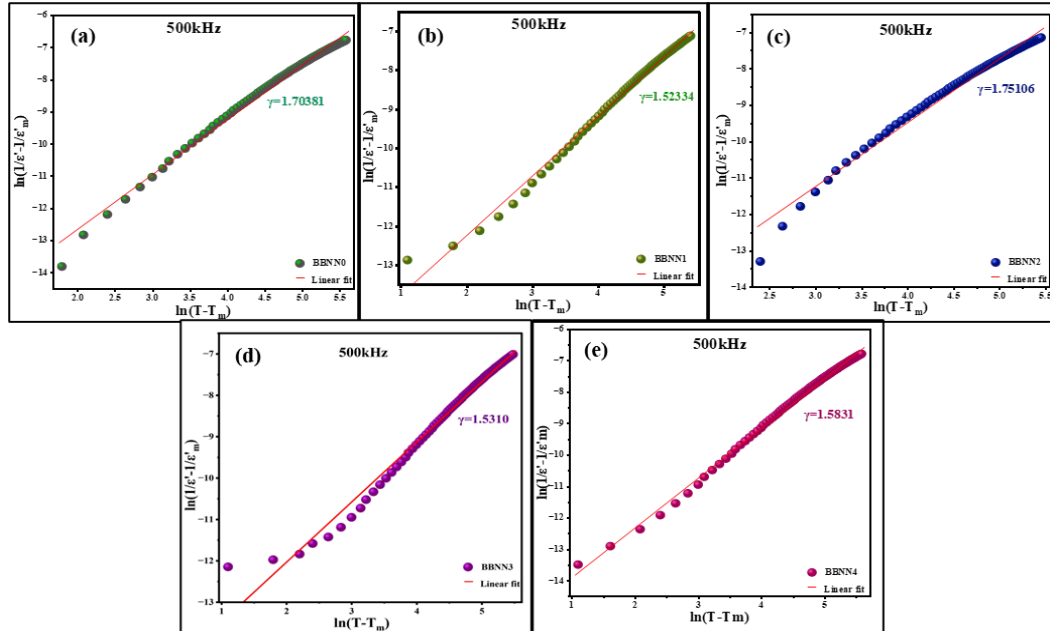


Fig. 3.20. Modified Curie–Weiss analysis at 500 kHz for (a) BBNB0, (b) BBNB1, (c) BBNB2, (d) BBNB3, and (e) BBNB4 ceramics. The plots of $\ln(1/\epsilon' - 1/\epsilon'_{\infty})$ versus $\ln(T - T_m)$, along with linear fitting, are used to determine the diffuseness parameter (γ).

CHAPTER 4

CONCLUSION

In the current study, Nd³⁺ doped BaBi₂Nb₂O₉ (BBN) Aurivillius ceramics with different compositions of BaBi_{2-x}Nd_xNb₂O₉ (x = 0.00, 0.04, 0.06, 0.08, and 0.10) have been successfully synthesized by employing the solid-state reaction method. The impact of Nd doping on the structural, microstructural, dielectric, ferroelectric and optical characteristics of BBN ceramics was systematically investigated. As per the outcomes, the incorporation of Nd leads to the effective manipulation of the electrical and structural properties of the material without altering the layered Aurivillius structure.

The XRD patterns revealed the existence of a single-phase orthorhombic Aurivillius structure in all the compositions without any formation of any other impurity phases under optimized synthesis conditions. The peak positions were found to be in accordance with the standard JCPDS card, confirming the single-phase nature of the ceramics. The minor shifting in the peak positions along with lattice parameters suggests the successful incorporation of Nd³⁺ ions into the Bi³⁺ site positions. The ratio of lattice parameters (b/a) is observed to approach 1 as the Nd content increases.

The SEM analyses indicated that there was an increase in the number of grains but with a finer grain size compared to that in the undoped one. Among all compositions tested, the BBNB2 composition (x = 0.06) had a denser microstructure and better grain connectivity, which led to higher electrical properties. The results obtained from density and porosity studies also corroborated this trend, whereby BBNB2 had a higher density of about 7.13 g/cc, although the porosity slightly increased due to the addition of Nd in the samples.

Both FTIR and Raman spectroscopic studies proved that the NbO₆ octahedral structure remained intact even after Nd doping. The FTIR absorption bands related to Nb–O bending vibration frequencies were observed to have been modified from 618 cm⁻¹ in the pure composition to 624 cm⁻¹ in the Nd-doped composition. As for the Raman analysis, peaks were observed to depend on composition, showing slight shiftings and broadenings. In particular, the Nb–O symmetric stretching vibrations showed a shift from 865.92 cm⁻¹ in BBNB0 to 862.17 cm⁻¹ in BBNB4, and the Nb–O bond lengths calculated ranged from 1.7733 Å to 1.7756 Å, respectively.

The optical analysis done through diffuse reflectance spectroscopy indicated that the Nd substitution plays a role in determining the electronic structure and the optical

absorption properties of the BBN ceramic materials. The optical bandgap was first raised from 2.6526 eV for BBNB0 to 2.8424 eV for BBNB1 and then lowered to 2.6359 eV for BBNB4. Such variations could be due to lattice strain, defects, and localized electronic states induced by the replacement of rare earth ions.

Ferroelectric analysis confirmed the presence of very small P-E hysteresis loops for all the compositions, which is consistent with relaxor ferroelectric behaviour with low hysteresis losses. Nd doping was able to lower the remnant polarization but improve energy storage efficiency. Out of all compositions, the highest energy efficiency of approximately 93.4% at 60 kV/cm was observed for BBNB2. For BBNB2, the efficiency remained above 91% under larger electric fields. With an electric field of 85 kV/cm, the recoverable energy density (W_{rec}) was found to be 0.32914 J/cm³ for BBNB2 with low remnant polarization.

Dielectric studies revealed diffuse ferroelectric–paraelectric phase transitions in the temperature range of 400–450 K for all compositions. The dielectric constant exhibited strong frequency dependence, confirming relaxor ferroelectric characteristics. The diffuseness parameter (γ) obtained from the modified Curie–Weiss relation was found to be greater than 1 for all compositions, further supporting diffuse phase transition behaviour. The highest γ value of 1.7511 was observed for BBNB2, indicating enhanced relaxor nature compared to other samples. In addition, BBNB2 consistently exhibited higher dielectric constant values together with lower dielectric loss, demonstrating improved dielectric stability and electrical response.

Overall, the present study establishes that Nd³⁺ substitution is an effective strategy for tuning the structural and functional properties of BaBi₂Nb₂O₉ ceramics. Among all investigated compositions, BBNB2 ($x = 0.06$) exhibited the most balanced combination of dielectric, ferroelectric, optical, and microstructural properties. The enhanced energy efficiency, stable dielectric behaviour, and preserved structural integrity make Nd-doped BBN ceramics promising candidates for applications in energy-storage devices, high-temperature capacitors, and advanced lead-free electronic components.

CHAPTER 5

FUTURE SCOPE

Results from the present study demonstrate promising prospects of utilizing Nd-doped BBN ceramics in the area of high-performing dielectric, ferroelectric, and energy storage devices owing to superior structural and electrical properties of the material. Nonetheless, there remains room for optimization of these materials for practical applications through further studies. For instance, the effect of the concentration of Nd^{3+} doping needs to be studied thoroughly to gain a comprehensive understanding of compositional influence on dielectric relaxation, polarization effects, and electrical conductivity. Additionally, co-doping with other rare earth elements such as Er^{3+} , Sm^{3+} , La^{3+} , or Dy^{3+} may further enhance the relaxation behaviour and other relevant properties. Future studies may aim to explore other aspects that determine the performance of Nd-doped BBN ceramics as dielectric and ferroelectric materials. Microstructural optimization may play an important role in enhancing the performance of the material. Characterization techniques including impedance spectroscopy, XPS, TEM, and Raman analysis may help understand the nature of charge transport in the material and lattice changes resulting from doping with Nd^{3+} . Domain dynamics and polarization behaviour of the material under different electric fields may also be studied.

As the BBNB2 system shows relatively better dielectric and ferroelectric properties compared to other compositions, this composition may be subjected to detailed studies under practical working conditions like high temperature, high frequency, and high electric field operations. Fatigue behavior, retention study, thermal aging, and cyclic stability tests may be performed to determine the reliability and life expectancy of these materials for their industrial usage. Besides, sintering conditions and preparation method optimization will help improve the densification and electrical properties of these materials.

From the application point of view, rare earth modified BBN ceramics are suitable for applications in high energy density capacitors, embedded capacitive devices, electroceramic sensors, actuators, piezoelectric devices, and temperature-stable dielectrics. The relaxor nature and stable dielectric properties render these materials attractive candidates for application in modern power electronic devices and pulsed

energy storage systems. Moreover, thin film research and MLCC-based studies may pave the way for development of miniaturized electronic devices.

In summary, the present work provides an excellent base for performing further research into rare earth modified Aurivillius compounds. With proper optimization and detailed device tests, Nd doped BBN ceramics have the potential to become efficient and reliable materials for electronic and energy storage applications.

CHAPTER 6

REFERENCES

1. V. Veerapandiyan, F. Beneš, T. Gindel, M. De Luca, Strategies to improve the energy storage properties of perovskite-free relaxor ferroelectrics: A review, *Materials* **13** (24) (2020) 5742. <https://doi.org/10.3390/ma13245742>
2. G. Liu, S. Zhang, W. Jiang, W. Cao, Losses in ferroelectric materials, *Mater. Sci. Eng. R Rep.* **89** (2015) 1–48. <https://doi.org/10.1016/j.mser.2015.01.002>
3. J. Ye, G. Wang, X. Chen, X. Dong, Effect of rare-earth doping on dielectric property and polarization behavior of antiferroelectric sodium niobate-based ceramics, *J. Materiomics* **7** (2) (2021) 339–346. <https://doi.org/10.1016/j.jmat.2020.08.007>
4. W. Huai, X. Fu, Y. Zhao, Z. Cai, S. Luan, Z. Xu, H. He, J. Wang, Z. Fu, X. Cao, L. Zhang, R. Sun, Enhanced temperature stability and reliability for Ho/Mg co-doped ultra-thin BaTiO₃-based MLCCs, *Ceram. Int.* **51** (27C) (2025) 55748–55756. <https://doi.org/10.1016/j.ceramint.2025.09.294>
5. I. Bella, T.P. Wendari, N. Jamarun, N. Mufti, Zulhadjri, Structural transformation in Mn-substituted Sr₂Bi₂Ta₂TiO₁₂ Aurivillius phase, *Ceram. Int.* **47** (6) (2021) 8014–8019. <https://doi.org/10.1016/j.ceramint.2020.11.154>
6. P. Gupta, P.K. Mahapatra, R.N.P. Choudhary, Structural and electrical characteristics of rare-earth modified bismuth layer structured compounds, *J. Alloys Compd.* **863** (2021) 158457. <https://doi.org/10.1016/j.jallcom.2020.158457>
7. J. Shi, X. Liu, W. Tian, High energy-storage properties of Bi_{0.5}Na_{0.5}TiO₃–BaTiO₃–SrTi_{0.875}Nb_{0.1}O₃ relaxors, *J. Mater. Sci. Technol.* **34** (12) (2018) 2371–2374. <https://doi.org/10.1016/j.jmst.2018.06.008>
8. Z. Liu, P. Ren, C. Long, X. Wang, Y. Wan, G. Zhao, Enhanced energy storage properties of NaNbO₃- and SrZrO₃-modified BNT ceramics, *J. Alloys Compd.* **721** (2017) 538–544. <https://doi.org/10.1016/j.jallcom.2017.05.162>
9. A. Banwal et al., Temperature stability and improved energy storage efficiency of BaBi₂Nb₂O₉: Er³⁺/Yb³⁺ relaxor ferroelectric ceramic, *Appl. Phys. A* **130** (2024) 334. <https://doi.org/10.1007/s00339-024-07475-x>

10. F. Luo et al., Up-conversion luminescence and energy storage performance of Yb³⁺/Er³⁺ co-doped glass-ceramics, *J. Alloys Compd.* **910** (2022) 164859.
<https://doi.org/10.1016/j.jallcom.2022.164859>
11. P. Wang et al., Energy density capability and upconversion luminescence in Er³⁺/Yb³⁺ co-doped BNT thin films, *Ceram. Int.* **48** (19) (2022) 28606–28613.
<https://doi.org/10.1016/j.ceramint.2022.06.174>
12. A. Banwal, R. Bokolia, Enhanced upconversion luminescence and optical temperature sensing in Er³⁺-doped BaBi₂Nb₂O₉, *Ceram. Int.* **48** (2) (2022) 2230–2240. <https://doi.org/10.1016/j.ceramint.2021.09.314>
13. Zulhadjri, A. Rizki, T.P. Wendari, Y.E. Putri, Structural and ferroelectric modifications in SrBi₂Nb₂O₉ by Nd³⁺ doping, *Mater. Chem. Phys.* **331** (2025) 130177. <https://doi.org/10.1016/j.matchemphys.2024.130177>
14. C. Karthik et al., Relaxor characteristics of layered Ba_{1-3/2}xLa_xBi₂Nb₂O₉ ceramics, *J. Appl. Phys.* **100** (2006) 014106. <https://hal.science/hal-00131722v1>
15. J. Makowska et al., Impedance spectroscopy of Sm-doped BaBi₂Nb₂O₉ Aurivillius ceramics, *Materials* **17** (2024) 4532.
<https://doi.org/10.3390/ma17174360>
16. M. Rerak et al., Effect of Pr doping on BaBi₂Nb₂O₉ Aurivillius ceramics, *Materials* **15** (2022) 5881. <https://doi.org/10.3390/ma1516579>
17. A. Banwal, R. Bokolia, Phase evolution and microstructure of BaBi₂Nb₂O₉ ceramics, *Mater. Today Proc.* **46** (4) (2021) 10121–10124.
<https://doi.org/10.1016/j.matpr.2020.09.380>
18. C. Burda, X. Chen, R. Narayanan, and M. A. El-Sayed, “Chemistry and properties of nanocrystals of different shapes,” *Chem. Mater.*, vol. 17, no. 20, pp. 5049–5055, 2005, <https://doi.org/10.1021/cr030063a>
19. A. Banwal, R. Bokolia, Efficient tunable temperature sensitivity in Er³⁺/Yb³⁺ co-doped BaBi₂Nb₂O₉, *J. Lumin.* **263** (2023) 120071.
<https://doi.org/10.1016/j.jlumin.2023.120071>
20. R.D. Shannon, Revised effective ionic radii, *Acta Crystallogr. A* **32** (1976) 751–767. <https://doi.org/10.1107/S0567739476001551>
21. Y. Zou et al., Development and optimization of porosity measurement techniques, *Ceram. Int.* **42** (2A) (2016) 2861–2870.
<https://doi.org/10.1016/j.ceramint.2015.11.015>

22. A. Benali et al., Electrical conductivity and AC dielectric properties of $\text{La}_{0.8}\text{Ca}_{0.2-x}\text{Pb}_x\text{FeO}_3$, *J. Alloys Compd.* **653** (2015) 506–512.
<https://doi.org/10.1016/j.jallcom.2015.09.018>
23. Y. González-Abreu et al., Vibrational analysis on two-layer Aurivillius phase $\text{Sr}_{1-x}\text{Ba}_x\text{Bi}_2\text{Nb}_2\text{O}_9$, *Vib. Spectrosc.* **77** (2015) 91–98.
<https://doi.org/10.1016/j.vibspec.2015.01.005>
24. H.C. Gupta, Archana, V. Luthra, Lattice vibrations of $\text{ABi}_2\text{Nb}_2\text{O}_9$ crystals, *Vib. Spectrosc.* **56** (2) (2011) 235–240. <https://doi.org/10.1016/j.vibspec.2011.03.002>
25. F.D. Hardcastle, I.E. Wachs, Determination of niobium–oxygen bond distances by Raman spectroscopy, *Solid State Ionics* **45** (1991) 201–213.
[https://doi.org/10.1016/0167-2738\(91\)90153-3](https://doi.org/10.1016/0167-2738(91)90153-3)
26. R. Ramaraghavulu, S. Buddhudu, Structural and dielectric properties of $\text{BaBi}_2\text{Nb}_2\text{O}_9$ powders, *Ferroelectrics* **460** (1) (2014) 57–67.
<https://doi.org/10.1080/00150193.2014.874924>
27. A. Kumar et al., Microwave dielectric and Raman scattering studies on $\text{BaBi}_4\text{Ti}_4\text{O}_{15}$ ceramics, *J. Appl. Phys.* **104** (2008) 104104.
<https://doi.org/10.1063/1.302110>
28. M.X. Façanha et al., Up-conversion emission of $\text{Er}^{3+}/\text{Yb}^{3+}$ co-doped $\text{BaBi}_2\text{Nb}_2\text{O}_9$ phosphors, *J. Lumin.* **183** (2017) 102–107.
<https://doi.org/10.1016/j.jlumin.2016.08.011>
29. D. Nuzhnyy et al., Dynamics of phase transitions in Bi-layered ferroelectrics, *Phys. Rev. B* **74** (2006) 134105. <https://doi.org/10.1103/PhysRevB.74.134105>
30. A. Janotti, C.G. Van de Walle, Fundamentals of zinc oxide as a semiconductor, *Rep. Prog. Phys.* **72** (2009) 126501.
<https://doi.org/10.1088/0034-4885/72/12/126501>
31. P.A. Tanner, Some misconceptions concerning the electronic spectra of trivalent europium and cerium, *Chem. Soc. Rev.* **42** (2013) 5090–5101.
<https://doi.org/10.1039/C3CS60025F>
32. J.-C.G. Bünzli, S.V. Eliseeva, Lanthanide luminescence for functional materials and biosciences, *Chem. Sci.* **4** (2013) 1939–1949.
<https://doi.org/10.1039/C3SC22267B>
33. W.T. Carnall, P.R. Fields, K. Rajnak, Electronic energy levels of trivalent lanthanide aquo ions, *J. Chem. Phys.* **49** (1968) 4424–4442.
<https://doi.org/10.1063/1.1669893>

34. P. Kubelka, F. Munk, Ein Beitrag zur Optik der Farbanstriche, *Z. Tech. Phys.* **12** (1931) 593–601. <https://ci.nii.ac.jp/naid/10008164867>
35. J. Tauc, R. Grigorovici, A. Vancu, Optical properties of amorphous germanium, *Phys. Status Solidi B* **15** (1966) 627–637.
<https://doi.org/10.1002/pssb.19660150224>
36. J.B. Neaton, K.M. Rabe, Theory of polarization enhancement in epitaxial BaTiO₃/SrTiO₃ superlattices, *Appl. Phys. Lett.* **82** (2003) 1586–1588.
<https://doi.org/10.1063/1.1558070>
37. S. Saha, T.P. Sinha, A. Mookerjee, Electronic structure and optical properties of perovskite oxides, *Phys. Rev. B* **62** (2000) 8828–8834.
<https://doi.org/10.1103/PhysRevB.62.8828>
38. L.E. Cross, Relaxor ferroelectrics, *Ferroelectrics* **76** (1987) 241–267.
<https://doi.org/10.1080/00150198708016945>
39. R. Guo, L.E. Cross, S.-E. Park, B. Noheda, D.E. Cox, G. Shirane, Origin of high piezoelectric response in relaxors, *Phys. Rev. Lett.* **84** (2000) 5423–5426.
<https://doi.org/10.1103/PhysRevLett.84.5423>
40. L. Zheng et al., Tailored energy-storage performance in BNT–ST ceramics via BaBi₂Nb₂O₉, *J. Mater. Chem. C* **9** (2021) 5234–5243.
<https://doi.org/10.1039/D1TC00437A>
41. D. Li et al., Slim P–E hysteresis in Ba_{0.3}Sr_{0.7}TiO₃-modified BNT ceramics, *J. Adv. Ceram.* **9** (2020) 183–192. <https://doi.org/10.1007/s40145-020-0358-9>
42. L. Wei et al., Correlation among oxygen vacancies in bismuth titanate ceramics, *Appl. Phys. Lett.* **85** (20) (2004) 4628–4630. <https://doi.org/10.1063/1.1823583>
43. J.R. Scott, Energy storage in ferroelectric capacitors, *Ferroelectrics* **157** (1994) 1–12. <https://doi.org/10.1080/00150199408245121>
44. C. Miranda et al., Relaxor properties of Ba-based layered perovskites, *J. Eur. Ceram. Soc.* **21** (2001) 1303–1306.
[https://doi.org/10.1016/S0955-2219\(01\)00006-1](https://doi.org/10.1016/S0955-2219(01)00006-1)
45. Z. Bi, S. Zhou, J. Ye, N. Wang, F. Shang, J. Xu, H. Wang, BaTiO₃-based high-entropy ceramics for enhanced capacitive energy storage performance, *Ceram. Int.* **51** (2025) 16052–16060.
<https://doi.org/10.1016/j.ceramint.2025.01.44>

46. Adak, M.K., *et al.* Fatigue-free relaxor ferroelectric and electrocatalytic properties of Y-doped BaBi₂Nb₂O₉. *Ceram. Int.* **49** (2023) 20726–20738
<https://doi.org/10.1016/j.ceramint.2022.09.077>
47. P. Keburis et al., Dielectric properties of relaxor ceramics BBN, *Ferroelectrics* **353** (1) (2007) 149–153. <https://doi.org/10.1080/00150190701368109>
48. P. Sun et al., Enhanced energy storage in BaBi₂Me₂O₉ (Me = Nb, Ta), *Ceram. Int.* **46** (10B) (2020) 15907–15914.
<https://doi.org/10.1016/j.ceramint.2020.03.139>.
49. A. Khokhar, P.K. Goyal, O.P. Thakur, K. Sreenivas, Effect of excess bismuth doping effects in BaBi₄Ti₄O₁₅, *Ceram. Int.* **41** (3A) (2015) 4189–4198.
<https://doi.org/10.1016/j.ceramint.2014.12.103>
50. A. Ali, H. Zahid, Dielectric, ferroelectric and optical properties of Na and Nb co-doped (Bi_{0.5}Na_{0.5})_{0.94}Ba_{0.06}TiO₃, *Physics and Chemistry of Solid State* **22** (2021) 607–613. <https://doi.org/10.15330/pcss.22.4.607-613>.
51. S. Pattipaka, Y. Lim, Y.H. Son, Y.M. Bae, M. Peddigari, G.T. Hwang, Ceramic-based dielectric materials for energy storage capacitor applications, *Materials* **17** (2024) 2277. <https://doi.org/10.3390/ma17102277>
52. M. Fang, Y. Ji, Z. Zhang, Y. Yang, C. Liu, D. Wang, L. Zhang, J. Gao, X. Ren, Re-entrant relaxor-ferroelectric composite showing exceptional electromechanical properties, *NPG Asia Mater.* **10** (2018) 1029–1036.
<https://doi.org/10.1038/s41427-018-0093-7>.



DELHI TECHNOLOGICAL UNIVERSITY
(Formerly Delhi College of Engineering)
Shahbad Daultpur, Main Bawana Road, Delhi-42

PLAGIARISM VERIFICATION

Title of the thesis “**Structural and electrical study of Nd³⁺ doped BaBi₂Nb₂O₉, Aurivillius ceramic for energy storage applications**”

Total Pages : 44

Name of the Student (s)

- (1) Mahima Momaliya
- (2) Helna Benny

Supervisor : Dr. Renuka Bokolia

Department: Department of Applied Physics

This is to report that the above thesis was scanned for similarity detection. Process and outcome is given below:

Software used: **Turnitin**, Similarity Index: **8%** on the count of **8 words**, Total Word Count: 7,352

Date: May 25, 2026

Place: New Delhi

Date: 28 May 2026

DR. RENUKA BOKOLIA
(SUPERVISOR SIGNATURE)

Helna Benny
(24/MSCPHY/47)

Mahima Momaliya
(24/MSCPHY/31)

PLAGIARISM REPORT



Digital Receipt

This receipt acknowledges that Turnitin received your paper. Below you will find the receipt information regarding your submission.

The first page of your submissions is displayed below.

Submission author: Mahima Helna
Assignment title: Quick Submit
Submission title: Thesis_plag_report_1.docx
File name: Thesis_plag_report_1.docx
File size: 5.32M
Page count: 44
Word count: 7,352
Character count: 42,738
Submission date: 25-May-2026 05:00PM (UTC+0530)
Submission ID: 2969089646

ABSTRACT

In this work, neodymium (Nd^{3+})-substituted barium bismuth niobate ceramics, $\text{BaBi}_{1-x}\text{Nd}_x\text{Nb}_2\text{O}_{10}$ ($x = 0.00, 0.04, 0.06, 0.08, \text{ and } 0.10$), belonging to the Aurivillius family, were systematically investigated to examine the influence of Bi-site doping on the structural, dielectric, and energy-storage properties. All compositions were synthesized via the conventional solid-state route and sintered at 1050°C . XRD analysis confirmed the formation of a single-phase orthorhombic Aurivillius structure, indicating successful incorporation of Nd^{3+} with minimal lattice distortion. SEM analysis revealed plate-like grains with a reduction in grain size upon doping. FTIR analysis confirmed the retention of characteristic NbO_6 vibrational bands, indicating preservation of the layered Aurivillius framework after Nd^{3+} substitution. Dielectric studies exhibited broad, frequency-dependent peaks, confirming relaxor behavior with the diffuseness parameter γ ranging from 1.45 to 1.75. DC conductivity decreased with increasing Nd content due to enhanced resistivity. Simultaneous P-E loops with reduced remnant polarization favored energy-storage performance, with $\text{BaBi}_{0.94}\text{Nd}_{0.06}\text{Nb}_2\text{O}_{10}$ exhibiting an efficiency exceeding 90%. Raman and DRS analyses confirmed the preservation of the crystal structure and tunable band gaps, highlighting the strong potential of these ceramics for low-loss energy-storage applications.

1

Copyright 2026 Turnitin. All rights reserved.

DR. RENUKA BOKOLIA
(SUPERVISOR SIGNATURE)

Place: New Delhi
Date: 28 May 2026

Thesis_plag_report_1.docx

ORIGINALITY REPORT

8%	5%	6%	1%
SIMILARITY INDEX	INTERNET SOURCES	PUBLICATIONS	STUDENT PAPERS

PRIMARY SOURCES

1	www.science.gov Internet Source	2%
2	Ankita Banwal, Manoj Verma, Bharti Singh, Renuka Bokolia. "Temperature stability and improved energy storage efficiency of BaBi2Nb2O9: Er3+/Yb3+ relaxor ferroelectric ceramic under moderate electric fields", Applied Physics A, 2024 Publication	1%
3	link.springer.com Internet Source	1%
4	M. Naveed Ul-Haq, Tayyaba Yunus, Arif Mumtaz, V.V. Shvartsman, Doru C. Lupascu. "Magnetodielectric effect in relaxor/ferrimagnetic composites", Journal of Alloys and Compounds, 2015 Publication	<1%
5	Submitted to Indian Institute of Technology Guwahati Student Paper	<1%
6	archive.org Internet Source	<1%
7	ouci.dntb.gov.ua Internet Source	<1%
8	Zulhadjri, Alfir Rizki, Tio Putra Wendari, Yulia Eka Putri. "Structural and ferroelectric modifications in SrBi2Nb2O9 Aurivillius phase	<1%

compounds by Nd³⁺ ion doping", Materials Chemistry and Physics, 2024

Publication

- | | | |
|-------|--|------|
| 9 | Saloni Pendse, Jie Jiang, Yuwei Guo, Lifu Zhang et al. "Unit-Cell-Thick Oxide Synthesis by Film-Based Scavenging", The Journal of Physical Chemistry C, 2020 | <1 % |
| <hr/> | | |
| 10 | ris.utwente.nl
Internet Source | <1 % |
| <hr/> | | |
| 11 | Bandgar, A.B., S.R. Sabale, and S.H. Pawar. "Synthesis of nanocrystalline titanium dioxide using refluxed aqueous peroxy titanium complex solution", Micro & Nano Letters, 2011. | <1 % |
| <hr/> | | |
| 12 | Submitted to Jawaharlal Nehru University (JNU)
Student Paper | <1 % |
| <hr/> | | |
| 13 | Ullah, A.. "The effects of sintering temperatures on dielectric, ferroelectric and electric field-induced strain of lead-free Bi ⁰ . ⁵ (Na ⁰ . ⁷ 8K ⁰ . ²) ⁰ . ⁵ TiO ³ piezoelectric ceramics synthesized by the sol-gel technique", Current Applied Physics, 201011 | <1 % |
| <hr/> | | |
| 14 | H.R Rukmini, R.N.P Choudhary, V.V Rao. "Structural and electrical properties of sol-gel prepared (La,Li) modified PZT ceramics", Materials Letters, 1998 | <1 % |
| <hr/> | | |
| 15 | Wen-Bo Li, Di Zhou, Ran Xu, Li-Xia Pang, Ian M. Reaney. " BaTiO –Bi(Li Ta)O , Lead-Free Ceramics, and Multilayers with High Energy | <1 % |

Storage Density and Efficiency ", ACS Applied
Energy Materials, 2018

Publication

- 16 Coondoo, I.. "Structural, dielectric and electrical studies in tungsten doped $\text{SrBi}_2\text{Ta}_2\text{O}_9$ ferroelectric ceramics", *Ceramics International*, 200701
Publication

<1 %

- 17 ijrsrset.com
Internet Source

<1 %

- 18 orbi.lu.uni.lu
Internet Source

<1 %

- 19 Ankita Banwal, Bhavya Kumar, Manoj Verma, Ankur Shandilya, Bharti Singh, Renuka Bokolia. "Improved optical characteristics in $\text{BaBi}_2\text{Nb}_2\text{O}_9$ ferroelectric ceramic infused with transition metal ion (W^{6+}) and rare earth ions ($\text{Er}^{3+}/\text{Yb}^{3+}$)", *Journal of Luminescence*, 2024
Publication

<1 %

- 20 Megha Narwan, Ankita Banwal, Bhavya Kumar, Manoj Verma, Ankur Shandilya, Vineet Kumar Rai, Richa Sharma, Renuka Bokolia. " Ho^{3+} - driven novel orange emission and enhanced energy storage in lead-free $\text{Bi}_{0.5}\text{Na}_{0.5}\text{TiO}_3$ ceramics", *Ceramics International*, 2025
Publication

<1 %

- 21 Nazia Khatun, Sajib Ahmed, Mohammad Sajjad Hossain, Syed Farid Uddin Farhad et al. "Influence of Y^{3+} and La^{3+} ions on the structural, magnetic, electrical, and optical properties of cobalt ferrite nanoparticles", *Heliyon*, 2023
Publication

<1 %

22	sciendo.com Internet Source	<1 %
23	Fergy John, Jijimon K. Thomas, John Jacob, Sam Solomon. "Electrical and Optical Properties of Nanocrystalline A ₈ ZnNb ₆ O ₂₄ (A=Ba, Sr, Ca, Mg) Ceramics", Journal of Electronic Materials, 2017 Publication	<1 %
24	Nurul Pratiwi, Yulia Eka Putri, Tio Putra Wendari, Andon Insani, Zulhadjri. "Structure-property relationship in Sn ²⁺ -doped PbBi ₂ Nb ₂ O ₉ : Toward tunable dielectric and optical characteristics", Materials Science in Semiconductor Processing, 2026 Publication	<1 %
25	S. Shanmuga Sundari, Binay Kumar, R. Dhanasekaran. "Synthesis, dielectric and relaxation behavior of lead free NBT-BT ceramics", Ceramics International, 2013 Publication	<1 %
26	Submitted to Universitas Andalas Student Paper	<1 %
27	Zulhadjri, Alfir Rizki, Muhammad Agung Andri, Tio Putra Wendari, Yulia Eka Putri, Upita Septiani, Rahmayeni, Imelda. "Structure-Property Correlation in La ³⁺ -Substituted SrBi ₂ Nb ₂ O ₉ Ferroelectric Ceramics Synthesized via Molten Salt Route", Materials Research, 2026 Publication	<1 %
28	arxiv.org Internet Source	<1 %
29	pdffox.com Internet Source	<1 %

30	scholarbank.nus.edu.sg	<1 %
	Internet Source	
31	studymoose.com	<1 %
	Internet Source	
32	waseda.repo.nii.ac.jp	<1 %
	Internet Source	
33	www.mdpi.com	<1 %
	Internet Source	

Exclude quotes ☐ On

Exclude bibliography ☐ On

Exclude matches

☐ < 8 words

AI-REPORT

Mahima Momaliya

Thesis_plag_report.docx

-  Quick Submit
-  Quick Submit
-  Delhi Technological University

Document Details

Submission ID
trn:oid::1:3574939038

Submission Date
May 20, 2026, 9:02 PM GMT+5:30

Download Date
May 20, 2026, 9:09 PM GMT+5:30

File Name
Thesis_plag_report.docx

File Size
5.3 MB

44 Pages

7,352 Words

42,738 Characters

*% detected as AI

AI detection includes the possibility of false positives. Although some text in this submission is likely AI generated, scores below the 20% threshold are not surfaced because they have a higher likelihood of false positives.

Caution: Review required.


It is essential to understand the limitations of AI detection before making decisions about a student's work. We encourage you to learn more about Turnitin's AI detection capabilities before using the tool.

Disclaimer

Our AI writing assessment is designed to help educators identify text that might be prepared by a generative AI tool. Our AI writing assessment may not always be accurate (i.e., our AI models may produce either false positive results or false negative results), so it should not be used as the sole basis for adverse actions against a student. It takes further scrutiny and human judgment in conjunction with an organization's application of its specific academic policies to determine whether any academic misconduct has occurred.


JOURNAL INDEX PROOFs

CERAMICS INTERNATIONAL (ELSEVIER)

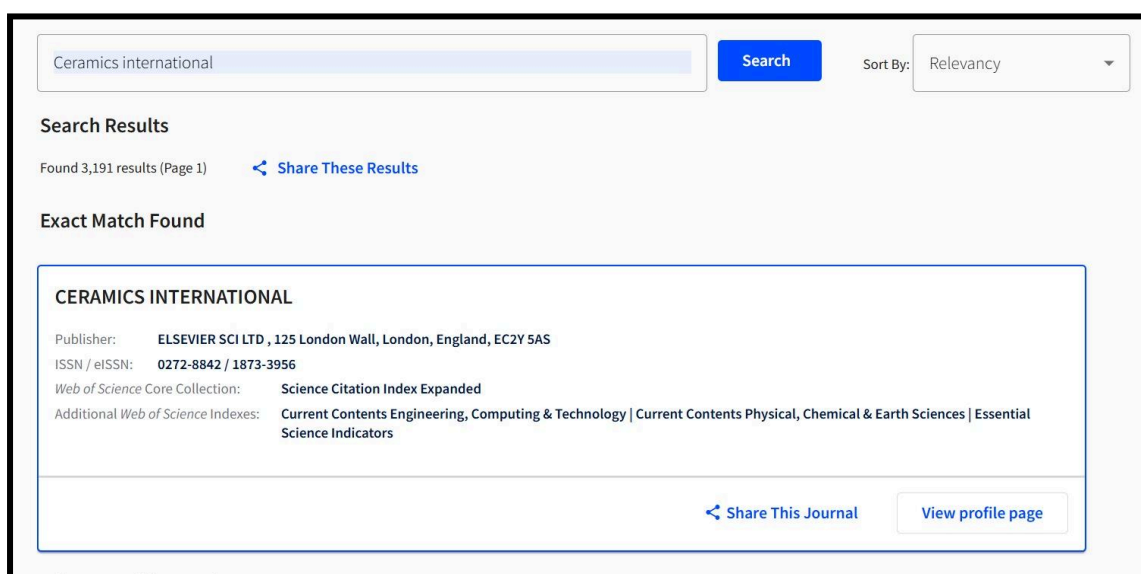

The screenshot shows the Elsevier search interface. A search bar at the top contains the text "Ceramics international". To the right of the search bar is a blue "Search" button and a "Sort By: Relevancy" dropdown menu. Below the search bar, the text "Search Results" is displayed, followed by "Found 3,191 results (Page 1)" and a blue link "Share These Results". Underneath, the section "Exact Match Found" is highlighted. A box contains the journal details: "CERAMICS INTERNATIONAL", Publisher: ELSEVIER SCI LTD, 125 London Wall, London, England, EC2Y 5AS, ISSN / eISSN: 0272-8842 / 1873-3956, Web of Science Core Collection: Science Citation Index Expanded, and Additional Web of Science Indexes: Current Contents Engineering, Computing & Technology | Current Contents Physical, Chemical & Earth Sciences | Essential Science Indicators. At the bottom of the box are two buttons: "Share This Journal" and "View profile page".

SCI/SCIE and Scopus indexed journal published by Clarivate

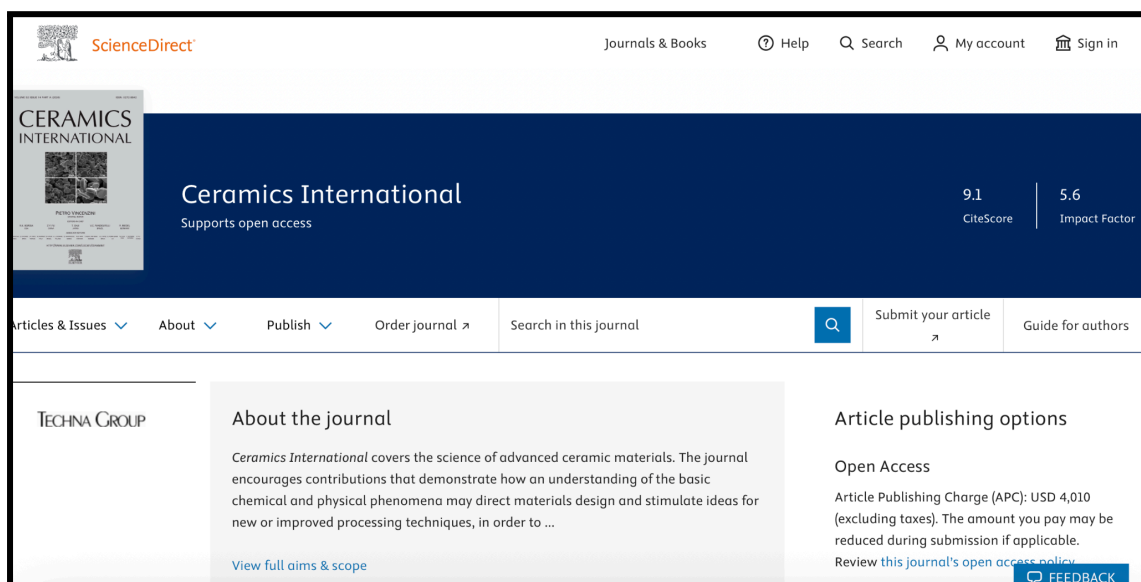

The screenshot shows the ScienceDirect journal page for Ceramics International. The header includes the ScienceDirect logo, "Journals & Books", "Help", "Search", "My account", and "Sign in". The journal cover image is on the left. The main title "Ceramics International" is in the center, with "Supports open access" below it. To the right, the CiteScore is 9.1 and the Impact Factor is 5.6. Below the header, there is a navigation bar with links: "Articles & Issues", "About", "Publish", "Order journal", "Search in this journal", "Submit your article", and "Guide for authors". The main content area is divided into three sections: "TECHNA GROUP" on the left, "About the journal" in the center, and "Article publishing options" on the right. The "About the journal" section describes the journal's focus on advanced ceramic materials. The "Article publishing options" section includes information about Open Access and Article Publishing Charge (APC). A "FEEDBACK" button is located at the bottom right.

Impact factor and cite score published by ScienceDirect

Indian Journal of Pure & Applied Physics

Search

Sort By: Relevancy

Search Results

Found 2,585 results (Page 1) [Share These Results](#)

Exact Match Found

INDIAN JOURNAL OF PURE & APPLIED PHYSICS

OPEN ACCESS

Publisher: NATL INST SCIENCE COMMUNICATION-NISCAIR, DR K S KRISHNAN MARG, PUSA CAMPUS, NEW DELHI, India, 110 012

ISSN / eISSN: 0019-5596 / 0975-1041

Web of Science Core Collection: Science Citation Index Expanded

Additional Web of Science Indexes: Current Contents Physical, Chemical & Earth Sciences | Essential Science Indicators

[Share This Journal](#)

[View profile page](#)

* Requires free login.

SCI/SCIE and Scopus indexed journal published by Clarivate

Scopus Preview

[Author Search](#) [Sources](#) [?](#) [🏛️](#)

[Create account](#) [Sign in](#)

Source details

[Feedback](#) [Compare sources](#)

Indian Journal of Pure and Applied Physics

[Open Access](#) ⓘ

Years currently covered by Scopus: 1969, 1971, from 1974 to 1990, from 1993 to 2025

Publisher: National Institute of Science Communication and Policy Research

ISSN: 0019-5596 **E-ISSN:** 0975-1041

Subject area: [Physics and Astronomy: Physics and Astronomy \(miscellaneous\)](#)

Source type: Journal


[View all documents](#) [Set document alert](#) [Save to source list](#)

CiteScore 2024 ⓘ
1.6

SJR 2024 ⓘ
0.176

SNIP 2024 ⓘ
0.424

Cite score and Scopus indexed journal published by CSIR-NIScPR



Bi-site Nd^{3+} substitution-induced dielectric relaxation and enhanced energy storage performance in $\text{BaBi}_2\text{Nb}_2\text{O}_9$ layered ceramics

Helna Benny^a, Mahima Momaliya^a, Surya Pratap Singh^a, Ravindra Kumar^a, Manoj Verma^b, Renuka Bokolia^{a,*}

^a FMRL, Department of Applied Physics, Delhi Technological University, Shahbad Daultpur, Main Bawana Road, Delhi, 110042, India

^b Department of Physics, Hindu College, University of Delhi, Delhi, 110007, India

ARTICLE INFO

Keywords:
Ceramics
Dielectrics
Ferroelectrics
Energy storage

ABSTRACT

Neodymium-substituted $\text{BaBi}_{2-x}\text{Nd}_x\text{Nb}_2\text{O}_9$ ($x = 0.00, 0.04, 0.06, 0.08$, and 0.10) Aurivillius ceramics were synthesized via a conventional solid-state route to investigate the effect of Bi-site doping on structural, dielectric, and energy storage properties. X-ray diffraction confirmed a single-phase orthorhombic Aurivillius structure for all compositions, indicating successful incorporation of Nd^{3+} ions without secondary phases. Subtle lattice distortion and NbO_6 octahedral modification were evidenced by XRD peak shifts and Raman spectroscopy. Scanning electron microscopy revealed typical plate-like grains with a systematic reduction in grain size upon Nd substitution. Electrical measurements showed a decrease in DC conductivity with increasing Nd content, attributed to suppressed oxygen-vacancy-mediated charge transport. Dielectric studies exhibited strong frequency dispersion and diffuse phase transition behavior, with diffuseness parameters (γ) ranging from 1.45 to 1.75, confirming relaxor ferroelectric characteristics. Slim, unsaturated P–E loops with reduced remnant polarization favored energy storage performance, with $\text{BaBi}_{1.94}\text{Nd}_{0.06}\text{Nb}_2\text{O}_9$ exhibiting efficiency exceeding 90% under applied electric fields of 60–85 kV/cm.

1. Introduction

Ferroelectric ceramics are materials that naturally exhibit electric polarization, which can be reversed when external electric field is applied [1]. In such materials, dipoles are aligned in particular directions within small domains. These materials exhibit spontaneous polarization that can be effectively controlled using external electric field. Ferroelectric ceramics find widespread applications as sensors, actuators, capacitors, and memory storage devices. The property of polarization, which can be controlled using electric field, along with domain control, is an important factor due to which ferroelectric ceramics are widely preferred as host materials [2]. Moreover, they possess multifunctional abilities in terms of electrical, optical, piezoelectric, and pyroelectric properties. Rare earths are widely used as dopants in ferroelectric ceramic material because they possess the capability to substantially increase the efficiency of ferroelectric ceramics materials. This leads to a relaxor-like property being developed due to subtle variations in phase transitions occurring during the process to be wider and stable [3]. Rare earth improves the characteristics of dielectric materials to be suitable for energy storage applications. These elements help stabilize ferroelec-

tric polarization, improve grain growth control, and allow better tuning of the microstructure. Another important advantage is the reduction of leakage current, thereby enhancing device efficiency and reliability. Furthermore, the rare earth element enhances the thermal stability of the material, thus improving its efficiency in high-temperature applications [4]. Recently, lead-free materials have been getting more attention in the research world due to the various environmental and health issues caused by lead, and it has taken a diversion towards the Aurivillius compounds, the family of Bismuth layered perovskite type oxides having generalised formula $(\text{Bi}_2\text{O}_7)^{2+}(\text{A}_{n-1}\text{B}_n\text{O}_{3n+1})^{2-}$ [5,6]. The A-site cations are usually large ions or the rare earth ions, which are ionically compatible with Bi^{3+} in the $(\text{Bi}_2\text{O}_7)^{2+}$ layers, whereas the B-site cations are smaller ions. The value of n indicates number of perovskite layers sandwiched between Bi_2O_7 sheets (see Tables 6–8).

Here, we investigate barium bismuth niobate (BBN), where $n = 2$, implying two perovskite-like layers between the $(\text{Bi}_2\text{O}_7)^{2+}$ sheets [7–9]. BBN is a relaxor ferroelectric with larger maximum polarization and lower remnant polarization and thus falls under the category of Bismuth Layered-Structured Ferroelectrics (BLSF) [9]. BLSFs are considered strong alternatives to lead-based ceramics because they are non

* Corresponding author.

E-mail address: renuka1274@gmail.com (R. Bokolia).

<https://doi.org/10.1016/j.ceramint.2026.05.398>

Received 23 February 2026; Received in revised form 17 May 2026; Accepted 26 May 2026
0272-8842/© 20XX


Note: Low-resolution images were used to create this PDF. The original images will be used in the final composition.

Track Your Accepted Article

The easiest way to check the publication status of your accepted article

Bi-site Nd³⁺ substitution–induced dielectric relaxation and enhanced energy storage performance in BaBi₂Nb₂O₉ layered ceramics

Article reference	CERI52748
Journal	Ceramics International
Corresponding author	Renuka Bokolia
First author	Helna Benny
Received at Editorial Office	23 Feb 2026
Article revised	17 May 2026
Article accepted for publication	26 May 2026



ISSN 0272-8842

Last update: 27 May 2026

[Share via email](#)

Status comment

- Your article has been received for production.
- Please complete your Rights & Access form if you've not already done so. If the form is not completed before publication of your paper, we will proceed with publication on the explicit understanding that we have all the rights customarily included in a publishing and distribution license, including the exclusive right to publish and use the article in all media and to sublicense such rights. Your own rights to share such articles with others are set out in [Elsevier's Sharing Policy](#).

Production events

27 May 2026	Rights & Access form sent to you for completion
27 May 2026	Offprint order letter sent to you for completion
26 May 2026	Received for production

Complimentary items

- You are entitled to a Share Link for your article free of charge. The Share Link will be sent you as soon as the final article is published in an issue.

Bibliographic information

Volume/Issue
Will appear soon

Full bibliographic details
Will appear soon

Article available online
Will appear soon

[Track another article](#)

Official acceptance status of the manuscript submitted to Ceramics International (SCI/SCIE indexed, Impact Factor: 5.6)

em Ceramics International								
Home Main Menu Submit a Manuscript About Help								
← Submissions with an Editorial Office Decision for Author								
Page: 1 of 1 (1 total completed submissions) Results per page 10								
Action	Manuscript Number	Title	Authorship	Initial Date Submitted	Status Date	Current Status	Date Final Disposition Set	Final Disposition
View Submission	CERI-D-26-02861	Bi-site Nd ³⁺ substitution–induced dielectric relaxation and enhanced energy storage performance in BaBi ₂ Nb ₂ O ₉ layered ceramics	Other Author	Feb 23, 2026	May 26, 2026	Completed - Accept	May 26, 2026	Accept

Editorial decision confirming acceptance of the manuscript in Ceramics International on 26 May 2026.

Manuscript Status in Indian Journal of Pure and Applied Physics

or.niscpr.res.in

96

Indian Journal of Pure & Applied Physics (IJPAP)

Submissions

My Queue 1

Archived

Help

My Assigned

Search

Filters

New Submission

31000 Momaliya et al.

1/4

1

Review

View

Title: X-Ray Diffraction Based Structural Optimiz...

or.niscpr.res.in

Indian Journal of Pure & Applied Physics (IJPAP)

My Assigned

Filters

New Submission

31000 Momaliya et al.

1/4
 1

Review

View

^

Title: X-Ray Diffraction Based Structural Optimiz...

1/4	Assigned reviews completed
0	Revisions submitted
1	Open discussions

Last activity recorded on Thursday, May 21, 2026.

APPENDICES
CONFERENCE PARTICIPATION CERTIFICATE



Bi-site Nd³⁺ substitution-induced dielectric relaxation and enhanced energy storage performance in BaBi₂Nb₂O₉ layered ceramics

Helna Benny¹, Mahima Momaliya¹, Surya Pratap Singh¹, Ravindra Kumar¹, Manoj Verma²,
Renuka Bokolia^{1*}

¹*FMRL, Department of Applied Physics, Delhi Technological University, Shahbad Daultapur,
Main Bawana Road, Delhi, 110042, India*

²*Department of Physics, Hindu College, University of Delhi, Delhi -110007, India*

ABSTRACT

Neodymium-substituted BaBi_{2-x}Nd_xNb₂O₉ ($x = 0.00, 0.04, 0.06, 0.08, \text{ and } 0.10$) Aurivillius ceramics were synthesized via a conventional solid-state route to investigate the effect of Bi-site doping on structural, dielectric, and energy storage properties. X-ray diffraction confirmed a single-phase orthorhombic Aurivillius structure for all compositions, indicating successful incorporation of Nd³⁺ ions without secondary phases. Subtle lattice distortion and NbO₆ octahedral modification were evidenced by XRD peak shifts and Raman spectroscopy. Scanning electron microscopy revealed typical plate-like grains with a systematic reduction in grain size upon Nd substitution. Electrical measurements showed a decrease in DC conductivity with increasing Nd content, attributed to suppressed oxygen-vacancy-mediated charge transport. Dielectric studies exhibited strong frequency dispersion and diffuse phase transition behavior, with diffuseness parameters (γ) ranging from 1.45 to 1.75, confirming relaxor ferroelectric characteristics. Slim, unsaturated P-E loops with reduced remnant polarization favored energy storage performance, with BaBi_{1.94}Nd_{0.06}Nb₂O₉ exhibiting efficiency exceeding 90% under applied electric fields of 60–85 kV/cm.

Keywords: Ceramics, Dielectrics, Ferroelectrics, Energy Storage

JOURNAL PAPER (IJPAP)

X-Ray Diffraction Based Structural Optimization and Electrical Properties of Nd³⁺ Doped BaBi₂Nb₂O₉ Aurivillius Ceramics

Mahima Momaliya¹, Helna Benny¹, Surya Pratap Singh¹, Manoj Verma², Renuka Bokolia^{1*}

¹FMRL, Department of Applied Physics, Delhi Technological University, Shahbad Daultapur, Main Bawana Road, Delhi, 110042, India

²Department of Physics, Hindu College, University of Delhi, Delhi -110007, India

ABSTRACT

Nd³⁺ doped BaBi₂Nb₂O₉ (BBN) ceramics were synthesised using conventional solid-state reaction route with optimized calcination (950 °C) and sintering (1050 °C) conditions to achieve phase purity. X-ray diffraction confirmed conformation of single-phase aurivillius framework with Fmmm space group. while scanning electron microscopy revealed a dense microstructure with a reduced, uniformly distributed grain size after Nd incorporation. FTIR analysis verified the presence of characteristic NbO₆ bonding, confirming structural stability. Ferroelectric studies showed well defined PE loops with decrease in maximum polarisation (P_m) from 12.85 $\mu\text{C}/\text{cm}^2$ to 8.47 $\mu\text{C}/\text{cm}^2$ upon Nd doping. Dielectric measurements showed a slight increase in dielectric constant (ϵ') from 255.77 to 267.30 at 455 K on Nd³⁺ doping along with reduced dielectric loss (ϵ'') and stable frequency dependent behaviour. These properties confirm that Nd doped BBN is a potential alternative for lead free energy storage and capacitor applications.