

# **Enhanced energy harvesting performance of flexible PVDF piezoelectric nanogenerators using SnS<sub>2</sub>/SnSe<sub>2</sub> heterostructure as nanofillers**

A DISSERTATION REPORT

SUBMITTED IN PARTIAL FULFILLMENT OF THE REQUIREMENTS  
FOR THE AWARD OF THE DEGREE  
OF

**MASTERS OF SCIENCE  
IN  
PHYSICS**

Submitted by:  
**UMESH KUMAR**  
24/MSCPHY/27

&  
**PRAGYA DOBHAL**  
24/MSCPHY/48

Under the supervision of  
**DR. BHARTI SINGH**



**DEPARTMENT OF APPLIED PHYSICS**  
**DELHI TECHNOLOGICAL UNIVERSITY**  
(Formerly Delhi College of Engineering)

**DEPARTMENT OF APPLIED PHYSICS**  
**DELHI TECHNOLOGICAL UNIVERSITY**  
**(Formerly Delhi College of Engineering)**  
**Bawana Road, Delhi-110042**

**CERTIFICATE**

I hereby certify that the Project Dissertation titled " *Enhanced energy harvesting performance of flexible PVDF piezoelectric nanogenerators using  $\text{SnS}_2/\text{SnSe}_2$  heterostructure as nanofillers*" which is submitted by **UMESH KUMAR**, Roll No. 2K24/MSCPHY/27 and **PRAGYA DOBHAL**, 2K24/MSCPHY/48, Department of Applied Physics, Delhi Technological University, Delhi in partial fulfilment of the requirement for the award of the degree of Master of Science, is a record of the project work carried out by the students under my supervision. To the best of my knowledge this work has not been submitted in part or full for any Degree or Diploma to this University or elsewhere.

Place: Delhi

Date: 29/05/2026

  
**Dr. Bharti Singh**  
**(SUPERVISOR)**

**DEPARTMENT OF APPLIED PHYSICS**  
**DELHI TECHNOLOGICAL UNIVERSITY**

We hereby certify that the work which is presented in the Major Project-II/Research Work entitled "**Enhanced energy harvesting performance of flexible PVDF piezoelectric nanogenerators using  $\text{SnS}_2/\text{SnSe}_2$  heterostructure as nanofillers**" in fulfilment of the requirement for the award of the Degree of Bachelor/Master of Technology in Department of Applied Physics, Delhi Technological University, Delhi is an authentic record of my/our own carried out during a period from June 2025 to June 2026, under the supervision of **Dr. Bharti Singh**.

The matter presented in this report/thesis has not been submitted by us for the award of any other degree of this or any other Institute/University. The work has been communicated in Scopus indexed journal with the following details.

**Title of the Paper:** *Enhanced energy harvesting performance of flexible PVDF piezoelectric nanogenerators using  $\text{SnS}_2/\text{SnSe}_2$  heterostructure as nanofillers.*


**Authors names:** Pragya Dobhal, Umesh Kumar, Ankita Dahiya, Bharti Singh.

**Name of journal:** Indian Journal of Pure and Applied Physics (IJPAP)

**Status of paper:** Accepted

**Date of paper communication:** 18 May 2026

**Date of paper publication:** Yet to be published

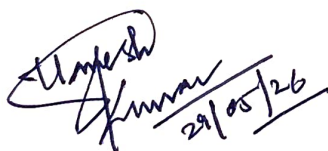

**Umesh Kumar (24/MSCPHY/27)**



**Pragya Dobhal (24/MSCPHY/48)**

**SUPERVISOR CERTIFICATE**

To the best of my knowledge, the above work has not been submitted in part or full for any Degree or diploma to this University or elsewhere. I, further certify that the publication and indexing information given by the students is correct.

**Place:** Delhi

**Date:** 29/05/2026



**Dr. Bharti Singh**

## **ACKNOWLEDGEMENT**

*We (Umesh Kumar and Praga Dobhal) would like to express our profound gratitude to **Dr. Bharti Singh**, Assistant Professor, Department of Applied Physics, Delhi Technological University, for granting us the opportunity to undertake this dissertation under her distinguished guidance. Her constant encouragement, scholarly insight, thoughtful suggestions, and unwavering support have been invaluable throughout the course of this work. We are equally grateful to the **Department of Applied Physics** and the **Advanced Materials and Devices Laboratory** for providing us with the necessary facilities, technical support, and an enriching academic environment that made the successful completion of this dissertation possible.*

*We would also like to convey our heartfelt appreciation to **Ms. Ankita Dahiya** for her constant guidance, patience, and generous assistance throughout the experimental phase of our work. Her willingness to help us at every stage, particularly during sample preparation and laboratory procedures, contributed immensely to the progress of this dissertation. We are sincerely thankful to all the **Ph.D. scholars and members of the Advanced Materials and Devices Laboratory** for their cooperation, valuable discussions, and for fostering a warm and encouraging research atmosphere.*

*We owe our deepest gratitude to our families (**Mrs. Bhawna Dobhal & Mr. Piyush Dobhal**) (**Mrs. Annu Jangra & Mr. Rajesh Jangra**) for their unconditional love, trust, and unwavering moral support throughout this journey. Their patience, understanding, and silent sacrifices became our source of strength during the most demanding phases of this work. Their constant encouragement gave us the confidence to persevere with dedication and determination.*

*We would also like to extend our sincere thanks to our dear friends, namely **Ms. Smriti Jha, Ms. Vatika Goel, Ms. Akriti Vishwas, Ms. Nidhi, Ms. Aditi Rawat, Mr. Kartik Bhardwaj, Mr. Ankit Malik, Dr. Aseem Agarwal, Mr. Priyanshu Arya and Mr. Tejaswi Rai** for their constant companionship, emotional support, and encouragement throughout this period. Without their presence and constant encouragement, the completion of this dissertation would not have been possible in the same spirit and strength with which we carried it forward.*

*The author, Pragya Dobhal, would like to lovingly remember her late grandparents, **Mrs. Anita Tewari and Mr. C. L. Tewari**, whose love, blessings, and values continue to inspire and guide her. Their memories remain a constant source of strength throughout this journey.*

*The author, Umesh Kumar, would like to lovingly remember his late grandfather, **Mr. Hoshiyar Singh**, whose blessings, values, and enduring memories continue to inspire and guide him at every step of this journey. He also expresses his heartfelt gratitude to his grandmother, **Mrs. Sabho Devi**, for her constant love, prayers, and unwavering support, and to his younger brother, **Mr. Deepanshu**, for his affection, encouragement, and companionship throughout this journey.*

*Finally, we express our sincere gratitude to everyone who, directly or indirectly, became a part of this journey and contributed to our growth and learning. This dissertation has not only enriched us academically but has also taught us resilience, patience, and the value of perseverance. We shall always remain thankful for the experiences, lessons, and relationships that became an integral part of this memorable chapter of our lives.*

## **ABSTRACT**

In this study, we report the effect of 2D transition metal dichalcogenides (TMDCs) including SnS<sub>2</sub>, SnSe<sub>2</sub>, their heterostructure (SnS<sub>2</sub>/SnSe<sub>2</sub>), and Polyvinylidene fluoride (PVDF) based composite films for improved performance of piezoelectric nanogenerators (PENG). SnS<sub>2</sub>, SnSe<sub>2</sub> and SnS<sub>2</sub>/SnSe<sub>2</sub> heterostructure were synthesized using hydrothermal method. The TMDC materials were incorporated within a PVDF matrix to create flexible thin films using the solution-casting method to investigate the outcome of TMDCs as nanofillers within the PVDF polymer framework. XRD confirmed the phase purity of SnS<sub>2</sub>, SnSe<sub>2</sub> and their heterostructure, while the Raman spectra verified vibrational modes indicating high crystallinity and interfacial coupling. The enhancement of piezoelectric behavior was revealed by FTIR spectroscopy which shows an increment in the crystallization of  $\beta$ -phase within PVDF, post adding TMDC nanofillers. PVDF/SnS<sub>2</sub>/SnSe<sub>2</sub> heterostructure nanogenerator exhibited the highest value for peak-to-peak open circuit voltage (Voc) of 13.20 V and short circuit current (Isc) of 0.87  $\mu$ A. This increment is linked to the cumulative effect of the formation of a heterointerface, facilitating charge separation, enhanced stress transfer and polarization due to asymmetric charge distribution at the interface. The generated voltage from the PENG device was used to power an LED. This study, thereby gives novel insights into heterostructure engineering for energy harvesting applications.

### **Keywords**

PVDF polymer, piezoelectric nanogenerators, heterostructure nanofillers, 2D SnS<sub>2</sub>/SnSe<sub>2</sub> heterostructure, Energy Harvesting,  $\beta$ - phase enhancement.

# **CONTENTS**

## **CHAPTER-1** **14-30**

### **INTRODUCTION AND OBJECTIVES**

1.1 Introduction

1.2 Objectives

1.3 Literature review

1.3.1 Nanoparticles and Nanotechnology

1.3.2 Nanoparticle synthesis

1.3.2.1 One-step pyrolysis

1.3.2.2 Hydrothermal method

1.3.2.3 Sol-gel method

1.3.3 Energy harvesting

1.3.4 Nanogenerators

1.3.4.1 Piezoelectric nanogenerators

1.3.4.2 Working of PENG

1.3.4.3 Advantages of PENG

1.3.4.4 Limitations of PENG

1.3.5 Polyvinylidene Fluoride

1.3.6 2D materials

1.3.6.1 Tin disulphide ( $\text{SnS}_2$ )

1.3.6.2 Tin diselenide ( $\text{SnSe}_2$ )

1.3.6.3  $\text{SnS}_2/\text{SnSe}_2$  heterostructure

---

## **CHAPTER 2** **31-34**

### **MATERIALS AND METHODS**

2.1 Materials

- 2.2 Synthesis of SnS<sub>2</sub> powder
  - 2.3 Synthesis of SnSe<sub>2</sub> powder
  - 2.4 Synthesis of SnS<sub>2</sub>/SnSe<sub>2</sub> heterostructure powder
  - 2.5 Fabrication of PVDF/TMDC thin films
  - 2.5 Fabrication of PENG devices
- 

## **CHAPTER 3** 35-50

### **CHARACTERISATION AND RESULTS**

- 3.1 Characterization Techniques
  - 3.2 Characterization results
    - 3.2.1 XRD analysis of powders
    - 3.2.2 XRD analysis of films
    - 3.2.3 Raman spectroscopy
    - 3.2.4 Field emission scanning electron microscopy (FESEM)
    - 3.2.5 PE hysteresis loop analysis
    - 3.2.6 FTIR analysis of films
    - 3.2.7 Electrical results analysis
    - 3.2.8 Piezoelectric nanogenerator
- 

## **CHAPTER 4** 51-52

### **CONCLUSION AND FUTURE SCOPE**

- 4.1 Conclusion
  - 4.2 Future Scope
-

## **LIST OF FIGURES**

| <b>Serial No.</b> | <b>Description</b>                                                                                                                                                                                                                         | <b>Page No.</b> |
|-------------------|--------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------|-----------------|
| 1.                | Nanoparticles synthesis techniques                                                                                                                                                                                                         | 17              |
| 2.                | Schematic illustrations for the steps of hydrothermal synthesis of Tin based TMDC powders                                                                                                                                                  | 29              |
| 3.                | Schematic illustration for the steps of film synthesis of TMDC nanofillers incorporated with PVDF using the drop casting method                                                                                                            | 31              |
| 4.                | XRD pattern of synthesised powders                                                                                                                                                                                                         | 33              |
| 5.                | XRD pattern of synthesized films                                                                                                                                                                                                           | 34              |
| 6.                | Raman Spectra of synthesized TMDC powders                                                                                                                                                                                                  | 36              |
| 7.                | FESEM micrographs for (a) PVDF, (b) PVDF/ SnS <sub>2</sub> , (c) PVDF/SnSe <sub>2</sub> , (d) PVDF/SnS <sub>2</sub> /SnSe <sub>2</sub>                                                                                                     | 37              |
| 8.                | PE hysteresis loop                                                                                                                                                                                                                         | 38              |
| 9.                | FTIR spectra of synthesized thin films                                                                                                                                                                                                     | 40              |
| 10.               | FTIR spectra of synthesised SnS <sub>2</sub> /SnSe <sub>2</sub> films incorporated with PVDF at different weight percentage                                                                                                                | 41              |
| 11.               | Open circuit voltage for (a) PVDF, (b) PVDF/SnS <sub>2</sub> , (c) PVDF/SnSe <sub>2</sub> , (d) PVDF/SnS <sub>2</sub> /SnSe <sub>2</sub> thin film nanogenerators at different tapping frequencies                                         | 42              |
| 12.               | Short circuit current for (a) PVDF, (b) PVDF/SnS <sub>2</sub> , (c) PVDF/SnSe <sub>2</sub> and (d) PVDF/SnS <sub>2</sub> /SnSe <sub>2</sub> thin film nanogenerators by tapping at 7 Hz frequency.                                         | 43              |
| 13.               | Schematic of piezoelectric response of PVDF/SnS <sub>2</sub> /SnSe <sub>2</sub> based device with aluminium electrodes: (a) initial dipole orientation, (b) dipole alignment under pressing, and (c) reversed electron flow upon releasing | 45              |
| 14.               | Open-circuit voltage (peak-to-peak) of PENG under applied force from (a). Finger (b). Thumb, (c). Schematic illustration of PENG circuit for operating an LED and (d). LED powered by PENG                                                 | 46              |

## **LIST OF TABLES**

| <b>Serial No.</b> | <b>Description</b>                                                                                           | <b>Page No.</b> |
|-------------------|--------------------------------------------------------------------------------------------------------------|-----------------|
| 1.                | $\beta$ -phase of synthesised films incorporated PVDF/TMDCs                                                  | 39              |
| 2.                | $\beta$ -phase of synthesised SnS <sub>2</sub> /SnSe <sub>2</sub> powder incorporated PVDF (different wt. %) | 40              |
| 3.                | Comparison of piezoelectric output of PVDF and TMDC nanocomposite films                                      | 44              |

## **LIST OF EQUATIONS**

| <b>Serial No.</b> | <b>Description</b>                        | <b>Page No.</b> |
|-------------------|-------------------------------------------|-----------------|
| 1.                | Electro-active $\beta$ -Phase calculation | 39              |

## **LIST OF SYMBOLS AND ABBREVIATIONS**

| <b>Abbreviation</b> | <b>Description</b>                          |
|---------------------|---------------------------------------------|
| 2D                  | Two-dimensional                             |
| PENGs               | Piezoelectric Nanogenerators                |
| PVDF                | Polyvinylidene fluoride                     |
| DI water            | De-ionised water                            |
| DMF                 | Dimethylformamide                           |
| XRD                 | X-ray diffraction                           |
| FESEM               | Field emission scanning electron microscopy |
| FTIR                | Fourier transform infrared                  |
| $V_{OC}$            | Open -circuit voltage                       |
| $I_{SC}$            | Short-circuit current                       |

# **CHAPTER 1**

## **INTRODUCTION AND OBJECTIVES**

### **1.1 Introduction**

The emerging requirements for wearable electronics, self-powered sensors and bio-medical devices has led to an intensified demand for autonomous and sustainable energy technologies [1]. The primitive energy storage systems like batteries and capacitors have limitations like finite operational lifetime, environmental concerns and restricted flexibility. In order to have miniaturized electronic systems, the need of lightweight, portable and maintenance free power sources becomes important. Therefore, in order to meet these requirements, extensive research has been done on harvesting renewable forms of energy including solar, thermal, wind and mechanical energy in order to develop next generation self-sustaining systems [2].

Mechanical energy which is available from environmental vibrations, body movements, acoustic waves and structural deformations has surfaced as one of the most copious and easily available forms of energy. Nanogenerator based technologies have gained wide popularity recently, owing to their capability to convert minimal frequency along with irregular mechanical energy into electrical output. In this domain, piezoelectric nanogenerators (PENGs) have shown potential for energy harvesting because of their simple architecture, high sensitivity and flexibility [3]. These devices operate on the direct

piezoelectric effect, where electrical polarization is generated when a mechanical force is applied on it externally. This effective conversion mechanism allows PENGs to act as an efficient power source for wearable electronics, biomedical devices and self-powered sensing systems [4].

Several piezoelectric materials, inorganic in nature like lead zirconate titanate (PZT), barium titanate ( $\text{BaTiO}_3$ ), zinc oxide (ZnO) and lithium niobate have shown high electromechanical conversion efficiencies [5]. However these materials suffer from brittleness, complex fabrication process, poor flexibility and toxicity due to the presence of lead-based compounds. These limitations inhibit their usage in flexible and wearable electronics where mechanical flexibility and bio-compatibility are essential parameters. Consequently, flexible piezoelectric polymers have come up as more efficient alternatives due to their low density, mechanical flexibility, lightweight structure and environmental stability.

Polyvinylidene Fluoride (PVDF) is a piezoelectric polymer which has garnered significant attention adhering to its piezoelectric, ferroelectric and pyroelectric characteristics. PVDF crystallises in several phases namely the  $\alpha$ ,  $\beta$ ,  $\gamma$  and  $\delta$ -phases [6]. The  $\beta$ -phase among all shows the highest piezoelectric activity owing to its all-trans planar zig-zag (TTTT) molecular configuration, resulting in enhanced dipole alignment and enhanced polarization behaviour. However, the pristine form of PVDF usually crystallizes in the non-polar  $\alpha$ -phase, thereby inhibiting its piezoelectric output performance. [7]. The strategy of incorporating nanofillers within the PVDF polymer matrix has proven to be efficient for the improvement of piezoelectric performance. These nanofillers lead to  $\beta$ -phase nucleation through interfacial interactions, enhanced dielectric properties and improved dipole alignments within the polymer chains.

Owing to their large surface area, excellent electrical properties and enhanced interfacial coupling 2D materials have garnered considerable attention recently. The transition metal dichalcogenides (TMDCs) are generally represented as  $MX_2$ , where X denotes the chalcogen elements and M represents transition metals [8]. These materials have layered structures with special electronic as well as electromechanical properties required for flexible energy harvesting systems.

Tin-based TMDCs like tin disulphide ( $SnS_2$ ) and tin diselenide ( $SnSe_2$ ) have emanate as favourable materials because of their tunable band structures, layered morphology, enhanced surface-to-volume ratio and strong interfacial coupling [9]. Recently, heterostructure formed by combining different two-dimensional materials have also emerged as efficient strategy for improving charge separation, internal electric field generation and polarization behaviour [10]. Heterostructure engineering allows the creation of in-built electrostatic fields at interfaces which can significantly enhance stress transfer mechanisms and dipole interactions within the polymer matrices. Hence as a consequence, integration of  $SnS_2/SnSe_2$  heterostructure into PVDF can potentially provide synergistic enhancement in  $\beta$ -phase formation and piezoelectric output [11].

Taking this forward, our present work shows a systematic investigation of TMDCs such as  $SnS_2$ ,  $SnSe_2$  and its heterostructure ( $SnS_2/SnSe_2$ ) used as nanofillers in integration with PVDF for piezoelectric nanogenerator applications. The choice of these materials especially  $SnS_2$  and  $SnSe_2$  was made due to their intrinsically layered van-der Waals structure, tunable electric properties and proven potential in electromechanical energy conversion systems [12]. This approach provides an efficient pathway towards developing highly efficient and self-powered energy harvesting systems for future wearable and portable electronic technologies.

## 1.2 Objectives

The prime objectives of our current study is to study the influence of transition metal dichalcogenides (TMDCs) like SnS<sub>2</sub>, SnSe<sub>2</sub> and their heterostructure SnS<sub>2</sub>/SnSe<sub>2</sub> as nanofillers within a PVDF matrix for enhanced piezocatalytic energy harvesting applications. By incorporating 2D materials and heterostructure engineering, the parameters like interfacial interactions,  $\beta$ -phase crystallization, polarization behaviour and the electrical response of PVDF based PENG is anticipated to improve. The specific objectives of our present study are listed below:

- (i). Synthesis of SnS<sub>2</sub> and SnSe<sub>2</sub> powder using the hydrothermal method.
- (ii). Synthesis of SnS<sub>2</sub>/SnSe<sub>2</sub> heterostructure powder to investigate hetero-interface formation.
- (iii). Optimization of the concentration of TMDC nanofillers within the PVDF polymer matrix.
- (iv). Fabrication of flexible PVDF/TMDC nanocomposite film with varying weight percentages of nanofillers.
- (v). Studying the effect of SnS<sub>2</sub>, SnSe<sub>2</sub> and SnS<sub>2</sub>/SnSe<sub>2</sub> heterostructure nanofillers on the  $\beta$ -phase nucleation within the PVDF polymer matrix.
- (vi). Analysis and comparison of the piezoelectric response and output of PVDF based PENGs with different nanofillers systems.
- (vii). Evaluating the practical application of the fabricated PENG to power small electronic components and system.

## **1.3 Literature review**

### **1.3.1: Nanotechnology and nanoparticles**

Nanotechnology, being an interdisciplinary field involves the understanding and application of materials and structures at dimensions ranging from 1-100 nm [13]. Within this size regime, materials show different chemical, electrical, optical, physical and mechanical attributes which are significantly distinct from their bulk counterparts. This happens because of quantum confinement effects, enhanced surface to volume ratio and enhanced surface energy. These characteristics arising at the nanoscale level has caused the development of advanced materials with tuneable functionalities resulting in extensive applications across electronics, energy system, medicines, environmental science and material engineering.

This concept has evolved rapidly over the past few years and is currently among one of the most transformative scientific and technological fields. Due to its capability to design and engineer materials at atomic and molecular levels, nanotechnology has contributed significantly in several sectors including semiconductor industries, biomedical engineering, communication systems, sensors and renewable energy technologies. Particularly, the emergence of nanomaterials has opened new domains in the development of lightweight, flexible and strong performance electronic devices [14]. This field has also played a vital role in addressing obstacles associated with sustainable energy production, environmental and healthcare applications.

Nanoparticles are materials having dimensions in the nanoscale range and they exhibit remarkable physical and chemical properties due to their reduced dimensions. Nanoparticles exist in various forms based on their morphology including zero

dimensional, one dimensional nanoparticles and nanotubes, two dimensional nanosheets and three dimensional nanostructured architectures [15]. Their unique behaviour is because of high surface area and enhanced interfacial activity which leads to superior optical absorption, catalytic performance, charge transfer characteristics and mechanical strength.

Nanoparticles can be categorized into metallic, metal oxide and polymeric nanoparticles along with carbon based nanostructures and semiconductor based nanomaterials. 2D materials in the recent years have gotten considerable research attention because of their atomically thin layered structures and remarkable electromechanical properties. Several materials like graphene, TMDCs and MXenes have shown exceptional performance in applications involving sensing, energy storage and energy harvesting systems [15]. Due to their layered structure effective charge transport and strong interfacial interactions occur, making them highly suitable for incorporation within the polymer matrices.

The physiochemical properties of nanoparticles depend on their size, shape, crystallinity and synthesis method. Therefore, controlled synthesis of nanoparticles is essential for controlling their functional properties for various applications. Synthesis routes including-hydrothermal synthesis, chemical vapour deposition, exfoliation, sol-gel processing and pyrolysis method are used to obtain nanostructures with desired morphology and structural characteristics [16]. These techniques allow strict control over particle dimensions, crystal structure and surface chemistry, therefore playing a significant role in device performance.

In piezoelectric applications, nanoparticles have gained exponential importance due to their ability to enhance dielectric behaviour, dipole alignment and improved electrochemical coupling within the polymer matrix. This method of incorporation of nanofillers within piezoelectric polymers has proven to be effective for improving  $\beta$ -phase nucleation and piezoelectric response. In particular, layered nanomaterials which have a high surface area

and strong interfacial interactions have shown considerable improvement in the performance of piezoelectric nanogenerators. Therefore, the inclusion of nanotechnology and advanced nanoparticles has become an important strategy for developing efficient and flexible self-powered systems.

### 1.3.2: Nanoparticle synthesis techniques

Nanoparticles can be synthesized by different techniques. These methods can be used to create dry particles as well as nanoparticles, which can be distributed in a liquid or gaseous media. Nanostructures can be produced by beginning with atoms or by shrinking micro particles to nanoparticle size.

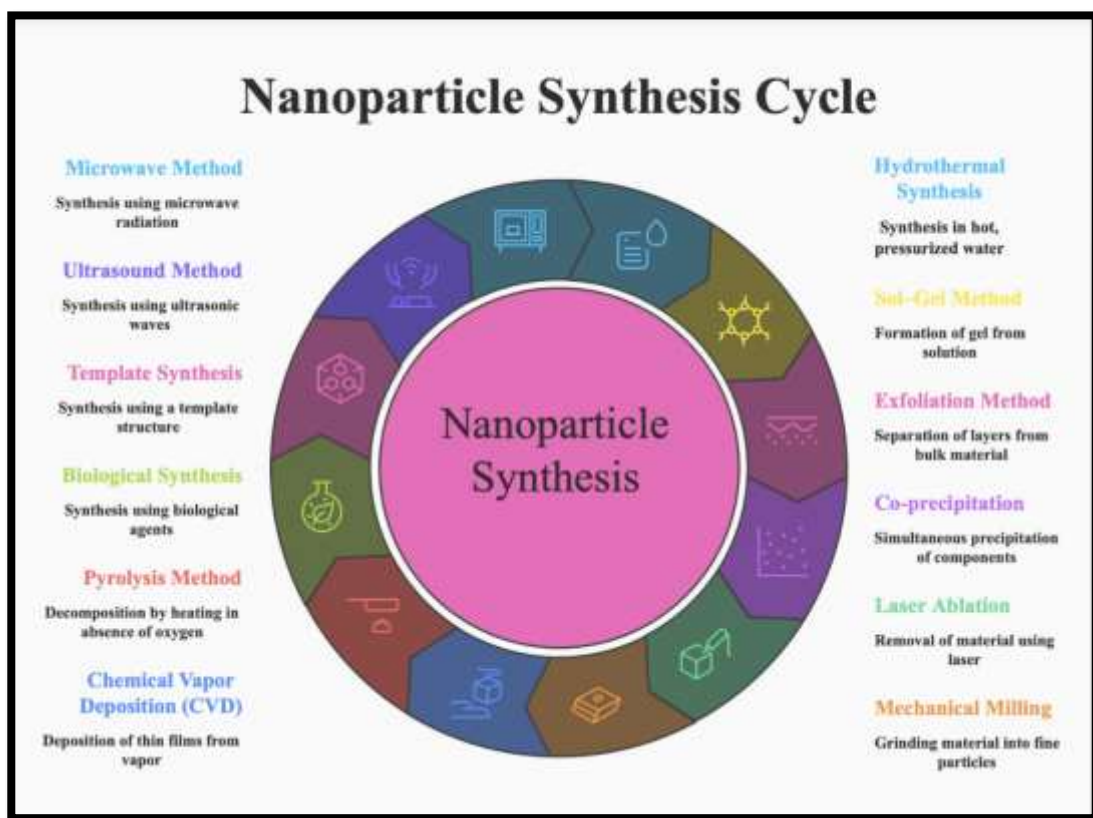


Fig.1: Nanoparticles synthesis techniques.

### **1.3.2.1 One-Step Pyrolysis Process**

One step pyrolysis is a thermal decomposition method conducted in an inert environment, commonly used for the synthesis of nanomaterials. In this technique, a precursor material is subjected to high temperatures to decompose into smaller, stable nanostructures. The process is straightforward and it is also one of the processes which is less complex and less time consuming for material synthesis. The precursor such as urea is placed in the muffle furnace at 600° C – 700° C for around 3hrs and then the sample is cooled and a powder form of the nanomaterial is obtained in the process [17].

The readily available precursors makes process economically viable, also the parameters like temperature, heating rate and precursor concentration can be tuned to achieve desired sizes and shapes of the material which is very important aspect keeping in mind the importance of particle size in the nanomaterial synthesis. It is a highly efficient and versatile technique for nanomaterial synthesis. Although it causes high energy costs and precision control but these factors can be optimized going forward.

### **1.3.2.2 Hydrothermal Process**

The hydrothermal route is widely used to produce solids such as fluorides, ceramics, complex oxides, microporous crystals, and superionic conducting materials. Magnetic materials and luminescence phosphors are also produced with the help of it. Novel condensed materials, such as stacking sequence material, are also accessible through it. Additionally, the synthesis of thin films, helical and chiral structures, and nanoscale particles is made possible.

"Hydrothermal synthesis" refers to the method of generating compounds by chemical reactions in a heated, sealed solution that is heated above ambient temperature and press [18].

### **1.3.2.3 Sol-gel process**

One method used to create solid materials using tiny molecules is the sol-gel process. The sol (or solution) changes during this chemical process, becoming a biphasic system that resembles a gel. There are two phases to this system: a liquid phase and a solid phase. The liquid phase can have various morphologies, such as single particles or networks of linked polymers. Finely ground and homogenous ceramic powders can be produced via precipitation. These single- and multi-component powders at the nanoscale are produced for use in dentistry and biomedicine [19].

### **1.3.3 Energy harvesting**

With the increase in global demand for sustainable energy and its technologies has led to heightened research towards alternate energy solutions. Conventional sources suffer from limitations like finite operational life, maintenance requirement and environmental concerns. Therefore, energy harvesting has surfaced as a potential approach to convert naturally available mechanical energy into electrical output for driving small scale electronic systems.

The term energy harvesting refers to the process of converting energy by capturing it from surrounding sources like solar radiation, thermal gradient, wind, electromagnetic waves and mechanical vibrations into electrical energy. Among all these sources, mechanical energy is considered as readily available and accessible due to its widespread occurrence in human activities, industrial systems and environmental motion. Activities like body movements, vibrations, pressure fluctuations and acoustic waves generate mechanical energy that can be used for electrical power generation.

Several mechanisms have been developed for converting mechanical energy including electromagnetic, electrostatic, triboelectric and piezoelectric approaches. However,

piezoelectric and triboelectric nanogenerators have garnered attention because of their simple device structure, flexibility and sensitivity. These systems possess advantages like lightweight structure, low fabrication cost and compatibility with substrates that makes them relevant for wearable and self-powered electronics[20] .

Due to the rapid advances in nanotechnology and material engineering, the energy harvesting efficiency has improved considerably by incorporating nanomaterials and functional composites. These developments have led to an expansion of energy harvesting systems in various domains.

### **1.3.4 Nanogenerators**

Nanogenerators are energy harvesting devices which convert mechanical, thermal and vibrational energy into electrical energy at nanoscale. In recent times, these devices have gained significant popularity owing to their applications in self-powered electronics and wireless sensor based systems. They are classified into piezoelectric nanogenerator (PENG) and triboelectric nanogenerator (TENG) based on their operating mechanisms.

#### **1.3.4.1 Piezoelectric nanogenerators**

Piezoelectric nanogenerators are self-powered electronic devices which convert energy produced from mechanical vibrations into an electrical output by utilizing the direct piezoelectric effect [21]. They were discovered by Zhong Lin Wang in 2006, post which they have gotten significant recognition because of their capability to convert low frequency mechanical energy from sources like environmental vibrations, human activities and pressure fluctuations. The growth of high performance piezoelectric nanogenerators has become essential due to the increasing demand for self-powered electronic systems and wearable technologies.

The working of PENG is based on the generation of electric polarization within piezoelectric materials under mechanical stress. The internal dipoles of the piezoelectric materials gets aligned under applied pressure leading to the separation of charges which creates an electric potential across the surface of the material. When the applied force is released, reverse polarization occurs, thereby producing an alternative electrical output. This periodic cycle of deformation and relaxation generates a periodic electrical signal.

Several materials including inorganic ceramics and polymer based piezoelectric materials have been used for PENG fabrication. PVDF and its nanocomposites have gained wide importance because of their flexibility, lightweight nature and ease of fabrication. Due to these advantages, PENGs have shown potential for applications in several domains like self-powered sensing technologies and wearable electronics.

#### **1.3.4.2 Working principle of PENGs**

Piezoelectric nanogenerators operate on the direct piezoelectric effect which converts energy produced from mechanical vibrations into electrical energy via stress induced polarization [22]. On applying an external mechanical force on the piezoelectric layer, deformation occurs in the crystal structure, therefore causing displacement of charge carriers and generating a dipole moment.

Under initial equilibrium conditions and the absence of external mechanical stress, the charges are uniformly distributed and no potential difference exists across the material. When a mechanical force is applied, polarization is induced due to dipole alignment and charge accumulation happens on the opposite electrode surfaces. This creates a potential difference which carries electrons through an external circuit producing an electrical output. However, when the applied stress is removed, the material comes back to its initial

state, hence leading to depolarization and reversal of charge flow. This conversion mechanism forms the basis of PENGs operation.

#### **1.3.4.3 Advantages of PENGs**

Piezoelectric nanogenerators have gained attention because of their ability to efficiently harvest energy from mechanical vibrations and convert it into a usable electrical output. Their primary advantage is their capability to produce electrical output from low frequency mechanical stimuli like body movements, vibrations and pressure variations. PENGs also possess lightweight and flexible structures thus making them highly relevant for amalgamation into wearable and portable electronic devices [23].

PENGs also possess a simple device architecture and has a cost effective fabrication method. They can operate without any source of external power, therefore reducing maintenance requirements and environmental concerns. They are also compatible with flexible polymers and the usage of nanomaterials makes it even more durable and efficient. Therefore, owing to these characteristics, PENGs show capability for applications in self-powered sensors, biomedical devices, electronic skin as well as wireless monitoring systems.

#### **1.3.4.4 Disadvantages of PENGs**

In spite of having substantial potential in energy harvesting applications, PENGs have limitations which can restrict their mainstream implementation. One of the major issues with PENG is that they have a relatively low electrical output especially current generation which hinders their applications in powering high energy electronic systems.

Another limitation includes the high internal impedance of PENGs devices which can cause complications in efficient energy transfer and integration with external electronic circuit. Apart from this, its output performance depends heavily on the frequency and magnitude of the external force. Inconsistent inputs and environmental variations can impact device efficiency. Therefore, addressing these limitations is essential for improving the practical applicability of PENGs in future self-powered systems [24].

### **1.3.5 Polyvinylidene Fluoride (PVDF)**

PVDF is a high performance synthetic and flexible polymer credited due to its chemical resistance, electric and piezoelectric properties and a unique electro active behaviour. It is used in chemical processing and energy storage devices due to its durability and flexibility. This polymer has a semi-crystalline nature and is also highly fluorinated which makes it stable against acids, bases and corrosive chemicals. It is thermally stable, has high mechanical strength, is UV resistant and non-toxic. [25]

PVDF consists of 5 crystalline phases namely- alpha, beta, gamma, delta and epsilon. The alpha phase is the most stable and ground state phase which is non polar in nature hence it does not exhibit piezo or ferro electric properties. The beta phase is a polymorphic phase found at high temperatures. It consists of an all Trans planar zig zag (TTTT) chain configuration. In this, all dipole moments are unidirectional, therefore creating a spontaneous polarization due to which it shows piezoelectric properties. The gamma phase is a high symmetry phase in polymers and is found under high temperature and unique processing conditions. The delta phase is less stable than others and is usually formed at a high temperature and pressure. The epsilon phase being the least common one of them all is found in extremely rare conditions, for example the iron in earth's core.

### 1.3.6 Two-dimensional materials

Two-dimensional (2D) layered non-centrosymmetric materials hold significant potential for electronic devices and nanoscale electromechanical systems. Recent research has increasingly focused on atomically thin two-dimensional materials due to their extraordinary and unconventional mechanical, optical, magnetic, and electrical capabilities. In 2D transition metal dichalcogenides (TMDCs), the interlayer MX bonds are pivotal, unlike the sandwiched layers that are maintained by weak van der Waals forces, allowing for facile cleavage at the layer surface. These TMDCs are predominantly covalent compounds, commonly represented as  $\text{MX}_2$ , where M represents a transition metal and X corresponds to a chalcogen atom. This has enabled the production of crystals with very tiny dimensions. Owing to their distinctive features such as flexibility, optical transparency, mechanical stability, and biocompatibility two dimensional materials are well suited for a wide range of advanced application. 2D materials are optimal for constructing energy harvesters such as PENGs. These materials include graphene, TMDCs, h-BN, MXenes. 2D materials have properties like high surface area, tunable bandgap, flexibility, optical transparency, high thermal conductivity. 2D materials find their applications in electronics, energy storage, optoelectronics, sensors, and in biomedical applications [26].

#### 1.3.6.1 Tin disulfide ( $\text{SnS}_2$ )

Tin disulphide ( $\text{SnS}_2$ ) is a layered semiconductor and a transition metal dichalcogenide (TMDC) which has unique structural and electronic properties.  $\text{SnS}_2$  has a hexagonal crystal structure, where a tin atomic layer is inserted between sulphur layers having van der Waals interactions. This layered architecture offers the possibility of the formation of ultrathin nanosheets with a high surface area and better interfacial properties, which makes  $\text{SnS}_2$  a promising material for electronic, sensing and energy harvesting applications [27].

SnS<sub>2</sub> possesses many favourable properties such as appropriate band gap, high carrier mobility, environmental stability and strong electromechanical coupling behavior. In addition, the high surface-to-volume ratio is beneficial for efficient stress transfer and enhancement of interfacial interactions with polymer matrices. Recently, SnS<sub>2</sub> has been reported to be an efficient nanofiller to improve the electroactive  $\beta$ -phase of PVDF via dipole interaction and nucleation effects. Incorporating SnS<sub>2</sub> into polymer systems enhances charge polarization and dielectric properties, resulting in improved electrical output performance of piezoelectric nanogenerators.

In the present work, SnS<sub>2</sub> has been selected as one of the TMDC nanofillers for incorporation into the PVDF matrix owing to its layered morphology and capability to facilitate  $\beta$ -phase enhancement. Also, its individual role and as part of the SnS<sub>2</sub>/SnSe<sub>2</sub> heterostructure system is investigated to improve piezoelectric energy harvesting performance

#### **1.3.6.2 Tin diselenide (SnSe<sub>2</sub>)**

Tin diselenide (SnSe<sub>2</sub>) is a layered two-dimensional transition metal dichalcogenide (TMDC) that has gained considerable attention owing to its attractive electronic, optical and structural properties. SnSe<sub>2</sub> crystallizes in a hexagonal CdI<sub>2</sub>-type layered structure, in which a tin atomic layer is sandwiched by two selenium layers and the layers adjacent to it are held together by weak van der Waals forces. This kind of structure allows the production of ultrathin nanosheets with high surface area and adjustable physicochemical properties for advanced functional applications [28].

SnSe<sub>2</sub> is a narrow band gap material with high electrical conductivity, excellent charge transport properties and good environmental stability, which makes it an attractive material for energy storage, optoelectronic and sensing applications. The ionic radii of selenium-

based compounds and their lattice polarizability are higher compared to those of sulfur-based TMDCs and can have a considerable effect on dielectric response and charge distribution. These properties are advantageous to enhance interfacial polarization and stress transfer when incorporated into polymer matrices.

SnSe<sub>2</sub> has been promising as a nanofiller for piezoelectric nanogenerator application through the facilitation of dipole arrangement and the enhancement of  $\beta$ -phase formation in PVDF matrices. In this work, SnSe<sub>2</sub> has been incorporated individually and as a constituent of the SnS<sub>2</sub>/SnSe<sub>2</sub> heterostructure to study its effect on polarization behavior and piezoelectric output enhancement.

#### **1.3.6.3 SnSe<sub>2</sub>/SnSe<sub>2</sub> heterostructure**

A competent method to tune the electrical, optical and electromechanical characteristics of two-dimensional materials has been developed as heterostructure engineering. A heterostructure is created by integrating two or more layered materials possessing different electronic characteristics, thereby creating an interface capable of modifying charge transport and polarization behavior. In two-dimensional systems heterostructures are constrained by van der Waals interaction without requiring strict lattice matching conditions and thus allow the formation of interfaces with unique functional properties [29].

The SnS<sub>2</sub>/SnSe<sub>2</sub> heterostructure offers the combined benefits of both sulfur- and selenium-based transition metal dichalcogenides (TMDCs). SnS<sub>2</sub> and SnSe<sub>2</sub> have similar crystal structures and small lattice mismatch, which can build up stable interface with strong interfacial coupling and efficient charge redistribution. The formation of a heterointerface gives rise to an internal electric field due to band offset differences and charge equilibration at the interface. This internal electric field assists in separating the charges and increasing the polarization.

In the case of piezoelectric applications, the heterostructure formation can be a significant improvement for the stress transfer mechanism and dipole interactions in the polymer matrices. In the present work, SnS<sub>2</sub>/SnSe<sub>2</sub> heterostructure was incorporated in PVDF as nanofillers to utilize the synergetic effects due to the interfacial interactions. Improved charge transfer and polarization behaviour are expected to enhance the  $\beta$ -phase nucleation and the electrical response of fabricated piezoelectric nanogenerator

## **CHAPTER 2**

### **MATERIALS AND METHODS**

#### **2.1 Materials**

Tin (IV) chloride penta-hydrate, Thio-Urea, Selenium dioxide and PVDF were bought from Sigma Aldrich. The solvents - Ethylene glycol and N,N-dimethyl formamide (DMF) were procured from Thermo Fisher and were used as received.

#### **2.2 Synthesis of SnS<sub>2</sub> powder**

Tin (II) Sulfide was synthesized in its powder form using hydro-thermal method. Tin (IV) chloride penta-hydrate (3.47 mmol) and Thio-Urea (4.97 mmol) were used as the precursor reagents and were mixed in 40 mL of de-ionized water. The solution was then stirred magnetically for 45 minutes at room temperature. It was then transferred into a Teflon container and sealed into a stainless-steel autoclave. The solution was then heated in the hot air oven at 200 °C for 24 hours. Post this, the sample was washed twice with de-ionized water and ethanol and centrifuged for 6 minutes at 5500 rpm. It was then left to dry in a vacuum oven overnight at 80 °C. Yellowish- brown particles of SnS<sub>2</sub> powder were obtained and were grinded into a fine powder using a mortar- pestle [30].

### 2.3 Synthesis of SnSe<sub>2</sub> powder

A simple hydrothermal route was used to synthesize SnSe<sub>2</sub> powder [31]. Tin (IV) chloride penta-hydrate (1.50 mmol) was added into 30 mL of de-ionized water and was labeled as solution 'A'. Selenium dioxide (1.50 mmol) was added into 10 mL of di-water and was labeled as solution 'B'. Both 'A' and 'B' were mixed and stirred for 20 minutes. Then 3 mL of hydrazine-hydrate was added into the solution and it was magnetically stirred for 20 minutes at room temperature. It was then transferred into a teflon container and sealed into a stainless-steel autoclave. The solution was then heated in the hot air oven at 200 °C for 24 hours. Post this, the sample was washed twice with de-ionized water and ethanol and centrifuged for 6 minutes at 5500 rpm. It was then left to dry in a vacuum oven overnight at 80 °C. Black particles of SnSe<sub>2</sub> were obtained and were grinded into a fine powder using a mortar- pestle




**Fig. 2: Schematic illustrations for the steps of hydrothermal synthesis of Tin based TMDC powders.**

## **2.4 Synthesis of SnS<sub>2</sub>/SnSe<sub>2</sub> heterostructure powder**

The following synthesis was done using the hydrothermal method. Tin (IV) chloride pentahydrate (5.42 mmol) and Selenium dioxide (11.1 mmol) were taken and mixed into 40 mL of ethylene glycol solution. The solution was stirred magnetically for 45 minutes. After which 3 mL of Hydrazine hydrate was added into it drop-by-drop and the mixture was stirred for 30 minutes at 70 °C. The solution was then heated in the hot air oven at 180 °C for 36 hours. Post this, the sample was washed thrice with de-ionized water and ethanol and centrifuged for 10 minutes at 5500 rpm. It was then left to dry in a vacuum oven for 12 hours at 80 °C. A black powder was obtained and was grinded using a mortar- pestle for 15 minutes [32].

## **2.5 Synthesis Methodology of TMDCs/PVDF films**

The synthesized powders were then integrated with a flexible and piezo electric polymer PVDF to synthesize thin films. For the synthesis of films 1g PVDF was dissolved in 10 mL DMF and was stirred magnetically for 3 hours. Then the respective powders were added at a weight percentage into the previously prepared solution and were stirred again for 2 hours. Post which, the solution was ultrasonicated for 30 minutes and was stirred again for 30 minutes. Then the final prepared solution was casted onto glass slides using a pipette and was left for drying in the oven at 60 °C for 12-15 hours. Then the films were retrieved from the oven and cleaned with DI water and stored in vacuum [33].

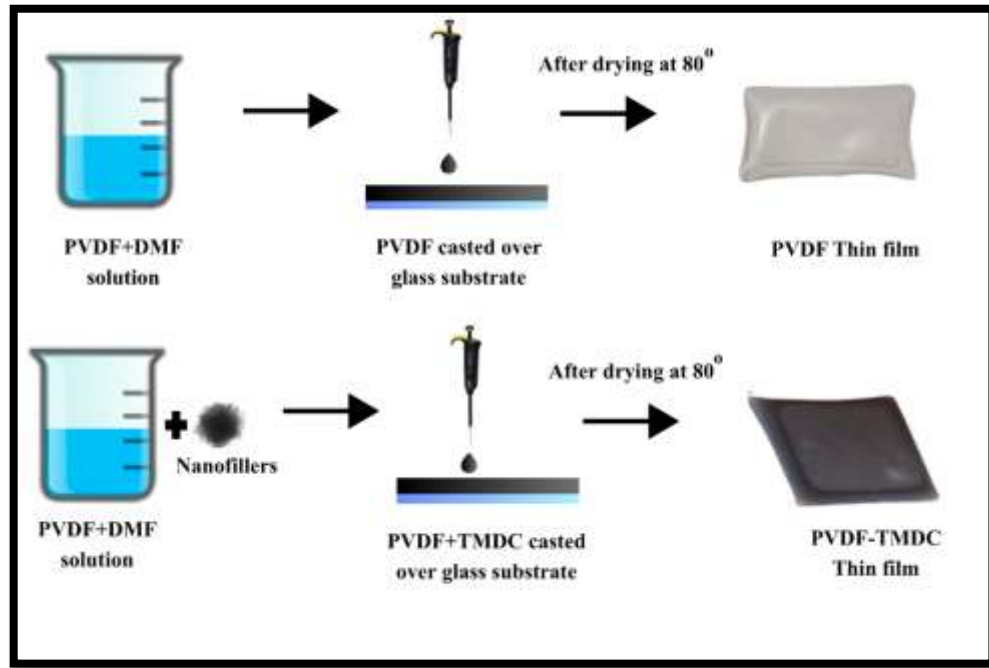

**Fig. 3: Schematic illustration for the steps of film synthesis of TMDC nanofillers incorporated with PVDF using the drop casting method.**

## **2.6 Fabrication of Piezoelectric Nanogenerator**

For device fabrication, initially the synthesized films were cut down to their requisite size. This film was kept between aluminum tapes serving as electrodes for the PENG. Following this, the aluminum electrodes were connected to thin strips of copper tapes from both sides and were soldered to ensure the connection between PENG and the measurement device. The device was then sheathed with kapton tape. These fabricated devices were rectangular in shapes having dimensions of 2x3 cm<sup>2</sup>.

## **CHAPTER 3**

### **RESULTS AND DISCUSSIONS**

#### **3.1 Characterization Techniques**

XRD analysis was performed on synthesized powder samples in which the peak confirmed the correct formation of the powder using X-ray diffractometer Cu X-ray source, 3 kW (JEOL Japan model: JSM 6610LV). Fourier transform infrared (FTIR) spectra was done in order to check the content of electro active beta phase using the Perkin Elmer Spectrum II device. It confirmed the presence of the crystallization of the electro active  $\beta$ -phase in the synthesized thin films. Raman spectroscopy was also done using the Horiba Jobin-Yvon LABRAM-HR spectrometer in order to check the vibrational phases of the material. Field emission scanning electron microscopy (FESEM) confirmed the morphology of the surface and microstructural information of the films. A PE loop tracker was used to obtain the PE hysteresis analysis of thin films. Voltage ( $V_{OC}$ ) and Current ( $I_{OC}$ ) measurements were done in order to check the open loop current and voltage values of the device using the digital storage oscilloscope (Tektronix, MD0500) and a digital multimeter (Keithly DMM6500).

## 3.2 Characterization Results

### 3.2.1 XRD of powders

XRD analysis for the powders is given in Fig. 4. The JCPDS card no for  $\text{SnS}_2$  is **00-023-0677** the JCPDS card No. for  $\text{SnSe}_2$  is **00-023-0602**. The peaks were observed for  $\text{SnS}_2$  at 15.20 , 28.55, 32.29, 42.12, 50.24, 52.66, 55.22, 60.95, 67.43 at corresponding planes (001), (100), (002), (003), (110), (111), (200), (100), (004) . For  $\text{SnSe}_2$  the peaks were noticed at 14.59, 30.95, 40.31, 47.91, 50.28, 52.76, 57.99, 60.53, 64.17 and 67.31 at corresponding planes (001), (011), (012), (110), (111), (103), (201), (004), (202) and (113). XRD pattern confirmed the coexistence of  $\text{SnS}_2$  and  $\text{SnSe}_2$  phases in the heterostructure implying successful formation of the heterostructure.


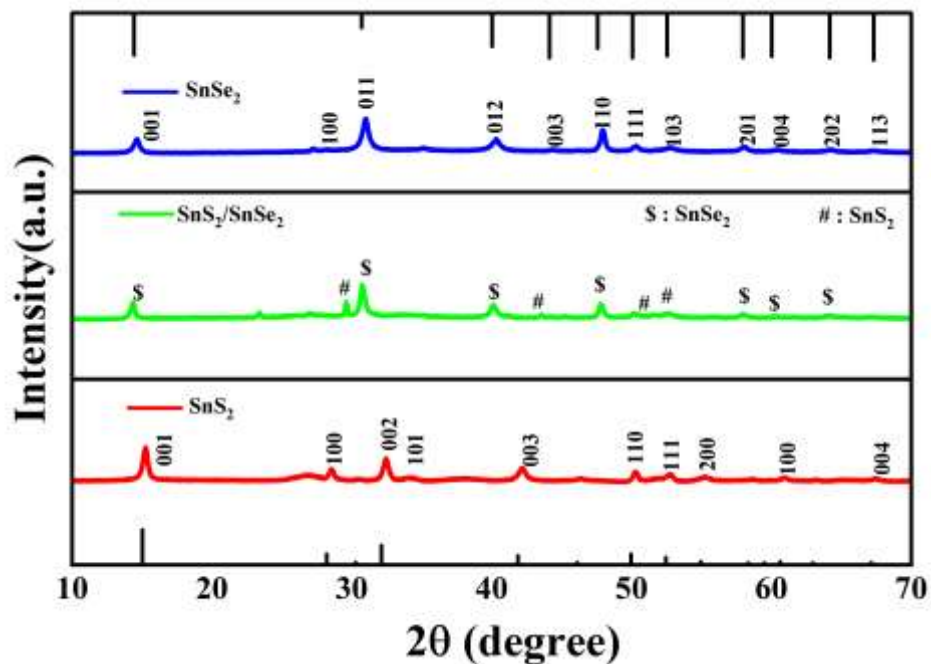


Fig. 4: XRD results of synthesised powders.

### 3.2.2 XRD of films


For bare PVDF and PVDF/TMDCs thin films, the XRD results is shown in the Fig. 5. The peak for the non-polar  $\alpha$  phase is detected at 18.4 degree and for the polar  $\beta$  phase is detected at 20.2 degree. The XRD analysis, as shown in Fig.5 \* represents the diffraction peaks with respect to PVDF, the peaks for  $\text{SnS}_2$  and  $\text{SnSe}_2$  are represented by # and \$ respectively. This data shows the co-existence of TMDC materials and the  $\beta$  phase in the synthesized composite films. It shows that the electro-active  $\beta$  phase crystallizes in bare PVDF as well.

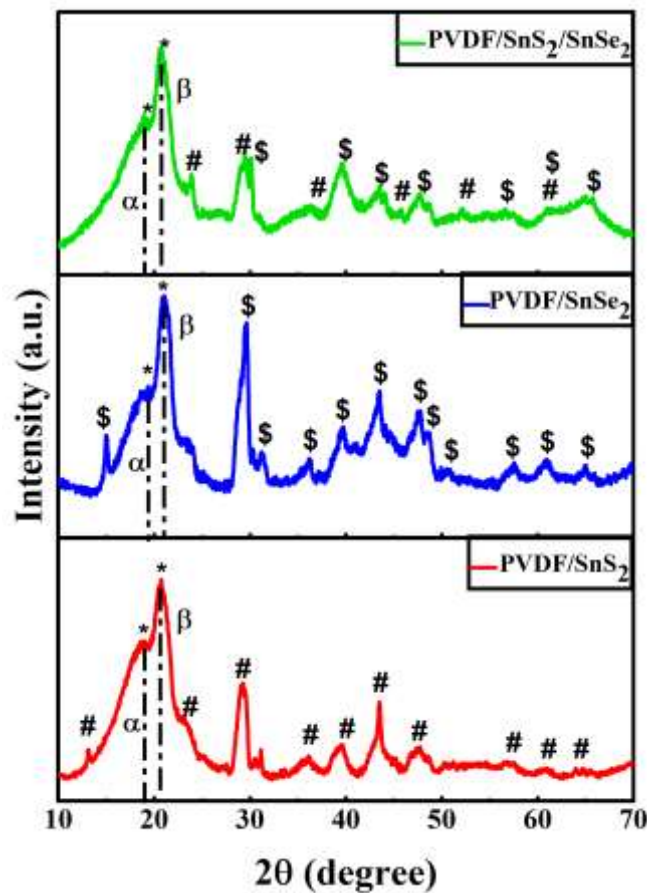

**Fig. 5: XRD results of synthesized films.**

### 3.2.3 Raman spectroscopy


The Raman spectral analysis of synthesized powders is shown in the Fig. 6. Two Raman active peaks were observed namely  $E_{2g}^1$  and  $A_{1g}$ . The  $E_{2g}^1$  mode in the spectra is due to the in-plane vibrations between the atoms whereas the  $A_{1g}$  mode is present because of the out-of-plane vibrations. For  $SnS_2$ , they were observed at  $202.86\text{ cm}^{-1}$  and  $311.83\text{ cm}^{-1}$  respectively. We know that, the  $E_{2g}^1$  mode in  $SnS_2$  is due to the vibration of two S atoms with respect to the Sn atom in the opposite direction [34]. The  $A_{1g}$  mode shows the out of plane vibrations of Sn-S along the c axis. For  $SnSe_2$ , they were detected at  $179.17\text{ cm}^{-1}$  and  $230.93\text{ cm}^{-1}$  respectively. The peaks for heterostructure were observed at  $182.31\text{ cm}^{-1}$  and  $291.59\text{ cm}^{-1}$  which matched with literature values. In our composite material, the major Raman peaks do not overlap onto the individual characteristic peaks of  $SnS_2$  and  $SnSe_2$ , thus confirming the synthesis of a uniformly distributed heterostructure.

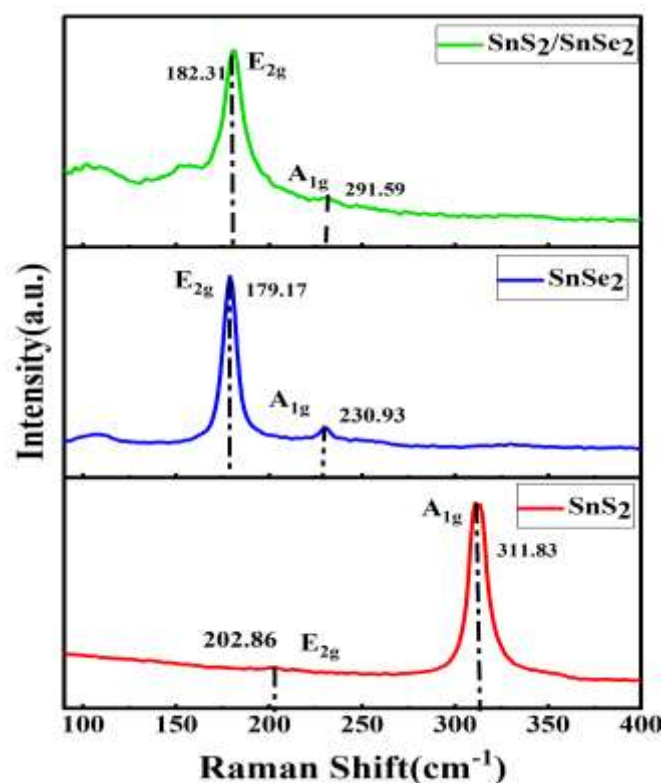

**Fig. 6: Raman Spectra of synthesized TMDC powders.**

### 3.2.4 FESEM of films

The FESEM (Field emission scanning electron microscopy) morphological analysis was done in order to study the surface morphology of the PVDF/TMDC thin films. The FESEM images as shown in Fig.7, depict the uniformity of the PVDF matrix. From the images, it can be seen that the distribution of SnS<sub>2</sub>, SnSe<sub>2</sub> and SnS<sub>2</sub> /SnSe<sub>2</sub> is ubiquitous over the PVDF polymer matrix without any signs of agglomeration which implies the effective dispersion of the nanofillers in the PVDF matrix.

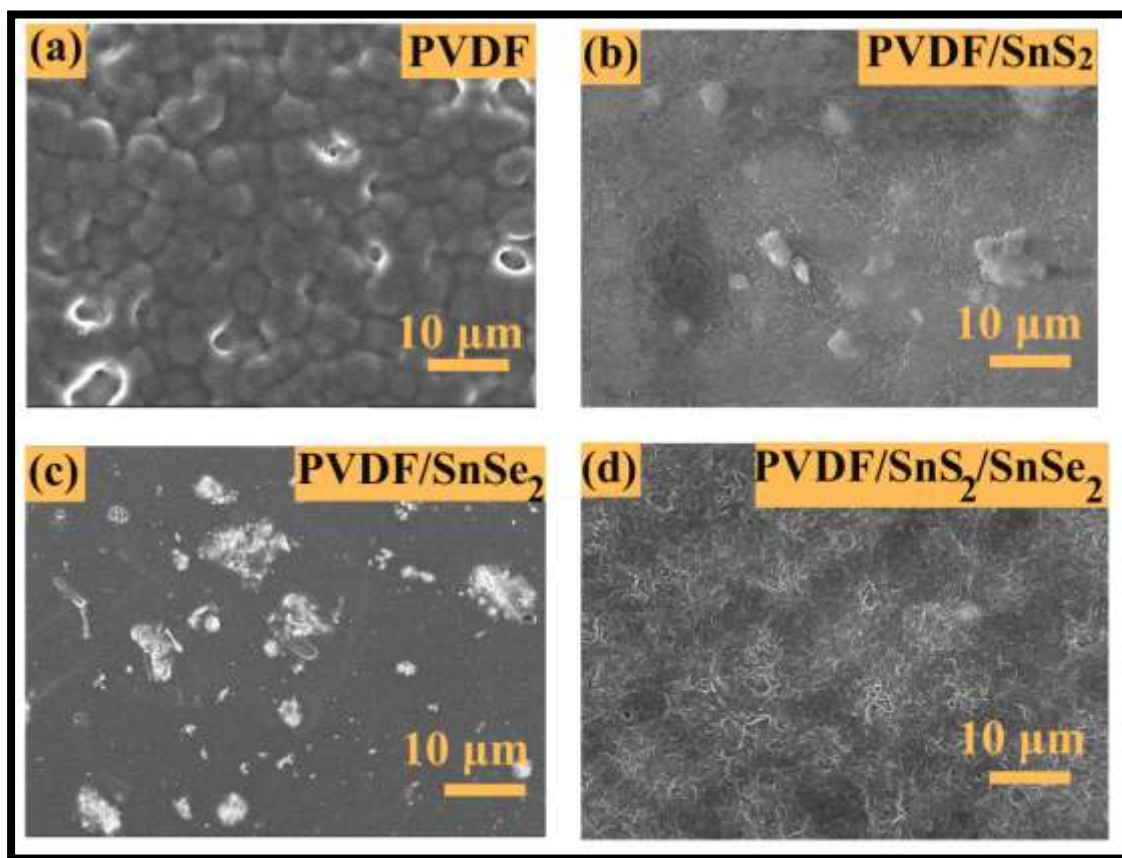


**Fig. 7 : FESEM micrographs for (a) PVDF, (b) PVDF/ SnS<sub>2</sub>, (c) PVDF/SnSe<sub>2</sub>, (d) PVDF/SnS<sub>2</sub>/SnSe<sub>2</sub>.**

### **3.2.5 PE hysteresis loop of films**

To compute the piezoelectric retentivity of thin films, the PE hysteresis study was done and in order to elaborate on their intrinsic dipole behaviour, which is directly linked to their piezoelectric performance as shown in Fig. 8. This study of hysteresis loop shows the clear presence of how polarization switches under an applied electric field, thereby confirming the presence of non centro-symmetric polarization domains in these PVDF enhanced layered dichalcogenides systems. The  $P_r$  values of PVDF, PVDF/SnS<sub>2</sub>, PVDF/SnSe<sub>2</sub>, PVDF/SnS<sub>2</sub>/SnSe<sub>2</sub> are evaluated from the PE loop and are  $6.13 \times 10^{-2}$ ,  $7.49 \times 10^{-2}$ ,  $7.58 \times 10^{-2}$  and  $8.78 \times 10^{-2} \mu\text{F cm}^{-2}$  respectively. This enhanced behavior of remanent polarization

is directly linked to the generation of an enhanced piezoelectric potential under mechanical perturbation which leads to efficient charge separation and migration.

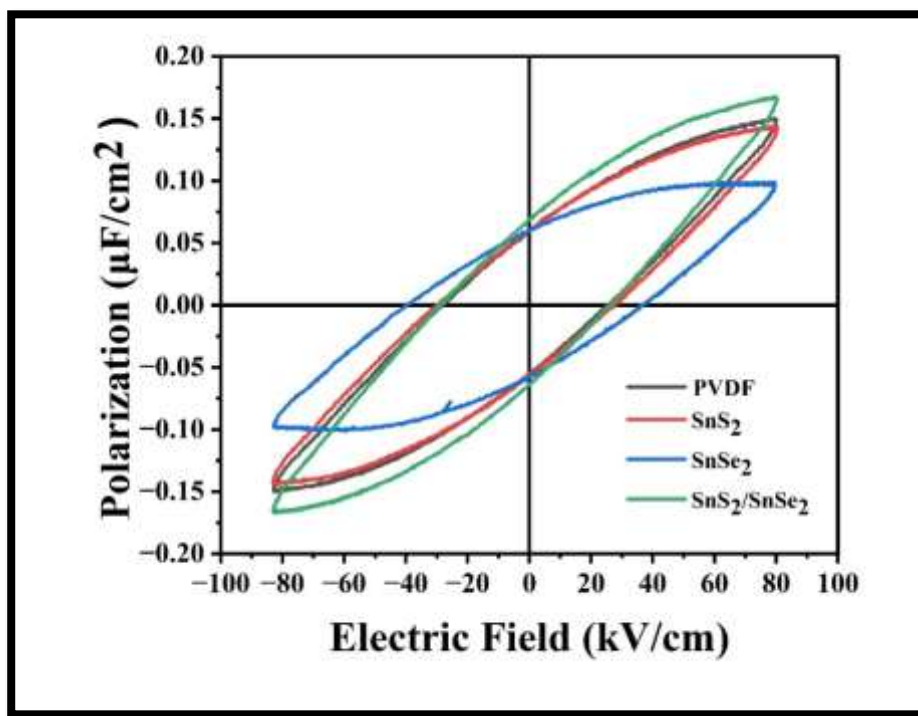

**Fig. 8: PE hysteresis loop.**

### 3.2.6 FTIR Spectroscopy of films

FTIR spectroscopy was carried out to analyze the phase transformation and to investigate the phases present in the PVDF-TMDC films synthesized at 3 wt. percentage. In the Fig.9, the beta phase is evaluated from the vibrational bands at  $840\text{ cm}^{-1}$  and the  $\alpha$ -phase from the vibrational band at  $762\text{ cm}^{-1}$ . These bands correspond to the unique bending and stretching modes related to the polar crystalline conformation of PVDF polymer matrix. The peaks in the Fig. 9 marked the presence of the beta phase, which is inherently piezoelectric and

inferred that by the inclusion of TMDC materials, it gets enhanced. The beta phase was calculated by using Lambert's Beers' law using the equation [35]–

$$F(\beta) = \frac{A_{\beta}}{\left(\frac{K_{\beta}}{K_{\alpha}}\right)A_{\alpha} + A_{\beta}} \quad \text{----- (1)}$$

Where  $K(\beta) = 7.7 \times 10^4 \text{ cm}^2/\text{mol}$  and  $K(\alpha) = 6.1 \times 10^4 \text{ cm}^2/\text{mol}$  and these are coefficients of absorption at  $840 \text{ cm}^{-1}$  and  $762 \text{ cm}^{-1}$  respectively. For bare PVDF, the beta phase was evaluated to be 61 % and for 3 wt. %  $\text{SnS}_2$ ,  $\text{SnSe}_2$  and heterostructure  $\text{SnS}_2/\text{SnSe}_2$  enhanced with PVDF, the  $\beta$  phase was given by 72 %, 70% and 76% respectively. Since  $\text{SnS}_2/\text{SnSe}_2$  exhibited the maximum value of electro active beta phase, its films with PVDF at varying weight percentages (1%, 3%, 5% and 7%) were prepared and the highest value was observed at 3%. The following table shows a clear increase in the beta phase from 0 to 3 wt. % and then a decrease on further increasing the weight due to agglomeration. We calculated  $\beta$  phase was as follows for different materials–

**Table 01:  $\beta$ -Phase of synthesised films incorporated PVDF/TMDCs.**

| Material                     | Electro active Beta phase |
|------------------------------|---------------------------|
| PVDF                         | 61%                       |
| $\text{SnS}_2$               | 72%                       |
| $\text{SnSe}_2$              | 70%                       |
| $\text{SnS}_2/\text{SnSe}_2$ | 76%                       |


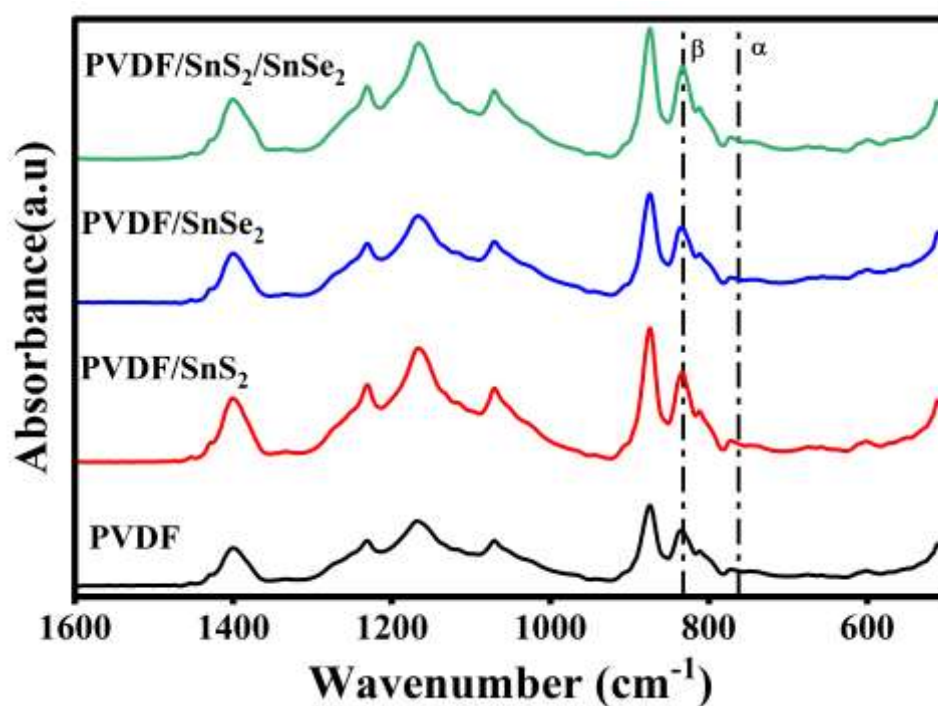


Fig. 9: FTIR spectra of synthesized thin films.

Table 02:  $\beta$ -Phase of synthesised  $\text{SnS}_2/\text{SnSe}_2$  powder incorporated PVDF (different wt. %).

| Wt. % of $\text{SnS}_2/\text{SnSe}_2$ | $\beta$ -phase (%) |
|---------------------------------------|--------------------|
| 0                                     | 61                 |
| 1                                     | 77.8               |
| 3                                     | 81.5               |
| 5                                     | 76.2               |
| 7                                     | 75.6               |

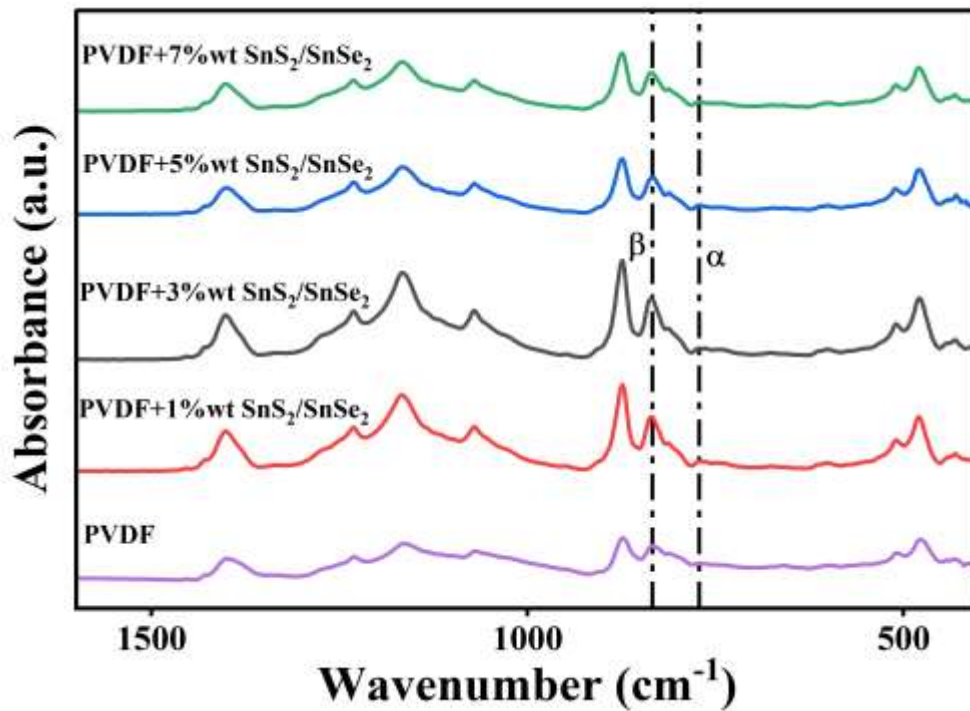


**Fig. 10: FTIR spectra of synthesized SnS<sub>2</sub>/SnSe<sub>2</sub> films incorporated with PVDF at different weight percentage.**

### 3.2.7 Electrical result Analysis


To analyse the piezoelectric response of the fabricated films incorporated with PVDF at 3 wt%, the open-circuit voltage ( $V_{oc}$ ) and short-circuit current ( $I_{sc}$ ) were evaluated, shown in Fig. 11 and 12. These measurements were made using the Tektronix MD034 oscilloscope and the Keysight B2985B electrometer. These values directly indicate the induced piezoelectric voltage in the sample, thereby signifying the efficient piezoelectric results of the samples. A higher value of  $V_{oc}$  and  $I_{sc}$  shows enhanced effective dipole alignment and separation of charges. The maximum piezo response for the thin films was observed at a resonant frequency of 7 Hz. The experimental value for  $V_{oc}$  was observed to be 5.79 V for bare PVDF, however when enhanced with TMDC nanofillers, the resultant voltage was inferred to be 10.82, 7.46

and 13.20 V for SnS<sub>2</sub>, SnSe<sub>2</sub>, and SnS<sub>2</sub>/SnSe<sub>2</sub> respectively. The values of the short-circuit current of the piezoelectric devices fabricated using PVDF and the TMDC nanofillers at 3 wt.% was reported to be 0.15, 0.57, 0.29 and 0.87  $\mu$ A for bare PVDF, SnS<sub>2</sub>, SnSe<sub>2</sub> and SnS<sub>2</sub>/SnSe<sub>2</sub> respectively.

This enhancement in the values of  $V_{oc}$  and  $I_{sc}$  corresponds to the collegial effects of improved dipole alignment arising from the broken centro and mirror symmetry in the nanofillers. As the  $\beta$ -phase content also complied to a similar trend, it can be inferred that by introducing asymmetry in the nanofillers, its piezoelectric response is enhanced. Therefore, the heterostructure stands out as the most promising candidate for energy harvesting applications.

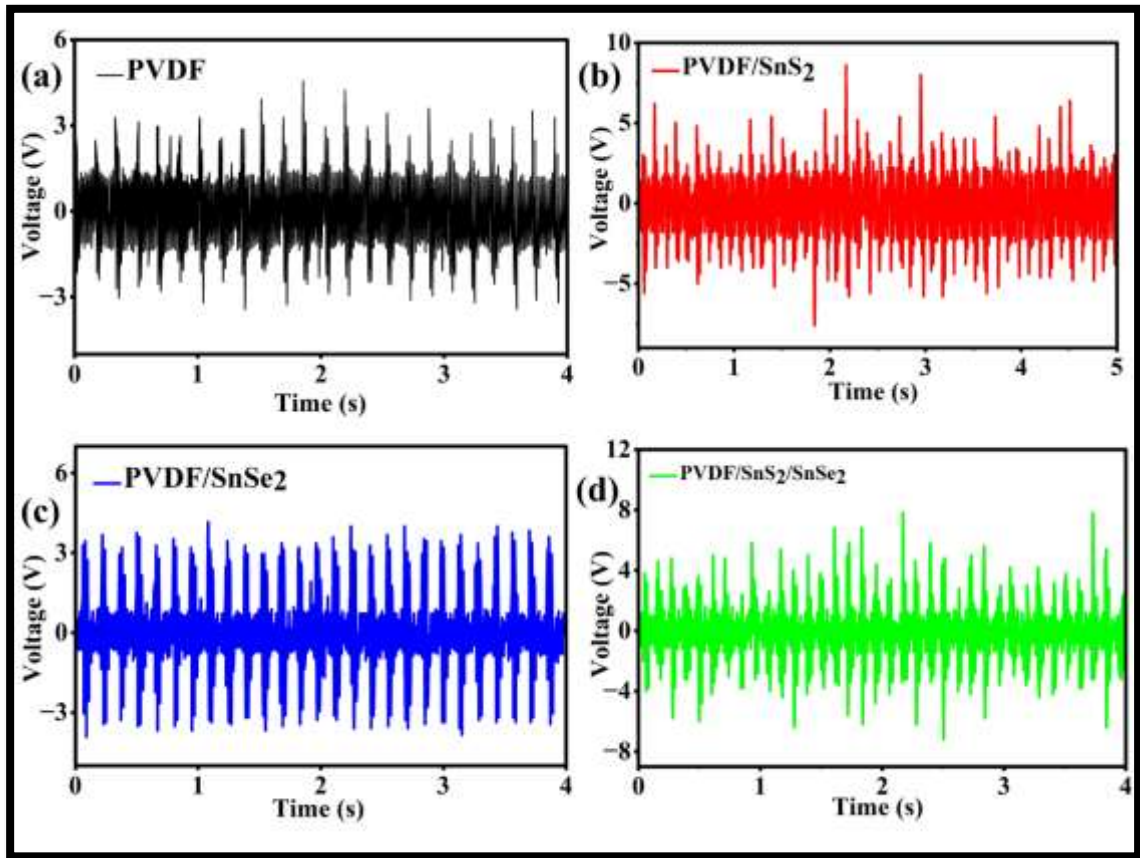

**Fig. 11: Open circuit voltage for (a) PVDF, (b) PVDF/SnS<sub>2</sub>, (c) PVDF/SnSe<sub>2</sub>, (d) PVDF/SnS<sub>2</sub>/SnSe<sub>2</sub> thin film nanogenerators at different tapping frequencies.**

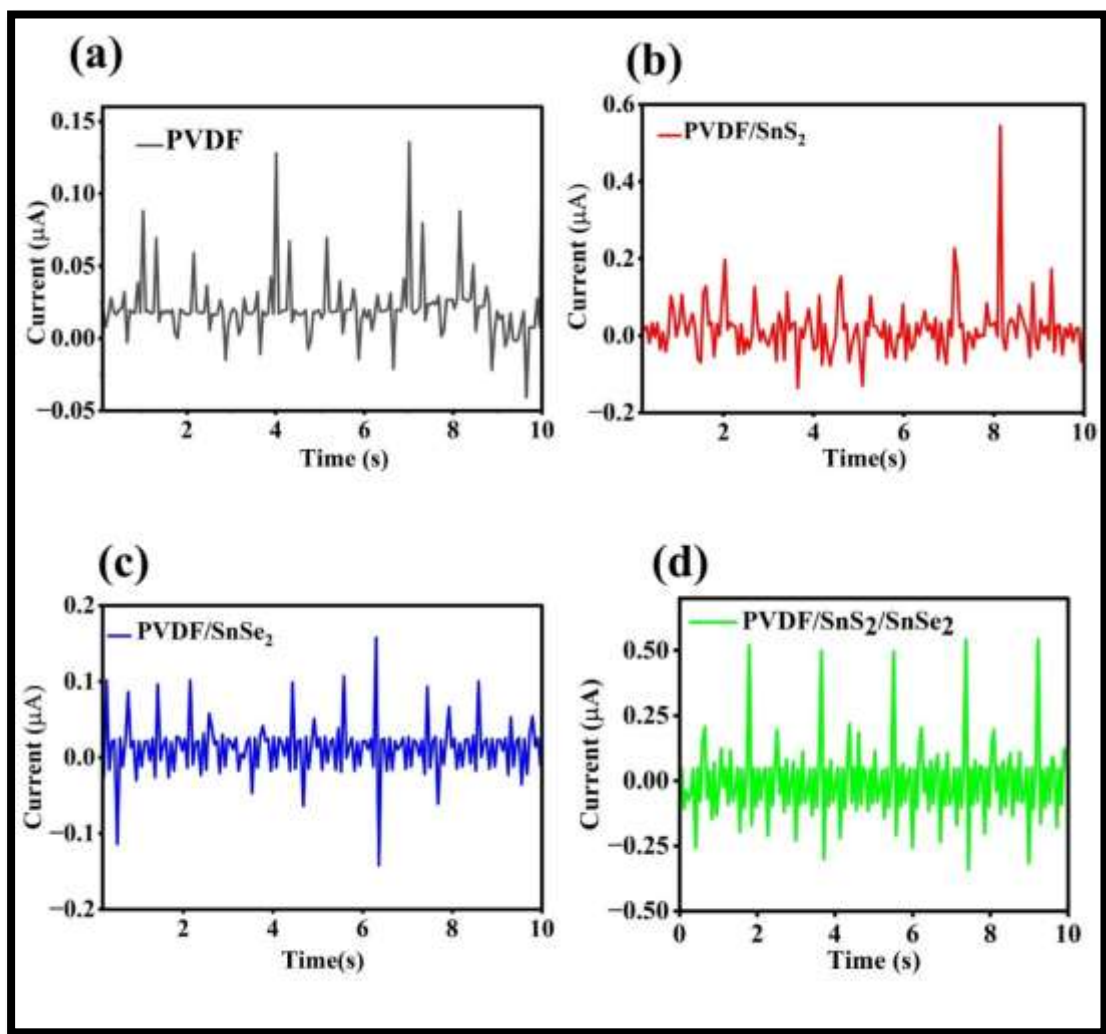


**Fig. 12:** Short circuit current for (a) PVDF, (b) PVDF/SnS<sub>2</sub>, (c) PVDF/SnSe<sub>2</sub> and (d) PVDF/SnS<sub>2</sub>/SnSe<sub>2</sub> thin film nanogenerators by continuous tapping at 7 Hz frequency.

**Table 3: Comparison of piezoelectric output of PVDF and TMDC nanocomposite films**

| Nanogenerator                            | V <sub>oc</sub> (V) | I <sub>sc</sub> (μA) | P <sub>r</sub> (μF/cm <sup>-2</sup> ) |
|------------------------------------------|---------------------|----------------------|---------------------------------------|
| PVDF                                     | 5.8                 | 0.15                 | 6.13 × 10 <sup>-2</sup>               |
| PVDF/SnS <sub>2</sub>                    | 10.8                | 0.57                 | 7.49 × 10 <sup>-2</sup>               |
| PVDF/SnSe <sub>2</sub>                   | 7.4                 | 0.29                 | 7.58 × 10 <sup>-2</sup>               |
| PVDF/SnS <sub>2</sub> /SnSe <sub>2</sub> | 13.2                | 0.87                 | 8.78 × 10 <sup>-2</sup>               |

### 3.2.8. Piezoelectric Nanogenerator (PENG)

Our present work reports the fabrication of flexible piezoelectric nanogenerators using PVDF enhanced Tin based 2D dichalcogenides namely SnS<sub>2</sub>, SnSe<sub>2</sub> and their heterostructure SnS<sub>2</sub>/SnSe<sub>2</sub>. A PENG works on the principle of piezoelectric effect, converting any form of mechanical stress and deformities into electrical energy. In its initial state as shown in Fig. 13, that without any applied force, the dipole alignment within the PVDF based matrix is randomly oriented creating no net electrical output. However, when a periodic mechanical force is applied, the film undergoes deformation, causing an alignment within dipoles, thereby generating a piezoelectric potential across the electrodes. This causes an accumulation of charge on the electrodes producing a potential difference which causes electrons to move through the external circuitry. Upon releasing the applied force, the dipoles revert back to their original state, hence creating a reversed charge flow. This periodic process of deformation and relaxation induces alternating electrical signals corresponding to successive cycles of compression and release.

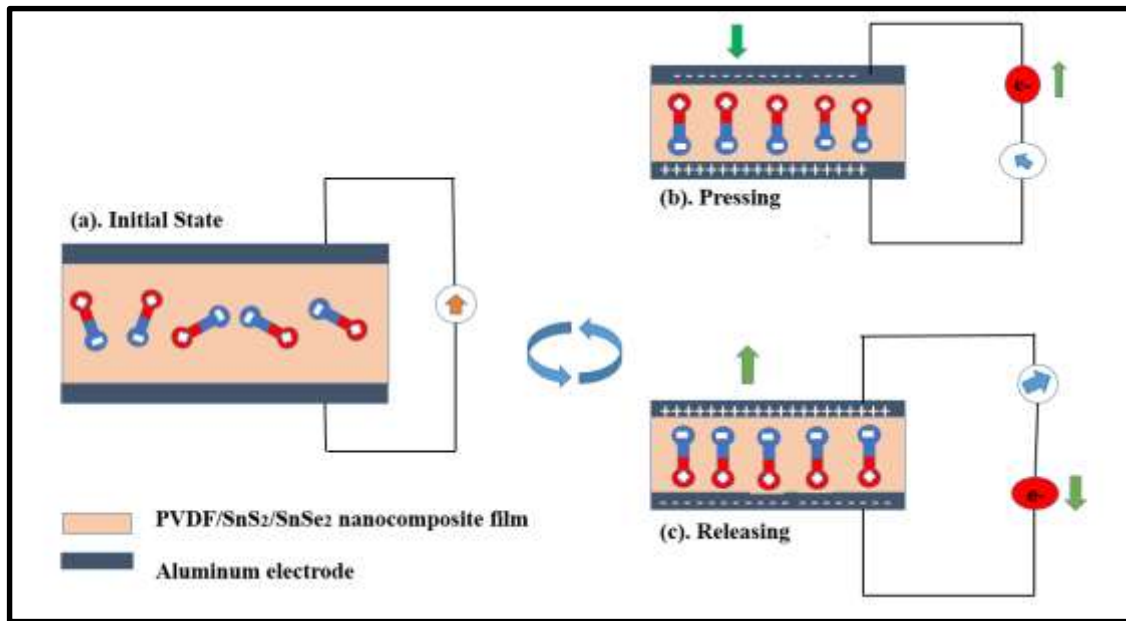


**Fig.13: Schematic of piezoelectric response of PVDF/SnS<sub>2</sub>/SnSe<sub>2</sub> based device with aluminium electrodes: (a) initial dipole orientation, (b) dipole alignment under pressing, and (c) reversed electron flow upon releasing.**

For evaluating the electrical response of the devices, the SnS<sub>2</sub>/SnSe<sub>2</sub> heterostructure based PENG was exposed to periodic mechanical stress. When subjected to biomechanical stimuli, using single finger and thumb tapping, the PENG exhibited an output voltage of 0.67 V and 0.74 V respectively, as depicted in Fig.14 (a) and (b). The resulting alternating piezoelectric response was made to pass through a bridge rectifier circuit to convert it into a unidirectional signal as depicted in Fig. 14(c). Post this, the rectified response was stored in a capacitor thus enabling effective charge accumulation and stable energy delivery to the external loads. The obtained output was thus rectified and stored in the capacitor and was successfully used to power an LED shown in Fig. 14(d).

The open circuit voltage (peak-to-peak) and short circuit current values exhibited a stable and periodic signal over multiple cycles, thereby indicating that the nanocomposite films are mechanically robust and possess good durability. Among all the devices, the

heterostructure based PENG demonstrated a superior electrical output. In addition to this, the presence of  $\text{SnS}_2$  and  $\text{SnSe}_2$  with distinct chalcogen atoms further enhances the asymmetric charge distribution and efficient charge separation within the nanofiller induced PVDF matrix.

This improved electrical output was supported by the XRD and FTIR analysis which confirmed the enhanced dipole alignment along with the effective incorporation of nanofillers within the PVDF polymer matrix. All these results showed the potential of Tin based dichalcogenides heterostructure integrated with PVDF for its application in flexible, self-powered and wearable energy harvesting systems.

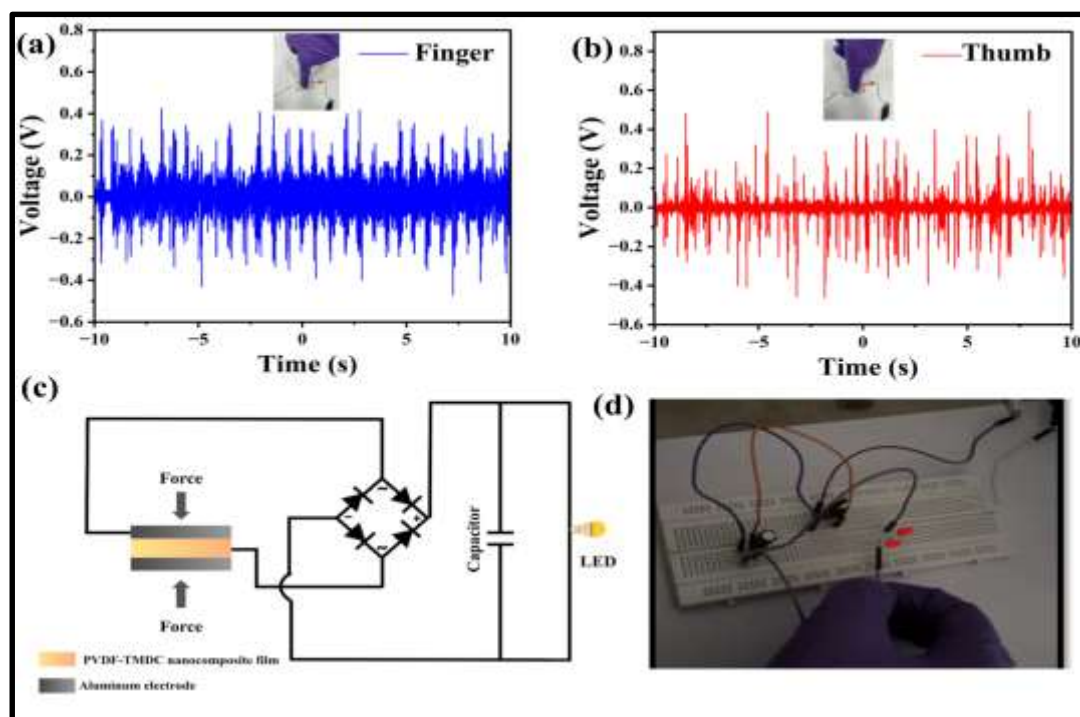

**Fig. 14: Open-circuit voltage (peak-to-peak) of PENG under applied force from (a). finger (b). thumb, (c). Schematic illustration of PENG circuit for operating an LED and (d). LED powered by PENG.**

## **CHAPTER 4**

### **CONCLUSION AND FUTURE SCOPE**

#### **4.1 Conclusion**

This work successfully shows the fabrication of PVDF/TMDCs nanocomposites based films for different materials, PVDF/SnS<sub>2</sub>, PVDF/SnSe<sub>2</sub> and PVDF/SnS<sub>2</sub>/SnSe<sub>2</sub>. The powdered samples were prepared by hydrothermal method which were then used as nanofillers within the PVDF polymer matrix as thin films using drop casting method. The SnS<sub>2</sub>/SnSe<sub>2</sub> heterostructure PENG demonstrated the maximum output performance. The values of  $P_r$  values of PVDF, SnS<sub>2</sub>/PVDF, SnSe<sub>2</sub>/PVDF, SnS<sub>2</sub>/SnSe<sub>2</sub>/PVDF are evaluated from the PE loop and are  $6.13 \times 10^{-2}$ ,  $7.49 \times 10^{-2}$ ,  $7.58 \times 10^{-2}$  and  $8.78 \times 10^{-2} \mu\text{C cm}^{-2}$  respectively. The output voltages were observed to be 10.82 V, 7.46 V and 13.20 V for SnS<sub>2</sub>, SnSe<sub>2</sub>, and SnS<sub>2</sub>/SnSe<sub>2</sub> respectively. The short-circuit current was reported to be 0.15  $\mu\text{A}$ , 0.57  $\mu\text{A}$ , 0.29  $\mu\text{A}$  and 0.87  $\mu\text{A}$  for bare PVDF, SnS<sub>2</sub>, SnSe<sub>2</sub> and SnS<sub>2</sub>/SnSe<sub>2</sub> respectively. The fundamental reasons responsible for their enhanced response of the heterostructure based device is the improved value of electroactive beta-phase and the increased values of  $P_r$  values of the PVDF films post the incorporation TMDCs nanofillers. The device was tested under biomechanical forces via single finger and thumb tapping to show the practical application of the fabricated devices. On combining all the above obtained results, the PENG integrated with heterostructure SnS<sub>2</sub>/SnSe<sub>2</sub> exhibited the most superior performance. Therefore, we propose that this device can effectively employed for mechanical energy harvesting and for powering low powered electronic devices. Our design successfully demonstrates an efficient, scalable and robust PENG with a high capability of converting mechanical energy into electrical energy.

## 4.2 Future Scope

- Heterostructure engineering involving other 2-D materials like Mo and W based multicomponent TMDC systems can be investigated.
- Synthesis of asymmetric Janus materials like SnSSe using chalcogen substitution for improved piezoelectric performance and output.
- Integration of PENG into wearable electronics and self-powered sensors for real-life and practical applications.
- Heterostructure powder can also be utilized for the piezocatalytic degradation of organic pollutants and azo-dyes.

## **REFERENCES**

- [1] L. Liu, X. Guo, W. Liu, and C. Lee, "Recent progress in the energy harvesting technology—from self-powered sensors to self-sustained IoT, and new applications," *Nanomaterials*, vol. 11, p. 2975, 2021.
- [2] A. Riaz, M. R. Sarker, M. H. M. Saad, and R. Mohamed, "Review on comparison of different energy storage technologies used in micro-energy harvesting, WSNs, low-cost microelectronic devices: challenges and recommendations," *Sensors*, vol. 21, p. 5041, 2021.
- [3] S. Mohammadpourfazeli, S. Arash, A. Ansari, S. Yang, K. Mallick, and R. Bagherzadeh, "Future prospects and recent developments of polyvinylidene fluoride (PVDF) piezoelectric polymer; fabrication methods, structure, and electro-mechanical properties," *RSC advances*, vol. 13, pp. 370-387, 2023.
- [4] S. Chakraborty, S. Pal, and S. K. Ray, "Flexible Piezoelectric Nanogenerators Based on Sono-Chemically Exfoliated MoSe<sub>2</sub>–PVDF Nanocomposites for Efficient Energy Harvesting," *ACS Applied Energy Materials*, vol. 8, pp. 2620-2629, 2025.
- [5] M. Habib, I. Lantgios, and K. Hornbostel, "A review of ceramic, polymer and composite piezoelectric materials," *Journal of Physics D: Applied Physics*, vol. 55, p. 423002, 2022.
- [6] N. Ahbab, S. Naz, T.-B. Xu, and S. Zhang, "A comprehensive review of piezoelectric PVDF polymer fabrications and characteristics," *Micromachines*, vol. 16, p. 386, 2025.
- [7] L. Wu, Z. Jin, Y. Liu, H. Ning, X. Liu, Alamusi, *et al.*, "Recent advances in the preparation of PVDF-based piezoelectric materials," *Nanotechnology Reviews*, vol. 11, pp. 1386-1407, 2022.
- [8] K. Khan, A. K. Tareen, M. Aslam, R. Wang, Y. Zhang, A. Mahmood, *et al.*, "Recent developments in emerging two-dimensional materials and their applications," *Journal of Materials Chemistry C*, vol. 8, pp. 387-440, 2020.
- [9] M. Tannarana, "A review of recent developments in tin diselenide (SnSe<sub>2</sub>) photodetectors: self-powered to flexible devices," *The European Physical Journal Plus*, vol. 139, p. 843, 2024.


- [10] S. Gbadamasi, M. Mohiuddin, V. Krishnamurthi, R. Verma, M. W. Khan, S. Pathak, *et al.*, "Interface chemistry of two-dimensional heterostructures–fundamentals to applications," *Chemical Society Reviews*, vol. 50, pp. 4684-4729, 2021.
- [11] S. Jaidka, A. Gupta, D. Shelly, Y. Kaur, A. Garg, S. Y. Lee, *et al.*, "Structure-Property-Application Correlations of Early Transition Metal Chalcogenides: A Dichalcogenide-Centered Perspective," *Small*, p. e08246, 2026.
- [12] P. C. Sherrell, M. Fronzi, N. A. Shepelin, A. Corletto, D. A. Winkler, M. Ford, *et al.*, "A bright future for engineering piezoelectric 2D crystals," *Chemical Society Reviews*, vol. 51, pp. 650-671, 2022.
- [13] R. Sharma, K. S. Sharma, and D. Kumar, "Introduction to nanotechnology," *Nanomaterials in Clinical Therapeutics: Synthesis and Applications*, pp. 1-31, 2022.
- [14] K. U. Savitha, "Nanomaterials and Composites in Flexible and Wearable Electronics and Textiles," in *Advanced Nanomaterials and Composites: Volume 1*, ed: Springer, 2026, pp. 221-246.
- [15] R. Chaudhary, F. K. Saah, and G. Nagpal, "Structural and Chemical Properties of Nanomaterials," in *Nanomaterials Revolution*, ed: Jenny Stanford Publishing, 2026, pp. 69-90.
- [16] M. R. S. Patil, "Synthesis and Characterization of Nanostructured Inorganic Materials for Energy Storage Devices."
- [17] S. Samireddi, N. Mishra, and A. Chaubey, "Pyrolysis for Sustainable Energy Materials and Their Applications," 2026.
- [18] Z. Zhang, Y. Liu, J. Zuo, Y. Ji, and L. Zhang, "A review of humic acid production from lignocellulosic biomass using hydrothermal methods: Mechanisms, optimization, environmental impacts, and perspectives," *Biomass and Bioenergy*, vol. 213, p. 109373, 2026.
- [19] N. Mustapha and M. Hjiri, "Advances in eco-efficient and accelerated sol–gel routes for hybrid nanostructures," *Journal of Sol-Gel Science and Technology*, vol. 117, p. 59, 2026.
- [20] Z. Yao, S. Zhang, Z. Guan, B. Liu, Q. Guo, J. C. Ho, *et al.*, "Flexible self-powered electronics: Materials design, structure engineering, and multifunctional integration," *Matter*, 2026.

- [21] S. A. Basith, A. Chandrasekhar, and A. Arockiarajan, "Advancing Piezoelectric and Triboelectric Energy Harvesting Using Piezoelectric Polymer Composites," *Electroactive Polymer-Based Smart Materials and Applications*, pp. 159-183, 2026.
- [22] F. Fernández-Gil, N. Rosales-Cuello, and H. Palza, "high-performance piezoelectric nanogenerators based on polymer composites with conductive particles—from interfacial polarization to piezotronic effects," *Emergent Materials*, vol. 9, p. 16, 2026.
- [23] J. Liang, V. A. Roy, and W. Wu, "Powering the future of wearable electronics: integrated energy harvest and storage for self-sustaining systems," *International Journal of Extreme Manufacturing*, 2026.
- [24] L. Wang, F. Yang, Y. Pei, X. Yang, and L. Lorenz, "Packaging and integration of silicon carbide power devices," *Nature Reviews Electrical Engineering*, pp. 1-16, 2026.
- [25] V. Singh, D. Meena, H. Sharma, A. Trivedi, and B. Singh, "Investigating the role of chalcogen atom in the piezoelectric performance of PVDF/TMDCs based flexible nanogenerator," *Energy*, vol. 239, p. 122125, 2022.
- [26] A. Singla, A. Marwaha, and S. Marwaha, "Electronic Properties of 2D Materials," in *Graphene and Beyond*, ed: CRC Press, pp. 52-69.
- [27] Y. Li, Y. Zhao, Z. Liu, T. Li, C. Zhao, Y. Wu, *et al.*, "Direct Observation of Convergent Valence Bands and Dimensionality Decoupling in Thermoelectric Material SnS<sub>2</sub>," *Chinese Physics B*, 2026.
- [28] A. Ruiz-Clavijo, A. Bahrami, J. Charvot, S. Lehmann, J. Julin, D. Wolf, *et al.*, "Thickness-Driven Modulation of Electronic Transport in SnSe<sub>2</sub>-grown Films by Low-Temperature Atomic Layer Deposition," *Advanced Electronic Materials*, vol. 12, p. e00560, 2026.
- [29] J. Singh, "Van der Waals Heterostructures Based on Two-Dimensional Materials: Interface Physics, Interlayer Coupling, and Multifunctional Devices," *2D Materials*, 2026.
- [30] P. Yadav and B. Singh, "Systematic investigation of the effect of SnS<sub>2</sub> nanofiller content on the piezoelectric performance of the PVDF-TrFE-based nanogenerator," *Materials Today: Proceedings*, 2023.

- [31] L. Wen, F. Cheng, X. Zhao, L. Han, D. Zhao, and S. Wang, "Crystal facet engineering of 2D SnSe<sub>2</sub> photocatalysts for efficient degradation of malachite green organic dyes," *Nanomaterials*, vol. 15, p. 850, 2025.
- [32] L. Liu, D. Song, M. E. Kaiser, J. Liu, J. J. De Yoreo, and M. L. Sushko, "Epitaxial Growth of 2D Core-Crown SnS<sub>2</sub>/SnSe<sub>2</sub> Heterostructure Through Interfacial Modification with Polyvinylpyrrolidone," *Small*, vol. 21, p. 2410526, 2025.
- [33] V. Singh and B. Singh, "MoS<sub>2</sub>-PVDF/PDMS based flexible hybrid piezo-triboelectric nanogenerator for harvesting mechanical energy," *Journal of Alloys and Compounds*, vol. 941, p. 168850, 2023.
- [34] D. Borisenko, N. Kargin, and M. Rybin, "Raman Spectroscopy of Multilayer Graphene Structures with Various Twist Angles Between Layers," *Journal of Applied Spectroscopy*, vol. 92, pp. 762-769, 2025.
- [35] X. Cai, T. Lei, D. Sun, and L. Lin, "A critical analysis of the  $\alpha$ ,  $\beta$  and  $\gamma$  phases in poly (vinylidene fluoride) using FTIR," *RSC advances*, vol. 7, pp. 15382-15389, 2017.

## **Declaration Regarding Plagiarism**

We, Umesh Kumar and Pragya Dobhal, hereby declare that the work presented in this thesis is original and has been carried out by us under the guidance of our supervisor. The thesis has been checked using plagiarism detection software, and the overall similarity index is within the permissible limit prescribed by the institute. All sources of information, references, and contributions of others have been properly acknowledged and cited.

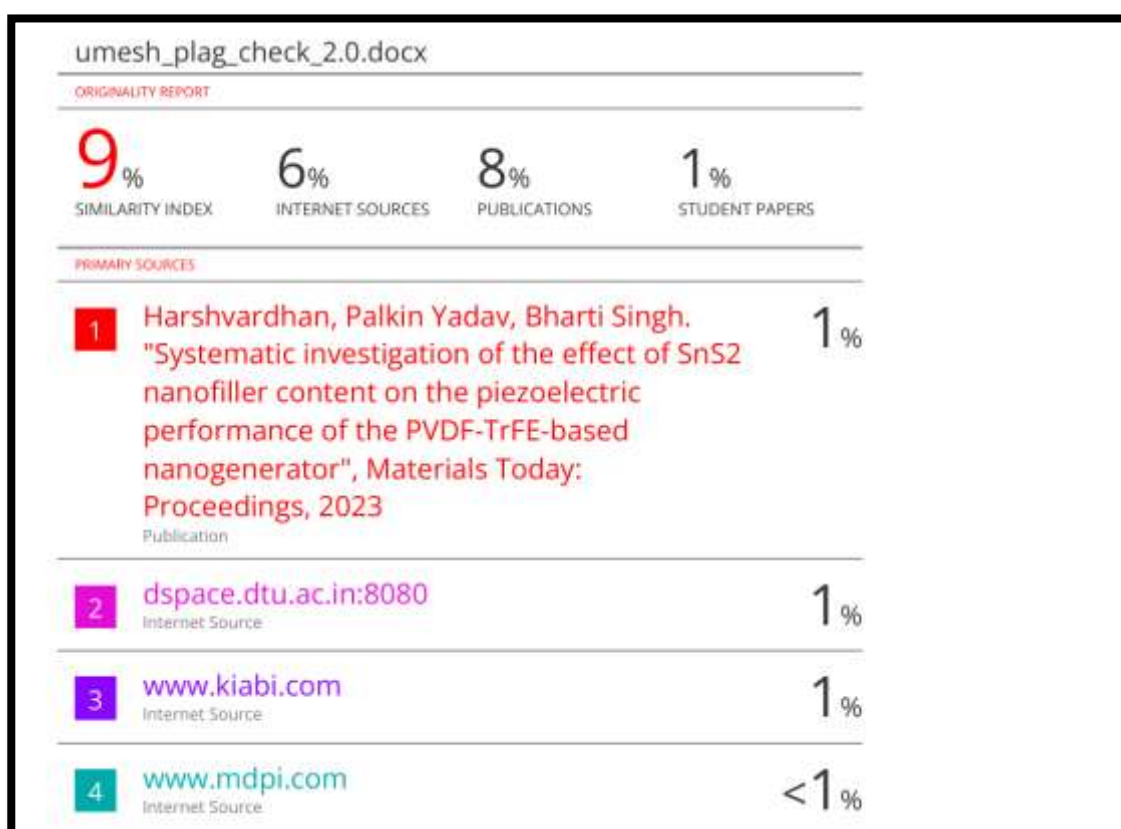


**Place:** Delhi

**Date:** 29/05/2026

## **Declaration Regarding AI Usage**

We, Umesh Kumar and Pragya Dobhal, hereby declare that no Artificial Intelligence (AI)-based tools were used in generating the scientific content, experimental analysis, interpretations, results, or conclusions presented in this thesis. The entire work presented in this thesis is our original contribution carried out under the guidance of our supervisor.

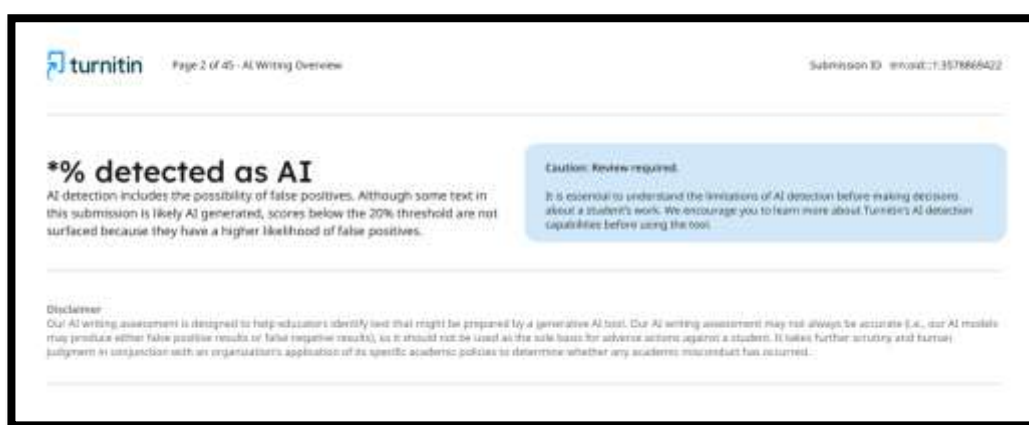


**Place:** Delhi

**Date:** 29/05/2026

## Conference Presentation and Participation


Participation and research presentation at the National Conference on “*Integrating Green Chemistry into Academia and Industry for Sustainable Development*” organized by the Department of Chemistry, Gargi College, where Umesh Kumar actively participated and Pragya Dobhal presented the research poster titled “*PVDF Integrated SnS<sub>2</sub>/SnSe<sub>2</sub> and their heterostructures (SnS<sub>2</sub>/SnSe<sub>2</sub>) based nanocomposites for enhanced piezocatalytic and photocatalytic dye degradation.*”

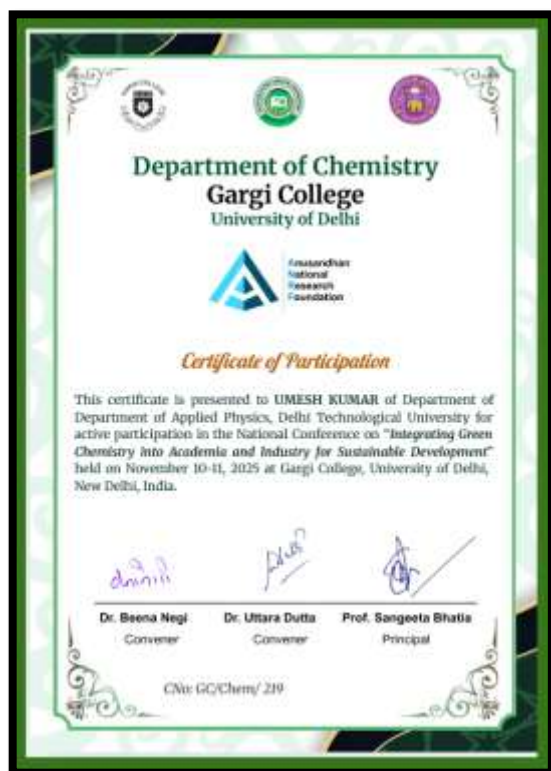

## **Research Paper Acceptance and Publication Status**

Our research work titled “*Investigating Improved Piezocatalytic Response Employing  $\text{SnS}_2/\text{SnSe}_2$  Heterostructure Nanofillers in PVDF Polymer Based Flexible Piezoelectric Nanogenerator Devices for Energy Harvesting Functionalities*” has been **officially accepted** for publication in the *Indian Journal of Pure & Applied Physics (IJPAP)*, a reputed *Scopus-indexed peer-reviewed journal* published by CSIR–National Institute of Science Communication and Policy Research (CSIR-NIScPR), Government of India. ***The manuscript successfully completed the editorial review and acceptance process***, reflecting the scientific significance and originality of the reported research work in the field of piezoelectric nanocomposites and energy harvesting applications.


The manuscript received its official **editorial acceptance on 18 May 2026** and is presently under the **production process for final publication** by the journal editorial office.

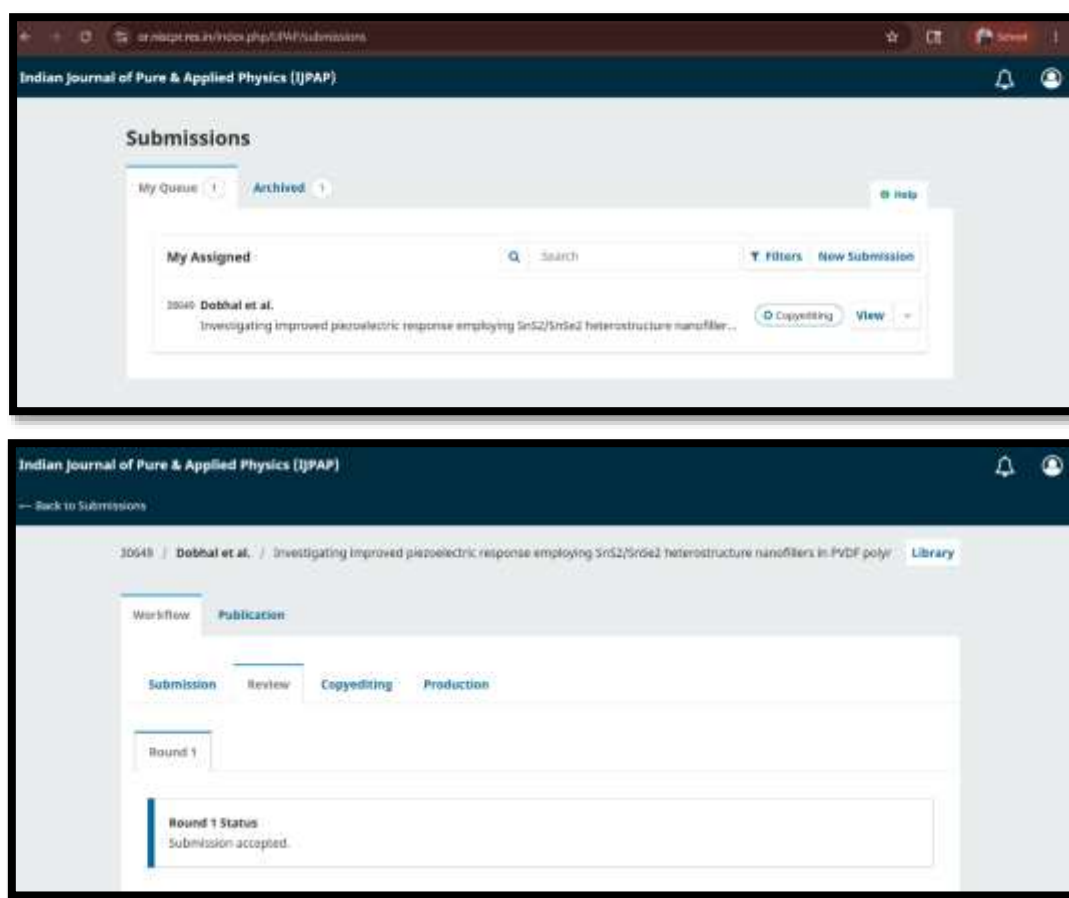

## **Declaration Regarding Journal Indexing**

We hereby declare that our research paper titled “*Investigating Improved Piezocatalytic Response Employing  $\text{SnS}_2/\text{SnSe}_2$  Heterostructure Nanofillers in PVDF Polymer Based Flexible Piezoelectric Nanogenerator Devices for Energy Harvesting Functionalities*” has been accepted for publication in the Indian Journal of Pure and Applied Physics, a reputed **Scopus-indexed, peer-reviewed international journal** published by the **National Institute of Science Communication and Policy Research (NIScPR), CSIR, Government of India**. The journal is indexed in the Scopus database with active coverage extending in the field of Physics and Astronomy.

According to the Scopus Source Details, the journal possesses a **CiteScore 2024 of 1.6**, **SJR 2024 of 0.176**, and **SNIP 2024 of 0.424**, reflecting its recognized academic visibility and research impact in the scientific community. The manuscript is currently under the production process following its editorial acceptance dated **18 May 2026**.

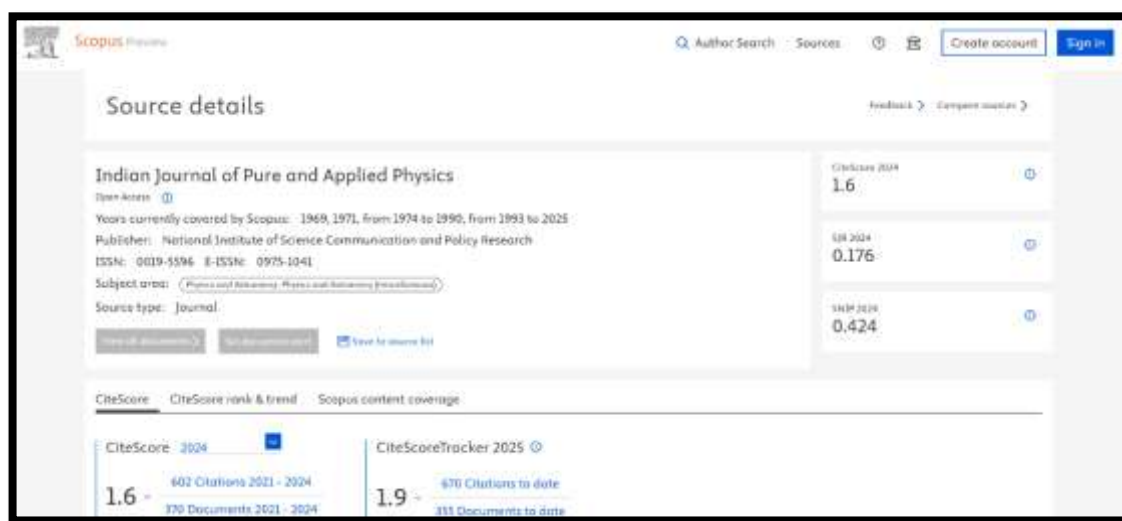

**Place:** Delhi

**Date:** 29/05/2026

[General Information](#)  
[Web of Science Coverage](#)  
[Journal Citation Report](#)  
[Open Access Information](#)  
[Peer Review Information](#)

INDIAN JOURNAL OF PURE & APPLIED PHYSICS

[Share This Journal](#)

ISSN / eISSN: 0038-5596 / 0975-1041

Publisher: NATL INST SCIENCE COMMUNICATION-RESEARCH, DR K S KRISHNAN MARG, PUSA CAMPUS, NEW DELHI, India, 110 012

General Information

|                                                     |                            |                    |         |
|-----------------------------------------------------|----------------------------|--------------------|---------|
| Journal Website                                     | <a href="#">Visit Site</a> | 1st Year Published | 2003    |
| Frequency                                           | Monthly                    | Issues Per Year    | 12      |
| Country / Region                                    | INDIA                      | Primary Language   | English |
| Avg. Number of Weeks from Submission to Publication | 18                         | Article DOIs       | No      |

Web of Science Coverage

| Collection       | Index                                  | Category                   | Similar Journals                      |
|------------------|----------------------------------------|----------------------------|---------------------------------------|
| Core Collection  | Science Citation Index Expanded (SCIE) | Physics, Multidisciplinary | <a href="#">Find Similar Journals</a> |
| Current Contents | Physical, Chemical & Earth Sciences    | Physics                    | <a href="#">Find Similar Journals</a> |
| Other            | Essential Science Indicators           | Physics                    | <a href="#">Find Similar Journals</a> |

[Return to Search Results](#)


**Place:** Delhi

**Date:** 29/05/2026

## **Declaration Regarding Editorial Acceptance**

We hereby declare that our research manuscript titled “*Investigating Improved Piezocatalytic Response Employing SnS<sub>2</sub>/SnSe<sub>2</sub> Heterostructure Nanofillers in PVDF Polymer Based Flexible Piezoelectric Nanogenerator Devices for Energy Harvesting Functionalities*” has received **provisional editorial acceptance** for publication in the Indian Journal of Pure & Applied Physics (IJPAP). The acceptance decision was officially communicated by the journal editorial office via email dated **18 May 2026**.

As per the editorial notification, the manuscript has successfully completed the review and evaluation process and has now entered the **production stage** for final publication. The paper is scheduled for publication in this ***Scopus-indexed peer-reviewed journal*** published by CSIR–National Institute of Science Communication and Policy Research (CSIR-NIScPR), Government of India.

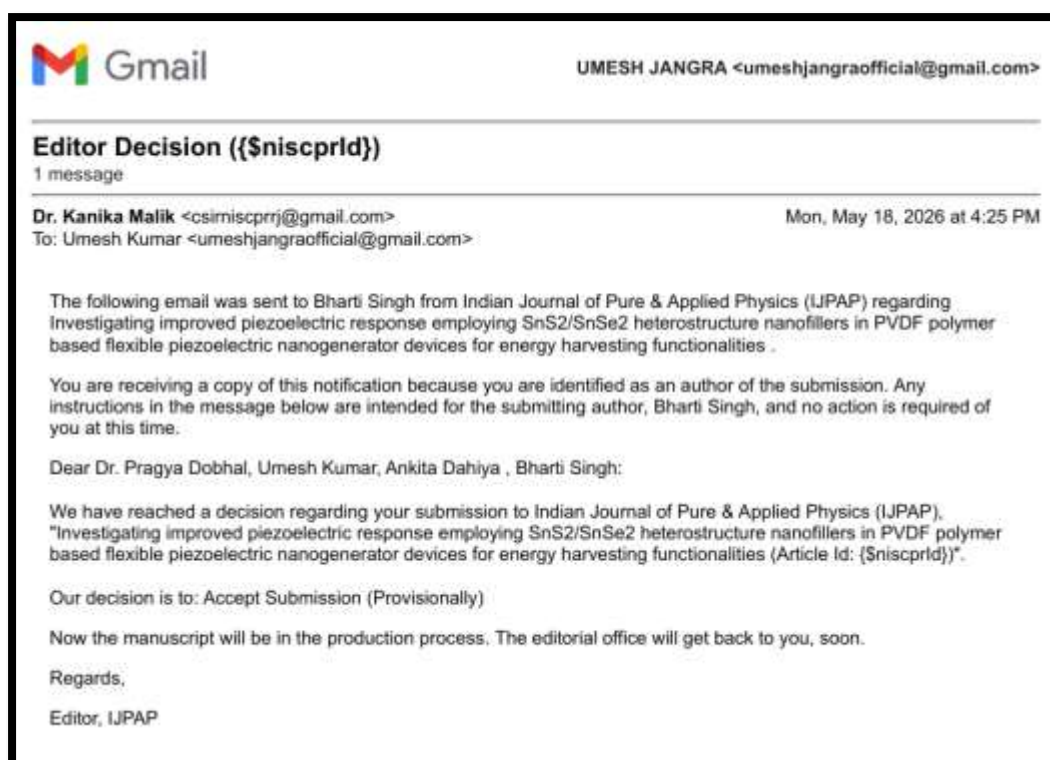

## Declaration Regarding Plagiarism

We, Umesh Kumar and Pragya Dobhal, hereby declare that the work presented in this thesis is original and has been carried out by us under the guidance of our supervisor. The thesis has been checked using plagiarism detection software, and the overall similarity index is within the permissible limit prescribed by the institute. All sources of information, references, and contributions of others have been properly acknowledged and cited.

umesh\_plag\_check\_2.0.docx

---

ORIGINALITY REPORT

---

|                  |                  |              |                |
|------------------|------------------|--------------|----------------|
| 9%               | 6%               | 8%           | 1%             |
| SIMILARITY INDEX | INTERNET SOURCES | PUBLICATIONS | STUDENT PAPERS |

---

PRIMARY SOURCES

---


|   |                                                                                                                                                                                                                                                       |     |
|---|-------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------|-----|
| 1 | Harshvardhan, Palkin Yadav, Bharti Singh.<br>"Systematic investigation of the effect of SnS2<br>nanofiller content on the piezoelectric<br>performance of the PVDF-TrFE-based<br>nanogenerator", Materials Today:<br>Proceedings, 2023<br>Publication | 1%  |
| 2 | dspace.dtu.ac.in:8080<br>Internet Source                                                                                                                                                                                                              | 1%  |
| 3 | www.kiabi.com<br>Internet Source                                                                                                                                                                                                                      | 1%  |
| 4 | www.mdpi.com<br>Internet Source                                                                                                                                                                                                                       | <1% |

Place: Delhi

Date: 29/05/2026

## Declaration Regarding AI Usage

We, Umesh Kumar and Pragya Dobhal, hereby declare that no Artificial Intelligence (AI)-based tools were used in generating the scientific content, experimental analysis, interpretations, results, or conclusions presented in this thesis. The entire work presented in this thesis is our original contribution carried out under the guidance of our supervisor.

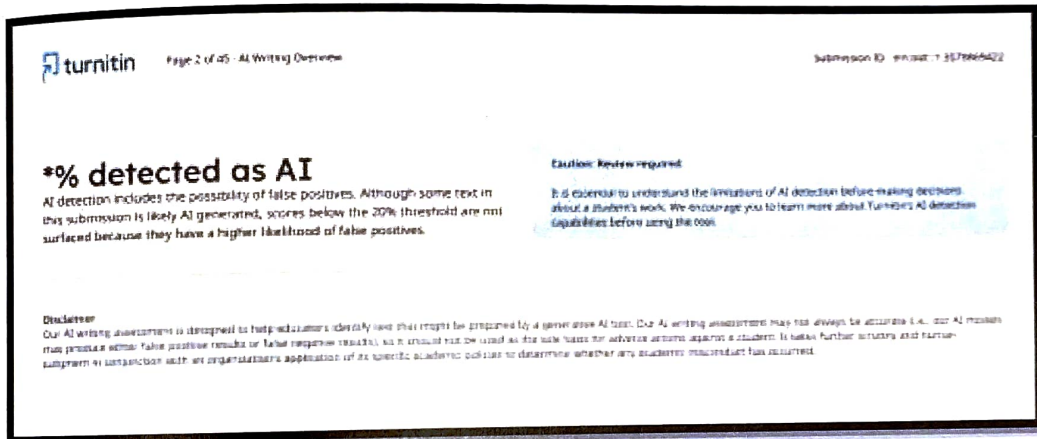

Place: Delhi

Date: 29/05/2026

*Umesh Kumar*

*Pragya*  
29/05/2026

*Shant*

## Declaration Regarding Editorial Acceptance

We hereby declare that our research manuscript titled "*Investigating Improved Piezocatalytic Response Employing SnS<sub>2</sub>/SnSe<sub>2</sub> Heterostructure Nanofillers in PVDF Polymer Based Flexible Piezoelectric Nanogenerator Devices for Energy Harvesting Functionalities*" has received provisional editorial acceptance for publication in the Indian Journal of Pure & Applied Physics (IJPAP). The acceptance decision was officially communicated by the journal editorial office via email dated **18 May 2026**.

As per the editorial notification, the manuscript has successfully completed the review and evaluation process and has now entered the production stage for final publication. The paper is scheduled for publication in this *Scopus-indexed peer-reviewed journal* published by CSIR–National Institute of Science Communication and Policy Research (CSIR-NIScPR), Government of India.

